

Cek_BCREC 13(2) 2018

by Maria Dewi

Submission date: 03-May-2021 09:09AM (UTC+0700)

Submission ID: 1576276999

File name: BCREC_13_2_2018_311-319.pdf (469.18K)

Word count: 5774

Character count: 29400

Research Article

Selective Hydrogenation of Dodecanoic Acid to Dodecane-1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy

R. Rodiansono^{1,*}, Muhammad Iqbal Pratama¹, Maria Dewi Astuti¹, A. Abdullah¹, Agung Nugroho², S. Susi²

¹Department of Chemistry, Faculty of Mathematics and Natural Sciences, Lambung Mangkurat University, Jl. A. Yani Km 36.0 Banjarbaru South Kalimantan, Indonesia.

²Department of Agro-industrial Engineering, Faculty of Agriculture, Lambung Mangkurat University, Jl. A. Yani Km 36.0 Banjarbaru South Kalimantan, Indonesia

Received: 26th November 2017; Revised: 24th December 2017; Accepted: 24th January 2018;
Available online: 11th June 2018; Published regularly: 1st August 2018

Abstract

Selective hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn alloy catalysts into dodecane-1-ol is demonstrated. Bimetallic nickel-tin supported on titanium oxide (Ni-Sn(1.5)/TiO₂) and gamma-alumina (Ni-Sn(1.5)/γ-Al₂O₃); 1.5 = Ni/Sn molar ratio) were synthesized via hydrothermal method in a sealed-Teflon autoclave reactor at 150 °C for 24 h, then followed by reducing with hydrogen gas at 400 °C for 1.5 h. The synthesized catalysts were characterized by means of XRD, IC-AES, N₂-adsorption (BET method), H₂-chemisorption, and NH₃-TPD. Bimetallic Ni-Sn(1.5)/TiO₂ catalyst was found to be effective for hydrogenation of dodecanoic acid (>99 % conversion) to dodecane-1-ol (93% yield) at 160 °C, 30 bar H₂, and 20 h and the highest dodecane-1-ol (97 % yield) was obtained at initial pressure of H₂, 50 bar. An increase of reaction temperature slightly enhanced the degree of hydrodeoxygenation of dodecanoic acid to produce dodecane over both Ni-Sn(1.5)/TiO₂ and Ni-Sn(1.5)/γ-Al₂O₃ catalysts. Copyright © 2018 BCREC Group. All rights reserved

Keywords: Bimetallic Nickel-Tin Alloy Catalyst; Dodecane; Dodecanoic Acid; Dodecane-1-ol; Hydrogenation

How to Cite: Rodiansono, R. Pratama, M.I., Astuti, M.D., Abdullah, A., Nugroho, A., Susi, S. (2018). Selective Hydrogenation of Dodecanoic Acid to Dodecane-1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy. *Bulletin of Chemical Reaction Engineering & Catalysis*, 13 (2): 311-319 (doi:10.9767/bcrec.13.2.1790.311-319)

Permalink/DOI: <https://doi.org/10.9767/bcrec.13.2.1790.311-319>

1. Introduction

The development of oleochemical products including surfactants, lubricants, plasticizers, dyes, and polymers has been made possible by remarkable advances made in organic syn-

thesis, catalysis, and biotechnology [1]. Fatty alcohol is one of the important basic oleochemicals which could be produced by hydrogenation of fatty acids or its esters by using heterogeneous catalysts (e.g. bimetallic copper chromite), but the reaction requires harsh temperature (e.g., up to 300 °C) and pressure (e.g., up to 300 bar of H₂) in the presence of copper-chromite catalysts, which are potentially harmful for the environ-

* Corresponding Author.

E-mail: rodiansono@ulm.ac.id (R. Rodiansono)
Telp: +62-5114773112, Fax: +62-5114782899

ment [2,3]. In this regard, the development of catalysts to produce fatty alcohols under milder conditions has been long-standing industrial target.

Many previous attempts on the reduction of the reaction pressures (down to 20 bar H_2) have been achieved with high conversion and selectivities by replacing Cu or Cr with noble metals such as Ru, Rh, Re, Pd, or Pt [4]. For example, the hydrogenation of carboxylic acids to alcohols using a Pt/TiO₂ catalyst as reported recently by Hardacre et al. at only 130 °C, 20 bar H_2 and gave over 80 % conversion (with 90 % selectivity) after 12 h [5]. Although these results are remarkable, it would be desirable to replace the expensive noble metals with more abundant and economic catalysts still capable of working at low H_2 pressures and moderate reaction temperatures. The commercial Ni-based catalysts such as: RANEY Ni/Kieselgur, or Ni/Al₂O₃ had been applied for fatty acids or fatty ester hydrogenation with high activity. However, the important drawbacks of these catalysts are low selectivity to desired products (i.e., produced the mixture of *cis*- and *trans*-product) and easily deactivated due to carbon deposited on the metal surface [6].

Interactions between metals in bimetallic catalysts can modify their surfaces, which can be beneficial for the conversion and upgrading of highly complex biomass derived compounds [7-9]. In previously published studies, several bimetallic alloy transition metal catalysts (e.g. Pd-M (M = Cu, Co, Ni) [10], Pd-Nb₂O₅ [11], Ru-Sn [12] Rh-Sn [13], and Ru-Ge-B [14] have shown superior performance for the selective hydrogenation of fatty acids compared with their single metal counterpart. Huang *et al.* [10] reported the catalytic performances of supported bimetallic Pd-M (M = Cu, Co, Ni) catalysts in hydrogenation of methyl palmitic in n-heptane solvent at 270 °C, H_2 55 bar within 7 h. Among these bimetallic catalysts, Pd-Cu/diatomite with loading amount of 1 % (Pd/Cu = 3) displayed the highest catalytic performances in hydrogenation of palmitic acid (99 % conversion) giving 1-hexadecanol (83 % yield) [10]. On the other hand, by using Pd/Nb₂O₅/SiO₂ catalyst, a significant improvement of 1-hexadecanol yield was achieved (c.a. 97 % yield) from palmitic acid in cyclohexane at 180 °C, H_2 25 bar, within 24 h of reaction time [11].

In previous reports, bimetallic Ru-based catalysts have also demonstrated high activity in hydrogenation of methyl oleate at relatively high temperature and H_2 pressure (ca. 270 °C and 44 bar, respectively) within 7 h. However,

the conversion of methyl oleate and selectivity of oleyl alcohol were only 80 % and 70 %, respectively. The addition of electropositive atom of Sn and B to Ru enhanced the dispersion of Ru and improved the electron density of Ru. The change of electron density Ru enhanced the affinity of Ru towards C=O bond of fatty acids which facilitated the reaction hydrogenation [12,13]. Similar results have been also reported on the hydrogenation of dodecanoic acid and palmitic acid at 300 °C, 60 bar H_2 , within 4 h over Ru-Sn/Al₂O₃ and Rh-Sn/Al₂O₃ catalysts and produced lauryl alcohol and hexadecane-1-ol, respectively. On the other hand, Ru-Ge-B/Al₂O₃ catalyst gave only 20 % of oleyl alcohol with conversion of methyl oleic, ca. 80 % [14].

In our previous investigations, we have reported the synthesis of both bulk and supported bimetallic Ni-Sn alloy catalysts from two types nickel precursors: *first*, from nickel salt (e.g. NiCl₂ or NiCl₂·4H₂O) produced from both bulk and supported Ni-Sn alloys [15] and, *second*, from Raney Ni-supported on aluminium hydroxide (R-Ni/AlOH), which produced a nickel-tin alloy supported on aluminium hydroxide (Ni-Sn(x)/AlOH; x = Ni/Sn molar ratio) [16]. We have also recently reported the catalytic performance of the Ni-Sn alloy during hydrogenation of biomass-derived levulinic acid water to γ -valerolactone (GVL) [17]. Over bulk Ni-Sn alloy catalysts, a relatively high reaction temperature (150 °C, 40 bar H_2 , 6 h) was applied to achieve both a high conversion and GVL yield (99 %) [18]. Alternatively, a GVL yield of >99 % was obtained over Ni-Sn(x)/AlOH catalysts at a lower reaction temperature (120 °C) compared to the bulk catalysts [19].

In this present report, we continue our extend investigation of the hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn alloy catalysts to the corresponding of lauryl alcohol. Bimetallic Ni-Sn alloy was supported on two types of supports c.a. titanium oxide (TiO₂) and gamma-alumina (γ -Al₂O₃). Monometallic nickel supported on TiO₂ (Ni/TiO₂) and γ -Al₂O₃ (Ni/ γ -Al₂O₃) catalysts were also evaluated for comparison.

2. Materials and Methods

2.1 Materials

Sodium hydroxide (NaOH) (97 %), nickel(II) chloride hexahydrate (NiCl₂·6H₂O, 99.9%), tin(II) chloride dihydrate (SnCl₂·2H₂O, 99.9%), aluminium hydroxide, and TiO₂ (mixture of rutile and anatase; S_{BET} = 50 m²g⁻¹) were pur-

chased and used as received from WAKO Pure Chemical Industries, Ltd. unless otherwise stated. The γ -Al₂O₃ ($S_{\text{BET}} = 100 \text{ m}^2\text{g}^{-1}$) were purchased from Japan Aerosil Co. All organic chemical compounds were purified using standard procedures prior to use.

2.2 Catalyst preparation

2.2.1 Synthesis of Ni-Sn(1.5)/TiO₂

A typical procedure of the synthesis of titanium oxide supported Ni-Sn (1.5 is feeding ratio) alloy catalyst is described as follows [15]: NiCl₂·6H₂O (7.2 mmol) was dissolved in deionized water (denoted as solution A), and SnCl₂·2H₂O (4.8 mmol) was dissolved in ethanol/2-methoxy ethanol (2:1) (denoted as solution B) at room temperature. A one-gram titanium oxide (TiO₂), solutions A, and B were mixed at room temperature; the temperature was subsequently raised to 50 °C and the mixture was stirred for 12 h. The pH of the mixture was adjusted to 12 through the dropwise addition of an aqueous solution of NaOH (3.1 M). The mixture was then placed into a sealed-Teflon autoclave for the hydrothermal reaction at 150 °C for 24 h. The resulting black precipitate was filtered, washed with distilled water, and then dried under vacuum overnight. Prior to the catalytic reaction, the obtained black powder was treated under hydrogen at 400 °C for 1.5 h.

2.2.2 Catalyst characterization

Powder X-ray diffraction (XRD) measurements were recorded on a Mac Science M18XHF instrument using monochromatic CuK α radiation ($\lambda = 0.15418 \text{ nm}$). The XRD was operated at 40 kV and 200 mA with a step width of 0.02° and a scan speed of 4° min⁻¹ ($\alpha_1 = 0.154057 \text{ nm}$, $\alpha_2 = 0.154433 \text{ nm}$). Inductively coupled plasma-atomic emission spectroscopy (ICP-AES) measurements were performed on an SPS 1800H plasma spectrometer by Seiko Instruments Inc. Japan (Ni: 221.7162 nm and Sn: 189.898 nm). The Brunauer-Emmett-Teller surface area (S_{BET}) and pore volume (V_p) were measured using N₂ physisorption at -196 °C on a Belsorp Max (BEL Japan). The samples were degassed at 200 °C for 2 h to remove physisorbed gases prior to the measurement. The amount of nitrogen adsorbed onto the samples was used to calculate the BET surface area via the BET equation. The pore volume was estimated to be the liquid volume of nitrogen at a relative pressure of approximately 0.995 ac-

ording to the Barrett-Joyner-Halenda (BJH) approach based on desorption data [20].

The H₂ uptake was determined through irreversible H₂ chemisorption. After the catalyst was heated at 100 °C under vacuum for 30 min, it was then heated at 400 °C under H₂ for 30 min. The catalysts were subsequently cooled to room temperature under vacuum for 30 min. The H₂ measurement was conducted at 0 °C, and the H₂ uptake was calculated according to a method described in the literature [21,22].

The NH₃-TPD was carried out on a Belsorp Max (BEL Japan). The samples were degassed at elevated temperature of 100-200 °C for 2 h to remove physisorbed gases prior to the measurement. The temperature was then kept at 200 °C for 2 h while flushed with He gas. NH₃ gas (balanced NH₃, 80 %, and He, 20 %) was introduced at 100 °C for 30 min, then evacuated by helium gas to remove the physisorbed also for 30 min. Finally, temperature programmed desorption was carried out at temperature of 100-800 °C and the desorbed NH₃ was monitored by TCD.

2.3 Catalytic reaction

Typical catalytic reaction procedure as follows. Catalyst (0.05 g), dodecanoic acid (1.8 mmol), internal standard 1,6-hexanediol (0.03 mmol) and *iso*-PrOH (5 mL) as solvent were placed into a glass reaction tube, which fitted inside a stainless-steel reactor. The reactor was flushed with H₂ for ~30 times. Finally, after H₂ was introduced into the reactor with an initial H₂ pressure of 30 bar at room temperature, the temperature of the reactor was increased to 160 °C. After 6 h of the reaction, both heating and stirring were stopped, the autoclave was removed from the hot plate and then cooled in ice-cold water. Once cooled, the contents of the autoclave were transferred into sample bin then centrifuged (~4000 rpm for 10 min) and ready for GC-FID analysis. The Ni-Sn(1.5)/TiO₂ catalyst was easily separated using either simple centrifugation (4000 rpm for 10 min) or filtration, then finally dried overnight under vacuum at room temperature prior to re-usability testing.

2.4 Product analysis

Gas chromatography analysis of the reactant (dodecanoic acid) and products was performed on a Perkin Elmer Autosystem XL with a flame ionization detector with an InertCap 225 (i.d. 0.25 mm, length 30 m, d.f. 0.25 mm) capillary column of GL Science Inc. Tokyo Ja-

pan. The products were confirmed by a comparison of their GC retention time, mass spectra with those of authentic sample. Gas chromatography-mass spectrometry (GC-MS) was performed on a Shimadzu GC-17B equipped with a thermal conductivity detector and an RT- β DEXsm capillary column.

The amount of remained reactant and products were determined from GC data using internal standard of 1,6-hexanediol that was introduced to the reactor before reaction run. Calibration curve was performed using known concentrations of internal standard, reactants and products in order to determine the correct response factors. The conversion of dodecanoic acid, yield, and selectivity of the products were calculated according to the following equations:

$$\text{Conversion} = \frac{F_0 - F_t}{F_0} \times 100\% \quad (1)$$

$$\text{Yield} = \frac{\text{mol product}}{F_0} \times 100\% \quad (2)$$

$$\text{Selectivity} = \frac{\text{mol product}}{\text{total mol products}} \times 100\% \quad (3)$$

where F_0 is the introduced mol reactant (dodecanoic acid), F_t is the remaining mol reactant, and ΔF is the consumed mol reactant (introduced mol reactant - remained mol reactant), which are all obtained from GC analysis using an internal standard technique.

3. Results and Discussion

3.1 Catalyst characterization

The chemical compositions, BET specific surface area (S_{BET}), and total pore volume (V_p) for γ - Al_2O_3 or TiO_2 supported Ni-Sn(1.5) catalysts after H_2 treatment at 400 °C for 1.5 h are summarized in Table 1. Based on the ICP-AES analyses, the compositions of the supported Ni-Sn alloy were approximately equivalent to the

feeding ratios of each precursor and were reflected in the composition of each Ni-Sn alloy phase. The total loading amount of Ni-Sn was 2.3~2.4 mmol.g⁻¹ for all of the supported Ni-Sn(1.5) samples (the composition (mol%) of Ni and Sn are listed in Table 1). The S_{BET} and total pore volume (V_p) of each supported Ni-Sn(1.5) alloy samples were also summarized in Table 1. It is found that the S_{BET} and V_p of Ni-Sn(1.5)/ γ - Al_2O_3 were 94 m².g⁻¹ and 0.39 cm³.g⁻¹, respectively (entry 1), while for Ni-Sn(1.5)/ TiO_2 were 52 m².g⁻¹ and 0.17 cm³.g⁻¹ (entry 2). It can be observed that S_{BET} and total pore volume of TiO_2 supported catalyst lower than that of γ - Al_2O_3 supported catalysts. It was reported that metal species lead more dispersible on support with lower porosity (e.g. TiO_2) due to strong interaction between metal and support which will prevent metal aggregation or sintering during thermal treatment [15,23].

The H_2 uptake for Ni-Sn(1.5)/ TiO_2 and Ni-Sn(1.5)/ γ - Al_2O_3 samples were 9.0 and 13.0 $\mu\text{mol.g}^{-1}$, respectively and the average Ni-Sn alloy crystallite sizes derived from Scherrer equation of Ni_3Sn_2 (101) phase at $2\theta = 30.8^\circ$ were 16 nm and 6 nm, respectively. The H_2 uptake supported Ni-Sn alloy in this work was much lower than that of the Raney Ni or supported Ni on aluminium hydroxide, suggesting that the presence of second metal of Sn reduced significantly the accessibility of hydrogen on the surface of Ni metal. Consequently, the catalytic reaction may be effectively proceeded at high pressure of H_2 as its have been reported previously [15-19].

The XRD patterns of Ni-Sn(1.5)/ γ - Al_2O_3 alloy catalyst after H_2 treatment at 400 °C for 1.5 h are shown in Figure 1. It can be observed easily that Ni_3Sn_2 species as major alloy phase was formed on γ - Al_2O_3 with sharpened peaks with very similar patterns to the JCPDS card standard of Ni_3Sn_2 of 6-414 [24]. On the other hand, the XRD patterns Ni-Sn(1.5)/ TiO_2 exhibited broadened peaks at $2\theta = 30.8^\circ$, 42.5° , and 44.2° , which correspond to the Ni_3Sn_2 (101),

Table 1. Chemical composition, BET surface area (S_{BET}), and total pore volume (V_p) for Ni-Sn(1.5)/ γ - Al_2O_3 and Ni-Sn(1.5)/ TiO_2 catalysts after H_2 treatment at 400 °C for 1.5 h.

Entry	Catalyst ^a	Comp. ^b (mol%)	S_{BET}^c (m ² .g ⁻¹)	V_p^c (cm ³ .g ⁻¹)
1	Ni-Sn(1.5)/ γ - Al_2O_3	Ni _{160.2} Sn _{39.8}	94	0.39
2	Ni-Sn(1.5)/ TiO_2	Ni _{160.4} Sn _{39.6}	52	0.17

^aThe value between the parenthesis is Ni/Sn molar ratio. ^bMolar composition of Ni or Sn, determined by ICP-AES. ^cDetermined by N_2 adsorption at -196 °C. The pore volume was estimated to be the liquid volume of nitrogen at a relative pressure of approximately 0.995 according to the Barrett-Joyner-Halenda (BJH) approach based on desorption data.

Ni_3Sn_2 (102), and Ni_3Sn_2 (117) diffraction peaks, respectively (Figure 2). These results suggest that the higher dispersions of Ni-Sn alloy on the TiO_2 were formed as roughly depicted in the average Ni_3Sn_2 (101) crystallite sizes, which were 6 nm (Table 2). In conclusion, the XRD analysis and H_2 measurement results confirm that Ni-Sn alloy phases were also formed on the supports and that their characteristics were consistent with the results observed for the bulk material as reported previously [15].

The results of ammonia-temperature programmed desorption (NH_3 -TPD) measurements of the synthesized catalysts are summarized in Table 3 and the NH_3 -TPD profiles are shown in Figure 3 and Figure 4. It can be observed that Ni-Sn(1.5)/ γ - Al_2O_3 alloy catalyst consisted of three different peak positions of 178, 510, and

607 °C with acidic amount of 0.23, 0.03, and 0.09 $\text{mmol}\cdot\text{g}^{-1}$, respectively (Figure 3 and Table 3, entry 1) with total number of acid sites = 0.35 $\text{mmol}\cdot\text{g}^{-1}$. Therefore, it can be concluded that Ni-Sn(1.5)/ γ - Al_2O_3 catalyst has mainly weak acid sites. On the other hand, Ni-Sn(1.5)/ TiO_2 displayed the peak position at 611 °C with total number of acidic sites = 0.29 $\text{mmol}\cdot\text{g}^{-1}$ that can be attributed to the strong acid sites (Figure 4 and Table 3, entry 2) [25, 26].

3.2 Hydrogenation of dodecanoic acid

3.2.1 Screening of catalysts

Results of selective hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn(1.5) catalysts are summarized in Table 4 and the reaction pathways are shown in

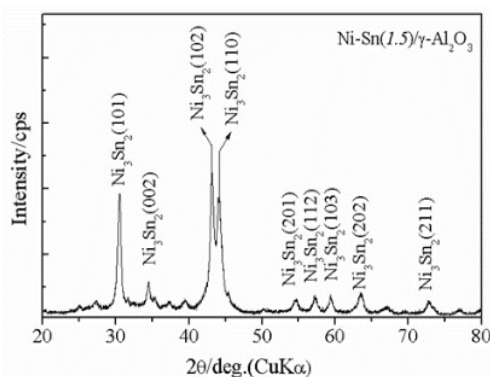


Figure 1. XRD patterns of bimetallic Ni-Sn(1.5) supported on γ - Al_2O_3 after H_2 treatment at 400 °C for 1.5 h

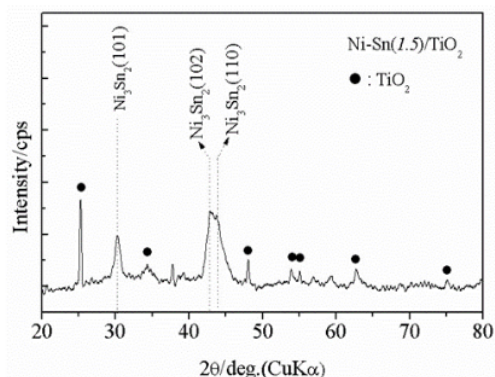


Figure 2. XRD patterns of bimetallic Ni-Sn(1.5) alloy supported on TiO_2 after H_2 treatment at 400 °C for 1.5 h

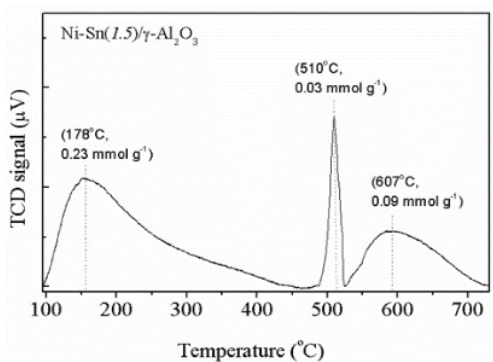


Figure 3. NH_3 -TPD spectra of Ni-Sn(1.5)/ γ - Al_2O_3 catalyst after H_2 treatment at 400 °C for 1.5 h

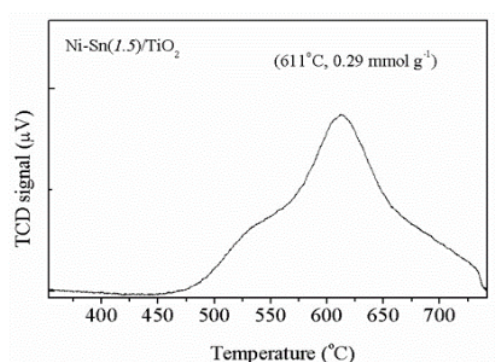


Figure 4. NH_3 -TPD spectra of Ni-Sn(1.5)/ TiO_2 catalyst after H_2 treatment at 400 °C for 1.5 h

4 Scheme 1. It can be observed that by using the Ni-Sn(1.5)/ γ -Al₂O₃ catalysts, the conversion of dodecanoic acid was 59 % with dodecane-1-ol yield was 40 % while dodecane-1,1-diol and dodecane yields were 1 % and 4 %, respectively (entry 1). The conversion of dodecanoic acid reached 89 % when the reaction time was extended to 16 h and yielded 57 % and 4 % of dodecane-1-ol and dodecane, respectively (entry 2). Interestingly, Ni-Sn(1.5)/TiO₂ catalyst displayed a high conversion of dodecanoic acid (c.a. 85 %) and high yield of dodecane-1-ol (c.a. 80 %) (entry 3). The yield of dodecane-1-ol increased significantly to 90 % (with 97 % conversion) without significant formation of by-product when the reaction time was extended to 16 h (entry 4). It can be observed that Ni-

Sn(1.5)/TiO₂ catalyst showed higher catalytic performance than that of Ni-Sn(1.5)/ γ -Al₂O₃. The high conversion of dodecanoic acid and the high yield of dodecane-1-ol over Ni-Sn(1.5)/TiO₂ can be attributed to the relatively high dispersion of Ni-Sn alloy on TiO₂ giving rise to active sites with a significantly higher catalytic activity. Alternatively, the high conversion and selectivity may be a result of the strong interactions between the active metals and TiO₂ generating significant interactions between C=O groups and Ni-TiO_x sites and leading to high selectivity to dodecane-1-ol [27].

The results of re-usability test confirmed that Ni-Sn(1.5)/TiO₂ catalyst was re-usable and the activity and selectivity of the catalyst can be restored to the initial after reducing with H₂

Table 2. H₂ chemisorption and average crystallite sizes of Ni₃Sn₂ alloy phase for Ni-Sn(1.5)/ γ -Al₂O₃ and Ni-Sn(1.5)/TiO₂ catalysts after H₂ treatment at 400 °C for 1.5 h

Entry	Catalyst ^a	H ₂ uptake ^b (mmol g ⁻¹)	D ^c (nm)
1	Ni-Sn(1.5)/ γ -Al ₂ O ₃	9.1	16
2	Ni-Sn(1.5)/TiO ₂	13.0	6

^aThe value between the parenthesis is Ni/Sn molar ratio. ^bBased on total H₂ uptake at 0 °C (noted after corrected for physical and chemical adsorption). ^cThe average crystallite sizes of Ni₃Sn₂(101) alloy phase at $2\theta = 30.8^\circ$ was derived from Scherrer equation.

Table 3. NH₃-TPD results for Ni-Sn(1.5) alloy supported on γ -Al₂O₃ and TiO₂ catalysts after H₂ treatment at 400 °C for 1.5 h

Entry	Catalyst ^a	NH ₃ -TPD data ^b	
		Peak position (°C)	Acidic amount ^c (mmol.g ⁻¹)
1	Ni-Sn(1.5)/ γ -Al ₂ O ₃	178 (weak)	0.23
		510 (medium)	0.03
		607 (strong)	0.09
2	Ni-Sn(1.5)/TiO ₂	611 (strong)	0.29

^aThe value in the parenthesis is Ni/Sn molar ratio. ^bAmmonia-temperature programmed desorption (NH₃-TPD). ^cAcidic amount (mmol.g⁻¹) was derived from NH₃-TPD spectra.

Table 4. Results of dodecanoic acid hydrogenation/hydrodeoxygenation over supported Ni-based catalysts

Entry	Catalyst ^a	LA of Ni ^b (mmol g ⁻¹)	Conversion ^c (%)	Yield ^c (%)			
				(1)	(2)	(3)	Others ^d
1	Ni-Sn(1.5)/ γ -Al ₂ O ₃	2.4	59	40	1	4	14
2 ^e	Ni-Sn(1.5)/ γ -Al ₂ O ₃	2.4	89	57	0	4	28
3	Ni-Sn(1.5)/TiO ₂	2.5	85	80	0	3	2
4 ^e	Ni-Sn(1.5)/TiO ₂	2.5	97	90	0	6	1
5 ^f	Ni-Sn(1.5)/TiO ₂	2.5	85	83	0	1	1
6 ^g	Ni-Sn(1.5)/TiO ₂	2.5	11	0	0	0	10
7	Ni/ γ -Al ₂ O ₃	2.7	55	23	0	7	25
8	Ni/TiO ₂	2.6	41	39	0	2	0
9	Sn/ γ -Al ₂ O ₃	3.7	0	0	0	0	0
10 ^h	Ni-Sn(1.5)/ γ -Al ₂ O ₃	2.4	>99	85	0	9	6

Reaction conditions: Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL, 160 °C; H₂ pressure 30 bar, reaction time is 6 h. ^aThe value in the parenthesis is Ni/Sn molar ratio. ^bLoading amount of Ni metal, determined by ICP-AES. ^cConversion and selectivity of the main products were determined by GC using an internal standard technique. Product (1) = dodecane-1-ol, (2) dodecane-1,1-diol, and (3) dodecane. ^dOther products were mainly C₁₁ hydrocarbon including undecane (C₁₁H₂₄), undecene (C₁₁H₂₂), and trace amount of cracking product like 1-pentylbenzene was identified by using GC-MS analysis. ^eReaction time was 16 h. ^fRe-usability test (second reaction run) after the recovered Ni-Sn(1.5)/TiO₂ was re-activated by reducing with H₂ at 400 °C for 1.5 h. ^gThe catalytic reaction in absence of H₂ gas. ^hReaction temperature was 180 °C, reaction time 6 h.


(85 % conversion and 83 % yield, entry 5). Catalytic reaction over Ni-Sn(1.5)/TiO₂ catalyst in absence of H₂ gas gave dodecanoic acid conversion of 11 % without the formation of hydrogenated products (entry 6). Compared to the supported bimetallic catalysts, monometallic Ni/ γ -Al₂O₃ and Ni/TiO₂ catalysts exhibited lower activity under the same reaction conditions (entries 7 and 8). Moreover, Sn/AlOH was not active as catalysts and did not produce the hydrogenated products under the same conditions (entry 9). In addition, Ni-Sn(1.5)/ γ -Al₂O₃ catalyst produced dodecane-1-ol (85 %), dodecane (9%), and other products (6 %) when the reaction temperature was 180 °C within 6 h (entry 10).

3.2.2 Profile of reaction kinetics

Kinetics of the hydrogenation of dodecanoic acid over bimetallic Ni-Sn(1.5)/TiO₂ and Ni-Sn(1.5)/ γ -Al₂O₃ catalysts are shown in Figure 5. When Ni-Sn(1.5)/ γ -Al₂O₃ catalyst was used, dodecanoic acid was slowly increased at the initial reaction time to achieve a 93 % yield after 24 h. Therefore, a similar explanation can be applied to the current results as follows. The induction periods could be associated with the slow formation of oxidic tin (Sn^{IV}) from metallic tin (Sn⁰), as reported by Sordelli *et al.* (Rh-Sn) [28] and Margitfalvi *et al.* (Pt-Sn) [29]. Since the crystallite size or dispersion of Ni-Sn alloy could affect the length of the induction period, the induction period of Ni-Sn(1.5)/TiO₂ diminished, and a 100 % dodecanoic acid conversion (~90 % dodecane-1-ol yield) was achieved after 20 h. The excellent catalytic performance of Ni-Sn(1.5)/TiO₂ produces a promising candidate suitable for the large-scale production of dodecane-1-ol from the selective hydrogenation of dodecanoic acid.

3.2.3 Effect of reaction temperature

The effect of reaction temperature on the catalytic performance of Ni-Sn(1.5)/TiO₂ in do-

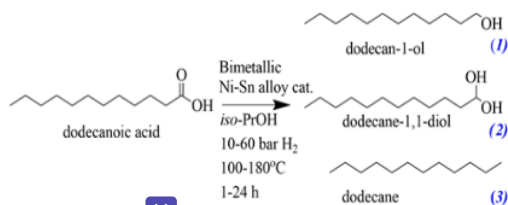

Scheme 1. Hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn(1.5) alloy catalysts.

decanoic acid hydrogenation are also investigated and the results are shown in Figure 6. The conversion of dodecanoic acid gradually increased as the increase of reaction temperature and reached to completed reaction at 180 °C within 6 h with dodecane-1-ol yield of 91 % (entry 4). A small amount of dodecane (4 % yield) and other products (total yield of 12 %) were observed at 100 °C and diminished at higher reaction temperature. These results indicated that further reaction of dodecane-1-ol did not occur effectively over Ni-Sn(1.5)/TiO₂ catalyst.

3.2.4 Effect of initial pressure of H₂

The effect of the initial H₂ pressure on the dodecanoic acid conversion and product selectivity is shown in Figure 7. The conversion of dodecanoic acid and dodecane-1-ol yield increased, whereas the selectivity of (2), (3), and other products decreased smoothly to almost 0% between 40-60 bar. The highest yield of dodecane-1-ol (97 %) was achieved at initial pressure H₂ of 50-60 bar, suggesting the hydrogenation reaction of dodecanoic acid to dodecane-1-ol over Ni-Sn(1.5)/TiO₂ catalyst can be proceed effectively under relatively high pressure of H₂. These results are consistent with the low H₂ uptake of bimetallic Ni-Sn(1.5)/TiO₂.

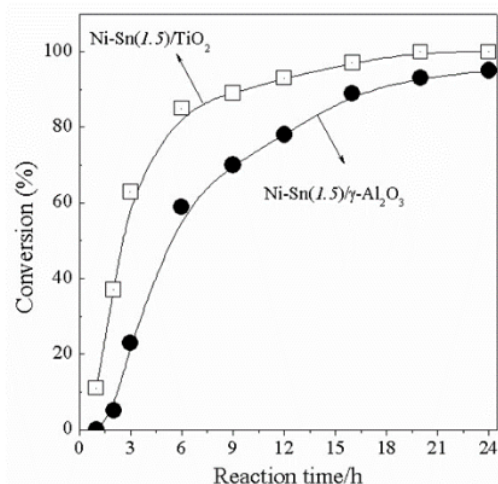


Figure 5. Kinetics of the hydrogenation of dodecanoic acid over bimetallic Ni-Sn(1.5)/TiO₂ and Ni-Sn(1.5)/ γ -Al₂O₃ catalysts. Reaction conditions: Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; iso-PrOH, 5 mL, 160 °C; H₂ pressure 30 bar, reaction time is 1-24 h

4. Conclusion

Selective hydrogenation of dodecanoic acid into dodecane-1-ol over supported bimetallic Ni-Sn alloy catalysts is demonstrated. Bimetallic Ni-Sn(1.5)/TiO₂ catalyst was found to be effective for hydrogenation of dodecanoic acid (>99 % conversion) to dodecane-1-ol (93 % yield) at 160 °C, 30 bar H₂, and 20 h and the highest dodecane-1-ol (97 % yield) was obtained at initial pressure of H₂ 50 bar. An increase of reaction temperature slightly enhanced the degree of hydrodeoxygenation of dodecanoic acid to produce dodecane over both Ni-Sn(1.5)/TiO₂ and Ni-Sn(1.5)/ γ -Al₂O₃ catalysts.

Acknowledgments

These works were financially supported by BPDP-Sawit, Ministry of Finances through GRK-2016 under contract number PRJ-49/2016. Partial these works were supported by Insentif Riset Pratama Individu (IRPI) FY 2016-2017 and International Publication Project of DGHE FY 2016 under Grant Number of DIPA-023-04.1.673453/2016 (XRD and ICP-AES measurements). We would also like thank to Dr. Husni Wahyu Wijaya for kind assistance in NH₃-TPD measurements.

References

- [1] Biermann, U., Bornscheuer, U., Meier, M.A.R., Metzger, J.O., Schafer, H.J. (2011). Oils and Fats as Renewable Raw Materials in Chemistry. *Angew. Chem., Int. Ed.* 50: 3854-3871.
- [2] Turek, T., Trimm, D.L., Cant, N.W. (1994). The Catalytic Hydrogenolysis of Esters to Alcohols. *Catal. Rev. Sci. Eng.* 36: 645-683.
- [3] Adkins, H., Connor, R. (1931). The Catalytic Hydrogenation of Organic Compounds over Copper Chromite. *J. Am. Chem. Soc.* 53: 1091-1095.
- [4] Rozmyslowicz, B., Kirilin, A., Aho, A., Manyar, H.G., Hardacre, C., Warna, J., Salmi, T., Murzin, D.Y. (2015). Selective Hydrogenation of Fatty Acids to Alcohols over Highly Dispersed ReO_x/TiO₂ Catalyst. *J. Catal.* 328: 197-207.
- [5] Manyar, H.G., Paun, C., Rilus, R., Rooney, D.W., Thompson, J.M., Hardacre, C. (2010). Highly Selective and Efficient Hydrogenation of Carboxylic Acids to Alcohols using Titania Supported Pt Catalysts. *Chem. Commun.* 46: 6279-6281.
- [6] Gallezot, P., Cerino, P.J., Blanc, B., Flèche, G., Fuertes, P. (1994). Glucose Hydrogenation on Promoted Raney-nickel Catalysts. *J. Catal.* 46: 93-102.

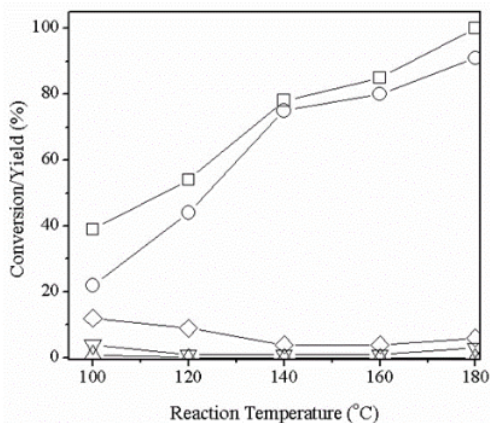


Figure 6. Results of dodecanoic acid hydrogenation over Ni-Sn(1.5)/TiO₂ at different reaction temperature. *Reaction conditions:* Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL; reaction temperature, 100-180 °C; H₂ pressure 30 bar; reaction time is 6 h. (□) Conversion of dodecanoic acid. (○) Yield of dodecane-1-ol. (△) Yield of dodecane-1,1-diol, and (▽) Yield of dodecane. (◇) Other products.

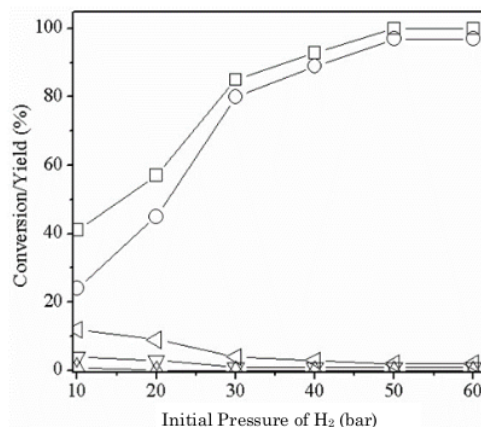


Figure 7. Results of dodecanoic acid hydrogenation over Ni-Sn(1.5)/TiO₂ at different initial pressure of H₂. *Reaction conditions:* Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL, 160 °C; H₂ pressure 10-50 bar; reaction time is 6 h. (□) Conversion of dodecanoic acid. (○) Yield of dodecane-1-ol. (△) Yield of dodecane-1,1-diol, and (▽) Yield of dodecane. (◇) Other products.

- [7] Alonso, D.M., Wettstein, S.G., Dumesic, J.A. (2012). Bimetallic Catalysts for Upgrading of Biomass to Fuels and Chemicals. *Chem. Soc. Rev.* 41: 8075-8098.
- [8] Pritchard, J., Filonenko, G.A., van Putten, R., Hensen, E.J.M., Pidko, E.A. (2015). Heterogeneous and Homogeneous Catalysis for the Hydrogenation of Carboxylic Acid Derivatives: History, Advances and Future Directions, *Chem. Soc. Rev.* 44: 3808-3833.
- [9] Besson, M., Gallezot, P., Pine, C. (2014). Conversion of Biomass into Chemicals over Metal Catalysts. *Chem. Rev.* 114: 1827-1870.
- [10] Huang, C., Zhang, H., Zhao, Y., Chen, S., Liu, Z. (2012). Diatomite-supported Pd-M (M = Cu, Co, Ni) Bimetal Nanocatalysts for Selective Hydrogenation of Long-chain Aliphatic Esters. *J. Coll. Interface Sci.* 386: 60-65.
- [11] Shao, Y., Xia, Q., Liu, X., Lu, G., Wang, Y. (2015). Pd/Nb₂O₅/SiO₂ Catalyst for the Direct Hydrodeoxygenation of Biomass-related Compounds to Liquid Alkanes under Mild Conditions. *ChemSusChem.* 8: 1761-1767.
- [12] Miyake, T., Makino, T., Taniguchi, S. I., Watanuki, H., Niki, T., Shimizu, S., Kojima, Y., Sano, M. (2009). Alcohol Synthesis by Hydrogenation of Fatty Acid Methyl Esters on Supported Ru-Sn and Rh-Sn Catalysts. *Appl. Catal. A.* 364: 108-112.
- [13] Deshpande, V. M., Patterson, W. R., Narasimhan, C. S. (1990). Studies on Ruthenium-tin Boride Catalysts I. Characterization. *J. Catal.* 121: 165-173.
- [14] Deshpande, V.M., Ramnarayan, K., Narasimhan, C.S. (1990). Studies on Ruthenium-tin Boride Catalysts II. Hydrogenation of Fatty Acid Esters to Fatty Alcohols. *J. Catal.* 21: 174-182.
- [15] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2012). Highly Efficient and Selective Hydrogenation of Unsaturated Carbonyl Compounds using Ni-Sn Alloy Catalysts. *Catal. Sci. Technol.* 2: 2139-2145.
- [16] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2012). A Novel Preparation Method of Ni-Sn Alloy Catalysts Supported on Aluminium Hydroxide: Application to Chemoselective Hydrogenation of Unsaturated Carbonyl Compounds. *Catal. Lett.* 41(8): 769-771.
- [17] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2014). Development of Nanoporous Ni-Sn Alloy and Application for Chemoselective Hydrogenation of Furfural to Furfuryl Alcohol. *Bull. Chem. React. Eng. Catal.* 9(1): 53-59
- [18] Rodiansono, R., Ghofur, A., Astuti, M.D., Sembiring, K.C. (2015). Catalytic Hydrogenation of Levulinic Acid in Water into γ -Valerolactone over Bulk Structure of Inexpensive Intermetallic Ni-Sn Alloy Catalysts. *Bull. Chem. React. Eng. Catal.* 10(2): 192-200.
- [19] Rodiansono, R., Astuti, M.D., Hara, T., Ichikuni, N., Shimazu, S. (2016). Efficient Hydrogenation of Levulinic Acid in Water using a Supported Ni-Sn Alloy on Aluminium Hydroxide Catalysts. *Catal. Sci. Technol.* 6: 2955-2961.
- [20] Lowell, S., Shields, J. E., Thomas, M. A., Thommes, M. (2004). *Characterization of Porous Solids and Powders: Surface Area, Pore Size and Density*, Kluwer Academic Publishers, Netherlands, Chapter 8.
- [21] Bartholomew, C.H., Pannel, R.B., Butler, J.L. (1980). Support and Crystallite Size Effects in CO Hydrogenation on Nickel. *J. Catal.* 65: 335-347.
- [22] Bartholomew, C.H., Pannel, R.B. (1980). The Stoichiometry of Hydrogen and Carbon Monoxide Chemisorption on Alumina- and Silica-supported Nickel. *J. Catal.* 65: 390-401.
- [23] Rodiansono, R., Astuti, M.D., Khairi, S., Shimazu, S. (2016). Selective Hydrogenation of Biomass-derived Furfural over Supported Ni₃Sn₂ Alloy: Role of Supports. *Bull. Chem. React. Eng. Catal.* 11(1): 1-9.
- [24] Powder Diffraction File, JCPDS-International Center for Diffraction Data (ICDD), 1991.
- [25] Dumitriu, E., Hulea, V.J. (2003) Effects of Channel Structures and Acid Properties of Large Pore Zeolites in the Liquid Phase Tert-butylation of Phenol. *J. Catal.* 218: 249-257.
- [26] Khandan, N., Kazemeini, M., Aghaziarati, M. (2008). Determining an Optimum Catalyst for Liquid Phase Dehydration of Methanol to Dimethyl Ether. *J. Appl. Catal. A.* 349: 6-12.
- [27] Dandekar, A., Vannice, M.A. (1999). Crotonaldehyde Hydrogenation on Pt/TiO₂ and Ni/TiO₂ SMSI Catalysts. *J. Catal.* 183: 344-354.
- [28] Sordelli, L., Psaro, R., Vlaic, G., Cepparo, A., Recchia, S., Fusi, A., Zanoni, R. (1999). EXAFS Studies of Supported Rh-Sn Catalysts for Citral Hydrogenation. *J. Catal.* 182: 186-198.
- [29] Margitfalvi, J. L., Tompos, A., Kolosova, I., Vallyon, J. (1998). Reaction Induced Selectivity Improvement in the Hydrogenation of Crotonaldehyde over Sn-Pt/SiO₂ Catalysts. *J. Catal.* 174: 246-249.

ORIGINALITY REPORT

15%

SIMILARITY INDEX

6%

INTERNET SOURCES

14%

PUBLICATIONS

2%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|--|----|
| 1 | Wahyu Satpriyo Putro, Takashi Kojima, Takayoshi Hara, Nobuyuki Ichikuni, Shogo Shimazu. "Selective hydrogenation of unsaturated carbonyls by Ni-Fe based alloy catalysts", Catal. Sci. Technol., 2017
Publication | 2% |
| 2 | Submitted to Universiti Teknologi Petronas
Student Paper | 2% |
| 3 | lib.dr.iastate.edu
Internet Source | 2% |
| 4 | Rodiansono, , Takayoshi Hara, Nobuyuki Ichikuni, and Shogo Shimazu. "A Novel Preparation Method of Ni —Sn Alloy Catalysts Supported on Aluminium Hydroxide: Application to Chemoselective Hydrogenation of Unsaturated Carbonyl Compounds", Chemistry Letters, 2012.
Publication | 2% |
| 5 | Vijaykumar S. Marakatti, Nidhi Arora, Sandhya Rai, Saurav Ch. Sarma, Sebastian C. Peter. "Understanding the Role of Atomic Ordering in | 1% |

the Crystal Structures of Ni Sn toward
Efficient Vapor Phase Furfural Hydrogenation
", ACS Sustainable Chemistry & Engineering,
2018

Publication

6

James Pritchard, Aysegul Ciftci, M.W.G.M. (Tiny) Verhoeven, Emiel J.M. Hensen, Evgeny A. Pidko. "Supported Pt-Re catalysts for the selective hydrogenation of methyl and ethyl esters to alcohols", *Catalysis Today*, 2017

Publication

7

Rodiansono Rodiansono, Maria Dewi Astuti, Kamilia Mustikasari, Sadang Husain, Sutomo Sutomo. "Recent progress in the direct synthesis of γ -valerolactone from biomass-derived sugars catalysed by Raney nickel-tin alloy supported on aluminium hydroxide", *Catalysis Science & Technology*, 2020

Publication

8

[epdf.tips](https://www.epdf.tips/)

Internet Source

9

Hara, Takayoshi, Masakazu Ishikawa, Junya Sawada, Nobuyuki Ichikuni, and Shogo Shimazu. "Creation of highly stable monomeric Pd(II) species in an anion-exchangeable hydroxy double salt interlayer: Application to aerobic alcohol oxidation under an air atmosphere", *Green Chemistry*, 2009.

10

Changming Li, Yudi Chen, Shitong Zhang, Simin Xu, Junyao Zhou, Fei Wang, Min Wei, David G. Evans, Xue Duan. "Ni-In Intermetallic Nanocrystals as Efficient Catalysts toward Unsaturated Aldehydes Hydrogenation", *Chemistry of Materials*, 2013

Publication

1 %

11

Michèle Besson, Pierre Gallezot, Catherine Pinel. "Conversion of Biomass into Chemicals over Metal Catalysts", *Chemical Reviews*, 2013

Publication

1 %

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On