
Your Submission - JECE-D-20-01602

1 message

Journal of Environmental Chemical Engineering <eesserver@eesmail.elsevier.com>

Wed, Jun 24, 2020 at 7:34 AM

Reply-To: Journal of Environmental Chemical Engineering <jece@elsevier.com>

To: ifnata@ulm.ac.id

Ms. Ref. No.: JECE-D-20-01602

Title: Selective adsorption of Pb (II) ion on amine-rich functionalized rice husk magnetic nanoparticle biocomposites in aqueous solution

Journal of Environmental Chemical Engineering

Dear Professor Nata,

Thank you for submitting the above paper to Journal of Environmental Chemical Engineering. Your manuscript needs major revisions.

The reviewers comments are included below for your attention. Please carefully address the issues raised in the comments. I invite you to submit your revised manuscript.

The due date for submitting your revised manuscript is Jul 24, 2020

If you are submitting a revised manuscript, please also:

a) outline each change made (point by point) as raised in the reviewer comments

AND

b) provide a suitable rebuttal to each reviewer comment not addressed

In order to facilitate the check of your manuscript, all the changes made during revision should appear in a different color. That is, the font color should be changed from black to red or blue (directly in the text) rather than using the track changes in Microsoft Word. A response letter for the revised manuscript should be sent to the editor along with your responses to the reviewer comments. These two steps are mandatory for the further review of the manuscript.

To submit your revision, please do the following:

1. Go to: <https://ees.elsevier.com/jece/>
2. Enter your login details
3. Click [Author Login]
This takes you to the Author Main Menu.
4. Click [Submissions Needing Revision]

PDFs are not acceptable revised manuscript files. Please prepare your manuscript text (with author details), tables, figure legends and any acknowledgements as a single Word file. Please prepare your Figures in an approved format (TIFF, EPS or MS Office files) with the correct resolution. Prepare any supporting information such as 'Response to Reviewers' as a separate Word file.

NOTE: Upon submitting your revised manuscript, please upload the source files for your article. For additional details regarding acceptable file formats, please refer to the Guide for Authors at: <http://www.elsevier.com/journals/journal-of-environmental-chemical-engineering/2213-3437/guide-for-authors>

When submitting your revised paper, we ask that you include the following items:

Manuscript and Figure Source Files (mandatory)

We cannot accommodate PDF manuscript files for production purposes. We also ask that when submitting your revision you follow the journal formatting guidelines. Figures and tables may be embedded within the source file for the submission as long as they are of sufficient visual quality. For any figure that cannot be embedded within the source file (such as *.PSD Photoshop files), the original figure needs to be uploaded separately. Refer to the Guide for Authors for additional information.

Highlights (optional)

Highlights consist of a short collection of bullet points that convey the core findings of the article and should be submitted in a separate file in the online submission system. Please use 'Highlights' in the file name and include 3 to 5 bullet points (maximum 85 characters, including spaces, per bullet point). See the following website for more information <http://www.elsevier.com/highlights>

Graphical Abstract (optional)

Graphical Abstracts should summarize the contents of the article in a concise, pictorial form designed to capture the attention of a wide readership online. Refer to the following website for more information: <http://www.elsevier.com/graphicalabstracts>

Please note that this journal offers a new, free service called AudioSlides: brief, webcast-style presentations that are shown next to published articles on ScienceDirect (see also <http://www.elsevier.com/audioslides>). If your paper is accepted for publication, you will automatically receive an invitation to create an AudioSlides presentation.

Journal of Environmental Chemical Engineering features the Interactive Plot Viewer, see: <http://www.elsevier.com/interactiveplots>. Interactive Plots provide easy access to the data behind plots. To include one with your article, please prepare a .csv file with your plot data and test it online at <http://authortools.elsevier.com/interactiveplots/verification> before submission as supplementary material.

MethodsX file (optional)

If you have customized (a) research method(s) for the project presented in your Journal of Environmental Chemical Engineering article, you are invited to submit this part of your work as MethodsX article alongside your revised research article. MethodsX is an independent journal that publishes the work you have done to develop research methods to your specific needs or setting. This is an opportunity to get full credit for the time and money you may have spent on developing research methods, and to increase the visibility and impact of your work.

How does it work?

- 1) Fill in the MethodsX article template: <https://www.elsevier.com/MethodsX-template>
- 2) Place all MethodsX files (including graphical abstract, figures and other relevant files) into a .zip file and upload this as a 'Method Details (MethodsX)' item alongside your revised Journal of Environmental Chemical Engineering manuscript. Please ensure all of your relevant MethodsX documents are zipped into a single file.
- 3) If your Journal of Environmental Chemical Engineering research article is accepted, your MethodsX article will automatically be transferred to MethodsX, where it will be reviewed and published as a separate article upon acceptance. MethodsX is a fully Open Access journal, the publication fee is only 520 US\$.

Questions? Please contact the MethodsX team at methodsx@elsevier.com. Example MethodsX articles can be found here: <http://www.sciencedirect.com/science/journal/22150161>

Include interactive data visualizations in your publication and let your readers interact and engage more closely with your research. Follow the instructions here: <https://www.elsevier.com/authors/author-services/data-visualization> to find out about available data visualization options and how to include them with your article.

MethodsX file (optional)

We invite you to submit a method article alongside your research article. This is an opportunity to get full credit for the time and money you have spent on developing research methods, and to increase the visibility and impact of your work. If your research article is accepted, your method article will be automatically transferred over to the open access journal, MethodsX, where it will be editorially reviewed and published as a separate method article upon acceptance. Both articles will be linked on ScienceDirect. Please use the MethodsX template available here when preparing your article: <https://www.elsevier.com/MethodsX-template>. Open access fees apply.

I look forward to receiving your revised manuscript.

Yours sincerely,

Guilherme Luiz Dotto, Ph.D
Editor
Journal of Environmental Chemical Engineering
Data in Brief (optional):

We invite you to convert your supplementary data (or a part of it) into an additional journal publication in Data in Brief, a multi-disciplinary open access journal. Data in Brief articles are a fantastic way to describe supplementary data and associated metadata, or full raw datasets deposited in an external repository, which are otherwise unnoticed. A Data in Brief article (which will be reviewed, formatted, indexed, and given a DOI) will make your data easier to find, reproduce, and cite.

You can submit to Data in Brief via the Journal of Environmental Chemical Engineering submission system when you upload your revised Journal of Environmental Chemical Engineering manuscript. To do so, complete the template and follow the co-submission instructions found here: www.elsevier.com/dib-template. If your Journal of Environmental Chemical Engineering manuscript is accepted, your Data in Brief submission will automatically be transferred to Data in Brief for editorial review and publication.

Please note: an open access Article Publication Charge (APC) is payable by the author or research funder to cover the costs associated with publication in Data in Brief and ensure your data article is immediately and permanently free to access by all. For the current APC see: www.elsevier.com/journals/data-in-brief/2352-3409/open-access-journal

Please contact the Data in Brief editorial office at dib-me@elsevier.com or visit the Data in Brief homepage (www.journals.elsevier.com/data-in-brief/) if you have questions or need further information.

Note: After the paper is accepted to production, we do not allow any authorship changes in your article since the editor would like to approve any changes to the authorship before acceptance of papers in EES.

Reviewers' comments:

Reviewer #1: The authors described a study for "Selective adsorption of Pb (II) ion on amine-rich functionalized rice husk magnetic nanoparticle biocomposites in aqueous solution". The approaches and problems addressed in this manuscript are within the scope of Journal of Environmental Chemical Engineering. But many problems have to be solved. The manuscript needs major revision. The specific comments are as follows:

1. There are a lot of grammatical errors. Author should remove all grammatical and spelling errors. Many places do not understand.
2. The abstract need be revised. Please further clarify the innovation points. Please add the result of characterization.
3. There are many water treatment technologies, such as adsorption, photocatalysis and microwave catalysis, should be introduced in the introduction. The advantages and disadvantages of these techniques should be introduced, followed by the introduction of adsorption techniques. The new references on adsorption, photocatalytic purification and microwave catalysis of wastewater should be introduced and cited. Adsorption: Journal of Hazardous Materials, 2020, 395:122686; Science of the Total Environment, 726 (2020) 138625
Microwave catalysis: Journal of Colloid and Interface Science, 2020, 574, 74-86
Photocatalytic purification: Journal of Colloid and Interface Science, 2020, 579: 37-49; Journal of Hazardous Materials, 2020, 399: 123070; J. Colloid Interf. Sci. 571 (2020) 275-284
4. Why select amine-rich functionalized rice husk magnetic nanoparticle biocomposites? Please explain the reason in detailed.
5. How is stability of materials?
6. The thermodynamic behavior of adsorption needs to be studied
7. Specific surface area is important for application of materials. In addition, please give N₂ adsorption-desorption and pore size distribution curve. The isotherm and hysteresis loop need be explained. BJH adsorption or desorption are selected for mesoporous ones. Please refer to and cite the literature for drawings and explanations. Journal of Colloid and Interface Science, 573 (2020) 11-20
8. Many of the references are old, so please quote the papers of the last three years, especially Journal of Environmental Chemical Engineering.
9. Amine group is important for adsorption. What is the content of amine? Please provide further evidence and role in the adsorption process.

Reviewer #2: 1. Please supplement the synthesis process of MH.

2. Some of the introductions in this article still need some latest references to support. For example: In Introduction, when introducing the heavy metal ions and their pollution, the following references (* Chemical Engineering Journal, 2019, 360, 750-761 and * Applied Surface Science, 2019, 483, 453-462) are suggested to cite. B) In Introduction, it is


recommended to introduce the specific advantages of magnetic nanoparticles and cite the following references (* Applied Catalysis B: Environmental, 2020, 268, 118433 and * Journal of Materials Chemistry A, 2019, 7, 13986-14000), which will be useful for readers.

3. It is best to mark the time of magnetic separation in the illustration in Figure 6.
4. Please supplement the optimization experiment regarding the optimal amount of adsorbent added.
5. To further analyze the adsorption properties of the material, combined with surface zeta potential analysis.
6. Why pH = 5 is selected as the parameter of the experimental process.
7. Please add N₂ adsorption-desorption experiment to prove the change of specific surface area of different materials.
8. This article does not make a detailed demonstration of the adsorption mechanism of the final material, please explain further.

Please note that the editorial process varies considerably from journal to journal. To view the submission-to-publication lifecycle, click here: http://help.elsevier.com/app/answers/detail/p/7923/a_id/160

For further assistance, please visit our customer support site at <http://help.elsevier.com/app/answers/list/p/7923>. Here you can search for solutions on a range of topics, find answers to frequently asked questions and learn more about EES via interactive tutorials. You will also find our 24/7 support contact details should you need any further assistance from one of our customer support representatives.

Selective adsorption of Pb(II) ion on amine-rich functionalized rice husk magnetic nanoparticle biocomposites in aqueous solution

 The corrections made in this section will be reviewed and approved by a journal production editor.

Iryanti Fatyasari [Nata*](mailto:ifnata@ulm.ac.id) ifnata@ulm.ac.id, Doni Rahmat [Wicakso](#), Agus [Mirwan](#), Chairul [Irawan](#), Divany [Ramadhani](#), [Ursulla](#)

Chemical Engineering Department, Faculty of Engineering, Lambung Mangkurat University, Jl. A. Yani Km. 35.5, Banjarbaru, South Kalimantan 70714, Indonesia

*Corresponding author.

Editor: G.L. Dotto

Abstract

Amine group on rice husk magnetic nanoparticle biocomposites (RHB-MH) was synthesized by one-step solvothermal method. The new finding of biocomposites is utilization of rice husk cellulose as a support which produced high amine content on surface of magnetic nanoparticle (MNPs). The rice husk cellulose (RH-D), iron(III) chloride hexahydrate, Na-acetate anhydrate were mixed in ethylene glycol, then kept at ± 200 °C for 6 h. Amine modified MNPs was constructed by addition of 1,6-hexanediamine in mixture before the reaction. The MNPs was growth on surface of RH-D then formed biocomposites. The Fe content about 93.11% and the magnetic nanoparticle structure was proved by specific peaks at 36° , 43° , 63° for magnetite. The magnetic saturation value of biocomposites about 16.4 emu/g. The thermal stability of biocomposites showed up to 200 oC with less than 10% of mass degradation. Higher amine content of 12.3 mmol/g on biocomposites was achieved after addition of 7 mL of 1,6-hexanediamine (RBH-MH2). Amine functional group on biocomposites exhibited the resonance bands at 1645 cm^{-1} and 1050 cm^{-1} . The adsorption of Pb(II) ion on RBH-MH2 follows pseudo 1 st order kinetic and well-fitted by Langmuir adsorption isotherm model which have maximum capacity of 680.19 mg/g at room temperature and $\text{pH} \sim 5$. The RBH-MH2 have significant effect to capture Pb(II) ion due to electrostatic interaction and showed 3.6-fold higher adsorption capacity than rice husk biocomposites without modification. The amine-rich on biocomposites does not only provide an easy retrievable from aqueous solution but also potential candidate for effective green adsorbent.

Keywords: Adsorption; Pb(II) ion; Magnetic nanoparticle; Rice husk; Solvothermal

1 Introduction

Recently, issue of environmental is a serious topic due to big effects to the environment and human. The contamination of water due to heavy metal and organic compound as well as dye has become a great environmental concern worldwide. Generally, heavy metal ions possess high toxicities and easily accumulated on organisms through the food chain mechanism [1]. One of dangerous metal ion is lead, when severe lead poisoning causes neonatal mortality and most serious effects is to break central nervous system [2]. Lead also can damage reproductive system such as kidney, liver, basic and brain functions [3]. Recent developments in adsorption technique of heavy metal ion and dyes in aqueous solution lead to a renewed interest in surface modification of adsorbent. It was modifying by surface functionalization with specific functional groups on polymeric materials [4–9]. There are several techniques water treatment technologies to remove metal ion in aqueous solution including chemical precipitation, photo catalytic purification, microwave catalysis, precipitation, ion exchange and adsorption [10–15]. Adsorption technique is simple, effective, and has high binding capacities for manganese, iron, cadmium, and lead ion adsorption [7,16–18].

Based on economical and environmental points of view, utilization of low cost agricultural by-products is main concern on this research. Conventionally, to eliminate the rice husk (RH) as waste only by burning or covering land that can cause air pollution due to increasing of CO gas [19,20]. Beside, RH has potential application as adsorbent by functional groups on surface such as amidogen and carboxyl [21]. However, the application of RH as adsorbent could be effective by modified surface using chemicals such as mineral and organic acids like tartaric acid, sodium hydroxide, oxidizing agent, etc. via increasing the number of functional groups. RH contains of 50% of cellulose which have light weight and better mechanical properties [22,23]. So that, RH is a potential natural fiber source as raw material to mix with MNPs for composite material. MNPs which have unique properties have been used in research such as magnetic storage [24], immunoassay [25] and photocatalyzing reaction [26,27]. The synthesis of MNPs by solvothermal method produces nanoparticles that are stable, uniform particle size and good magnetification property [7,28].

Following our previous work [28], we have developed RH fiber and functionalized MNPs as biocomposites material. Amine group was introduced onto biocomposites structure by one-step reaction. Batch adsorption study was carried out to investigated adsorption behaviors of Mn(II) ion and total suspended solid by biocomposites magnetic nanoparticle rice husk cellulose based as adsorbent [17]. Moreover, concern on improving for high quality of functional material, we develop a biocomposites using waste material and modified surface which having chemical, physical and adsorption properties. In this study, we reported one-step synthesis to enhance amine functionalize MNPs on RH cellulose and its capability to capture Pb(II) ion in aqueous solution. The RHB-MH was synthesized in solvothermal method by variation of amine source, analyzed and also characterized which have high amine content on biocomposites. The kinetic adsorption type, effect pH of solution, Pb(II) ion adsorption isotherm and reusability of adsorbent were also investigated.

2 Material and methods

2.1 Material

The rice husk (RH) was taken from rice mill at Martapura, South Kalimantan. Anhydrous sodium acetate ($C_2H_3NaO_2$), iron(III) chloride hexahydrate ($FeCl_3 \cdot 6H_2O$), ethylene glycol ($C_2H_4O_2$), 1,6-hexanediamine ($C_6H_{16}N_2$, HDMA), lead(II) nitrate ($Pb(NO_3)_2$), hydrochloric acid (HCl), and sodium hydroxide (NaOH)

were purchased from ACROS. The analytical grade for all the chemicals were chosen and used without further purification.

2.2 Rice husk cellulose preparation

Untreated RH was washed with distilled (DI) water for two times, and then dried at 105 °C. Dried RH was blended, then continuous with 60 mesh sieves and through to delignification step. The 40% of RH soaked in solution of 1% NaOH, heated at 80 °C while stirring rate at 150 rpm for 2 h. After reaction, the RH washed with DI water until filtrate became neutral. The obtained product was rice husk cellulose (RH-D) after dried at 90 °C for 24 h.

2.3 Synthesis of amine functionalized rice husk magnetic nanoparticle biocomposites

The biocomposites was produced by one-step solvothermal reaction base on previous works [28] with slight modification. Briefly, the mixture 24 mL of ethylene glycol, 0.8 g of iron(III) chloride hexahydrate, and 1.8 g of sodium acetate anhydride, heated at 80 °C under stirred then added 5 g of RH-D. In order to functionalized surface of magnetic nanoparticle of 5, 7 and 9 mL of 1,6-hexanediamine was added for each batch, and keep at 200 °C for 6 h in Teflon stainless steel autoclave. After reaction, the reactor cooling manually, then black biocomposites was taken from the mixture by employing external magnetic field and then rinsed with DI water and 40% of ethanol for 3 times. The biocomposites produced by 5, 7, and 9 mL of 1,6-hexanediamine were called RHB-MH1, RHB-MH2, and RHB-MH3, respectively. Naked MH was produced same procedure above without addition of fiber. As a control, biocomposites without addition of 1,6-hexanediamine (RHB-M) was also produced. In other hand, the all obtained materials were kept in DI water for future use as adsorbent.

2.4 Adsorption of Pb(II) ion onto amine functionalized rice husk magnetic nanoparticle biocomposites

The highest concentration of amine group on biocomposites was chosen as the best adsorbent for adsorption of Pb(II) ion. The Pb(II) ion removal was carried out in batch experimental. A 200 mL of a certain concentration of Pb(II) ion in 300 mL bottle and adjusting to pH 5, 6, and 7 with 1 M HCl or 1 M NaOH. A weighed amount of RHB-M and RHB-MH was added into bottle. The mixture was placed in a shaker (Firstek Scientific) at room temperature for certain contact time: 15, 30, 60, 120, 180, and 240 min. After experiment, the solution was separated by external magnetic field and filtered by using 0.2 µm PVDF membranes. Finally, the filtrate was analyzed for Pb(II) ion concentration using inductively coupled plasma atomic emission spectrophotometer (ICP-AES JY2000 2, Horiba Jobin Yvon). The Pb(II) ion adsorbed was described from the difference between initial and final adsorbate concentration. The data was taken in duplicate and the average value. In order to investigate the performance of biocomposites for repeated uses, the Pb(II) ions-loaded RBH-M and RBH-MH were desorbed by shaking in 0.1 N HCl for 4 h. After washing with DI water, the regenerated RHB-M and RHB-MH were used as the adsorbent for the next cycle. The recycle usage of adsorbent was repeated for three times in duplicate sample.

2.5 Characterization

The surface morphology of magnetic nanoparticle rice husk cellulose based biocomposites was examined by Field-emission scanning electron microscopy (FE-SEM, JOEL JSM-6500 F). The X-ray diffraction (XRD) measurement was investigated on Rigaku D/MAX-B X-ray diffractometer by using Copper K-alpha (CuK α) radiation. The machine worked at 40 kV and 100 mA for operation voltage and current, respectively. Brunauer-

Emmet-Teller (BET) surface area was evaluated by nitrogen adsorption-desorption using a Quantachrome, Autosorb-1 instrument. The superconducting quantum interference device (SQUID, LakeShore 7307) magnetometer was used to study magnetic property. Fourier transform infrared spectrometry (FT-IR, Bio-rad, Digilab FTS-3500) was taken to identify the functional groups on sample. For degradation material was studied by thermal gravimetric analysis (TGA) analysis using a Perkin Elmer, Diamond TG/DTA at 30 °C-1000 °C in nitrogen atmosphere flow (10 °C/min). The degradation material content in sample was studied by mass degradation from TGA curves. The surface charges of all materials were determined by zeta potential analyzer (Zetasizer 2000, Malvern Instrument, Malvern, UK). Retro-titration method was used for calculating amine content on biocomposites [29]. 50 mg of sample was added in to 25 mL of 0.01 M HCl and then shaken for 2 h at room temperature. 10 mL of supernatant was titrated by 0.01 N NaOH after through filtration. The amine group concentration calculation using:

$$C_{\text{NH}_2} = \left[\frac{(C_{\text{HCl}} \cdot V_{\text{HCl}}) - (5 C_{\text{NaOH}} \cdot V_{\text{NaOH}})}{m_{\text{sample}}} \right] \quad (1)$$

where C_{HCl} and C_{NaOH} are the concentration of HCl solution (mmol/L) and concentration of NaOH solution (mmol/L), respectively, V_{HCl} is the volume of HCl solution (L), V_{NaOH} is the volume of NaOH used in the titration of non-reacted acid's excess (L) and m_{sample} is the weight of sample (g).


3 Results and discussion

3.1 Characterization of amine functionalized rice husk magnetic nanoparticle biocomposites

Rice husk has complex structure consist of hemicelluloses and lignin. The cellulose from RH was obtained by delignification. The result of RH cellulose was give different in the term of color, morphology, structure, and functional groups. The original color of RH is brown after treatment turns become gray (Fig. 1. inset). Treatment by NaOH cause breaking lignocelluloses structure of RH. As shown in Fig.1 by FE-SEM observation, the surface morphology has shown irregular shape and bumpy surface. After treatment, hemicelluloses, lignin and silica were removed from surface of RH [28,30]. It clearly showed the surface of RH smoother and extended in diameter.

alt-text: Fig. 1


Fig. 1

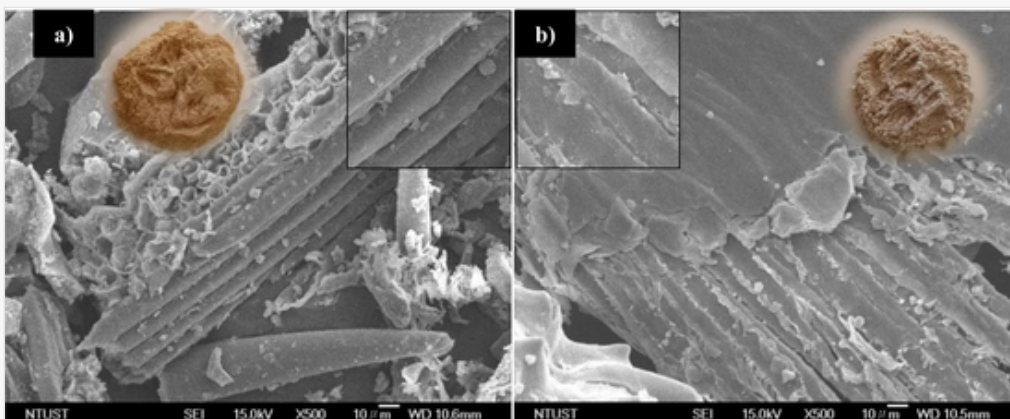

Amine magnetic nanoparticle functionalization (MH) was successfully synthesized onto surface of rice husk cellulose. MH formation was generated in the presence of HMDA during the synthesis; different concentrations of HMDA have effects on the amount of amine concentration on MNPs. Amine source from HMDA as primary amine which contain of two hydrogen atoms and one atom nitrogen bonded on surface to form $-NH_2$. The schematic diagram of preparation magnetic nanoparticle rice husk cellulose based biocomposites as shown in Fig. 2.

alt-text: Fig. 2

Fig. 2

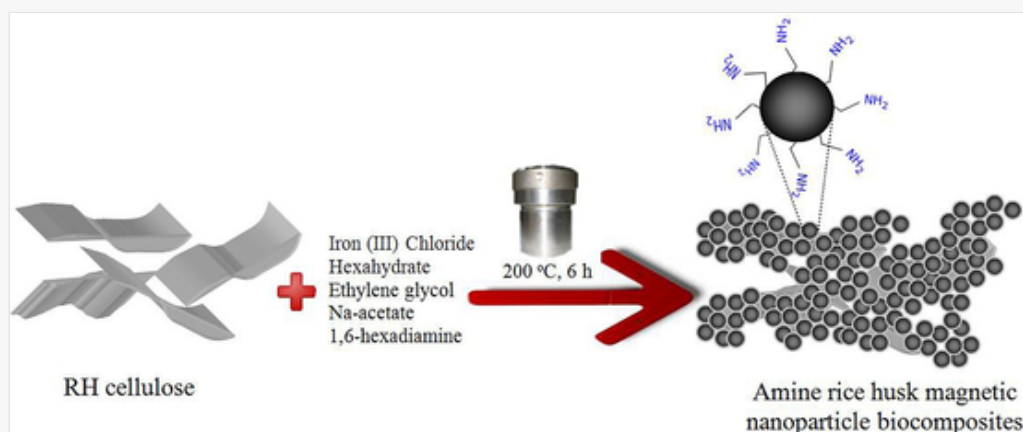


Schematic preparation of amine rice husk magnetic nanoparticle biocomposites by solvothermal method.

The qualitatively technique using Ninhydrin which generated a Ruhemann's purple colored solution was used to identified amine group on the surface of biocomposite (Fig. 3, inset). Amine groups was confirmed which purple color developed for each biocomposites. The amine concentration on RHB-MH1, RHB-MH2 and RHB-MH3 were about 3.64; 12.3; 5.97 mmol/g, respectively. In addition, amine functionalization on RHB surface was also protected of iron for leaching to solution at low pH. In the case of aminated functionalization of magnetic nanoparticle coated on montmorillonite (Mt@MH), the amine content on RHB-MH almost same with Mt@MH [7]. Fig. 3 showed the surface texture of RHB in different concentration of HMDA and without addition of HMDA. It clearly revealed the round shaped of monodispersed magnetic nanoparticles were growth and covered surface layer of RH cellulose. HMDA is play role in the magnetic nanoparticles (Fe_3O_4) formation, when HMDA grafting on the core site of Fe_3O_4 , it prevents to further growth and directly functionalized by amine group. Base on images, the Fe_3O_4 particle size of RHB-M (Fig. 3(a)) is 2-fold bigger than that all biocomposites which prepared by addition of HMDA. In other hand, the Fe_3O_4 was turn to aggregate for higher concentration of HMDA (Fig. 3(d)). Presumably, higher amount of amine group will block remaining ferric ion to growth become Fe_3O_4 . The less amount of Fe_3O_4 on RHB-MH1 is shown in Fig. 3(b) compare Fe_3O_4 on RHB-MH2 (Fig. 3(c)). This observation also confirms by XRF result for Fe content on RHB-MH1, RHB-MH2 and RHB-MH3 are 90.12%; 93.10%; and 87.99%, respectively.

alt-text: Fig. 3

Fig. 3

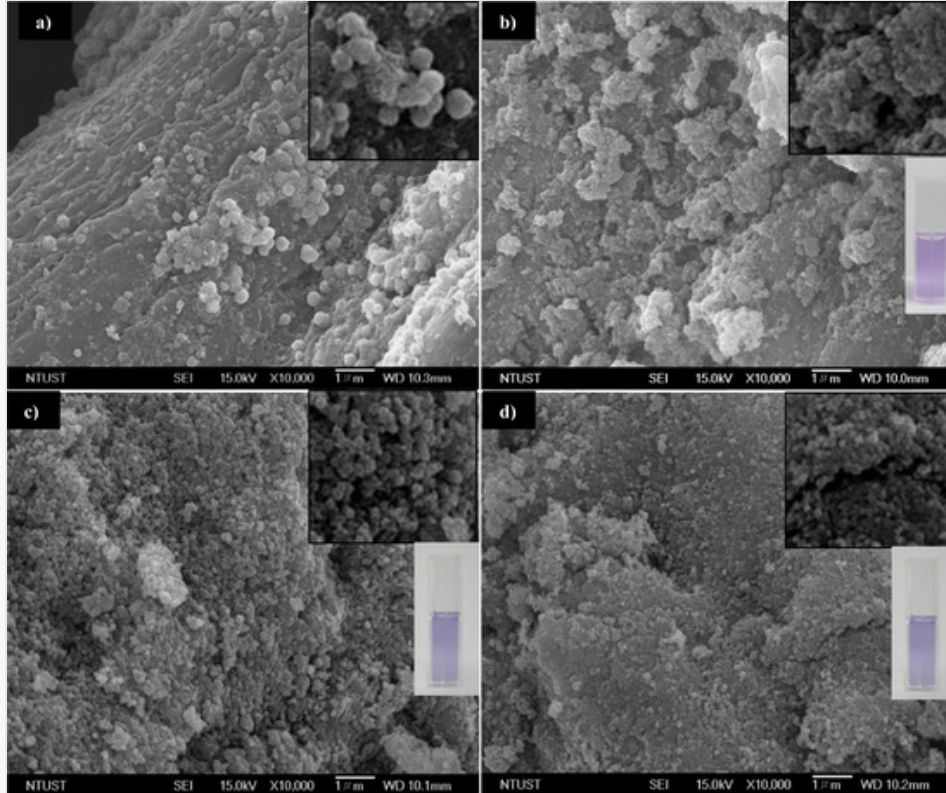


FE-SEM images (a) RHB without addition of HMDA (RHB-M); (b) RHB with addition of 5 mL of HMDA (RHB-MH1); RHB with addition of 7 mL of HMDA (RHB-MH2); and (c) RHB with addition of 9 mL of HMDA (RHB-MH3).

The FT-IR spectra (Fig. 4) exhibited the resonance bands of amine group (1645 cm^{-1} and 1050 cm^{-1}), Fe-O (598 cm^{-1}), Si-O (1098 cm^{-1}) and OH (3400 cm^{-1}) bindings [7,28,30]. The RH and RHD founded Si-O band, it confirms that the RH content of Si. In addition, all samples for RHB spectra shown specific peak for Fe-O and amine group, it indicates the magnetic nanoparticle surface modification by one-step solvothermal treatment has been achieved. In the term of specific peaks for amine groups, RHB-MH2 has high peak intensity which related to concentration amine group on the surface of RHB. This result also confirm by Nynhidrin test and amine content for RHB-MH2.

alt-text: Fig. 4

Fig. 4

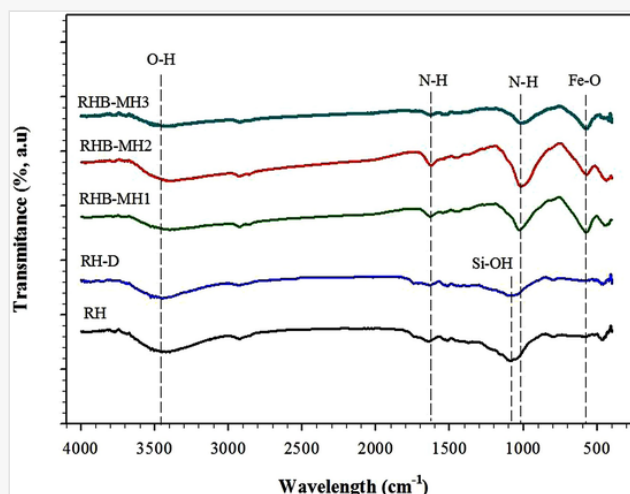


IR spectra of rice husk (RH), rice husk cellulose (RH-D); rice husk biocomposites with addition of 5 mL of HMDA (RHB-MH1), rice husk biocomposites with addition of 7 mL of HMDA (RHB-MH2) and rice husk biocomposites with addition of

The results obtained from the analysis of XRD are presented in Fig. 5. The typical spectrum of RH and RH-D could be observed for amorph and crystalline around peak at $2\theta = 16.2$ and 22.6 , respectively. Delignification treatment was increased the crystalline index (CrI) of RH from 56.67% to 77.55%. The increasing number of CrI is due to releasing of silica, lignin and hemicelluloses. The amorph on lignocelluloses material is a less number of organized polysaccharide structure which the position is at low angle and broad peak [31]. Strong evidence crystalline of Fe_3O_4 was formed on surface of RH for specific peaks at 36° , 43° , 63° [32]. Again, high intensity of Fe_3O_4 peak for RHB-MH2 is elated with FE-SEM, FT-IR and XRF results.

alt-text: Fig. 5

Fig. 5

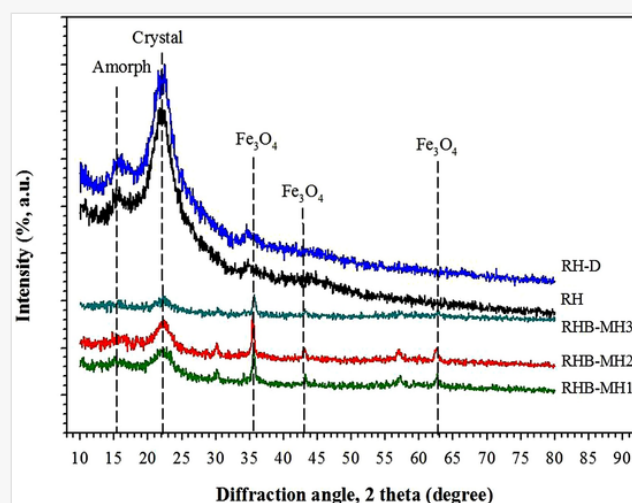


Typical XRD pattern of rice husk (RH), rice husk cellulose (RH-D); rice husk biocomposites with addition of 5 mL of HMDA (RHB-MH1), rice husk biocomposites with addition of 7 mL of HMDA (RHB-MH2) and rice husk biocomposites with addition of 9 mL of HMDA (RHB-MH3).

Further analysis, RHB is a magnetite (Fe_3O_4) phase which has superparamagnetic properties, and will have reaction to external magnetic field which facilitate for separation. The biocomposites which contain of 0.5 g of fiber in 90 mL of water takes 50 seconds apart from the solution (Fig. 6 inset). The saturation magnetization measurement was investigated at room temperature employing SQUID analysis. Fig. 6 presents the result of ferromagnetic behavior of MH and RHB-MH2. The value of magnetic saturation of MH and RHB-MH2 are 67.94 and 16.47 emu/g, respectively. Decreasing magnetic saturation value of RHB-MH2 was 75.7%, it is due to an appreciable amount of RH cellulose. It is apparent from Fig. 6 when MH in the composite form will loss amount of saturation value [33].

alt-text: Fig. 6

Fig. 6

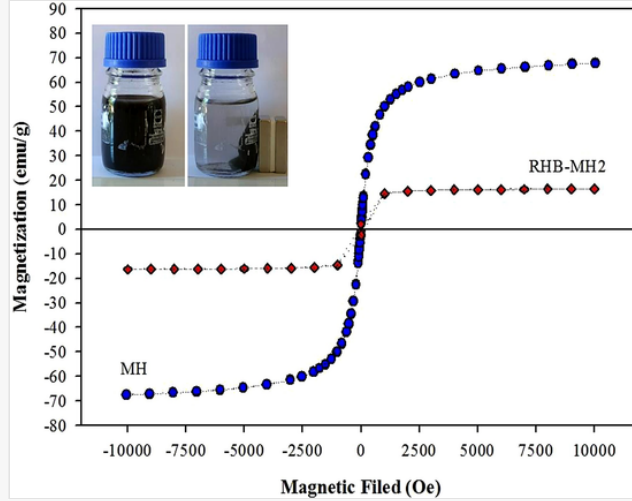


Magnetization curve of magnetite (MH) and rice husk biocomposites with addition of 7 mL of HMDA (RHB-MH2) at room temperature.

The nitrogen adsorption-desorption isotherm and distribution of pore diameter of RH-D and resulting biocomposites were shown in Fig. 7. The porosity is clearly difference from RH-D and biocomposites. The RH-D exhibits low up take nitrogen amount in isotherm, which confirm by low surface area of $1.309 \text{ m}^2/\text{g}$. In contrast, the all biocomposites show type II isotherm which higher adsorption nitrogen amounts as compare of RH-D [34]. The BET surface area (SBET) of RHB-MH2 is significantly increased 15-fold higher than RH-D. The determined SBET of RHB-M and RHB-MH2 were $9.113 \text{ m}^2/\text{g}$ and $19.954 \text{ m}^2/\text{g}$, respectively. The pore volume (Fig. 7a) and pore diameter (Fig. 7b) analysis distribution of RH-D were smaller than those biocomposites. The formation of magnetic nanoparticle on surface of RH-D which leads to significant increased the surface area. The critical important for this results is technique to improved the surface area by surface functionalization [35,36].

alt-text: Fig. 7

Fig. 7

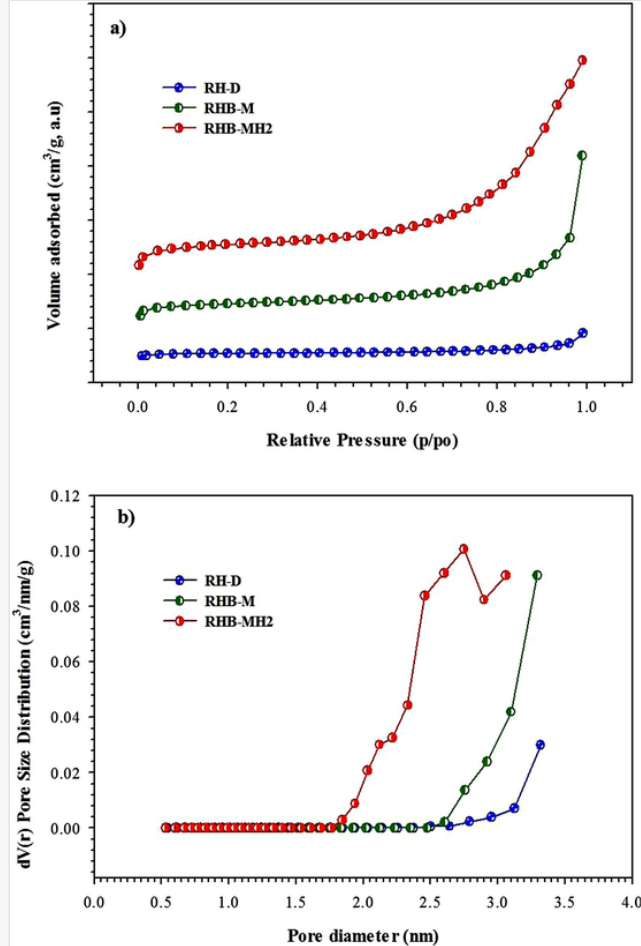


The nitrogen adsorption-desorption (a) isotherm and (b) distribution of pore diameter of RH-D, RHB-M and RHB-MH2.

The gravimetric analysis was conducted for study typical degradation of biocomposites. Fig. 8 shows samples carbonized up to 1000 °C. In Fig. 8 for RH, there is a clear trend of decreasing weight for three stages. The 1st stage weight loss of RH located at temperature <200 °C which dehydration or evaporation of light organic compound was occurred. The weight loss of 2nd stage was indicated at 200 °C-500 °C which degradation of hemicelluloses, cellulose and lignin and 3rd stage occurred at 700 °C [37]. For MH, it indicated only evaporation of water that proved by no significant weight loss during heating process. For RHB-M and RHB-MH2 also have 3 stages, the third stage is decomposition of amine groups on magnetite in the range 750 °C-800 °C. Interestingly, amine functionalized magnetic biocomposites produced the higher amount of magnetite. The excess amount base on TGA curve of RH, RHB-M and RHB-MH2 are 42.2%; 50.98%; 60.96%, respectively.

Based on this data, RHB-MH2 containing of magnetite 10% higher than that RHB-M. This result also confirm by XRF and SEM observation.

alt-text: Fig. 8

Fig. 8

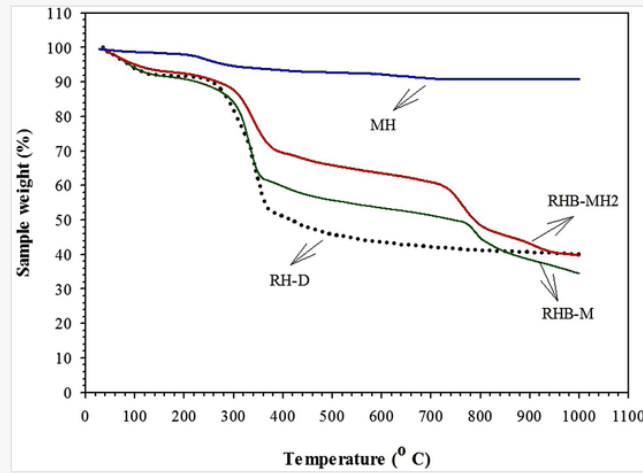

TGA curve of rice husk (RH); rice husk biocomposites without of HMDA (RHB-M); rice husk biocomposites with addition of 7 mL of HMDA (RHB-MH2).

3.2 Adsorption Kinetic of Pb(II) onto amine functionalized rice husk magnetic nanoparticle biocomposites

The rice husk biocomposites with amine functionalized magnetic nanoparticles was employed to adsorb Pb(II) ion. The RHB-MH2 was chosen as adsorbent with high amount of magnetic and amine groups. The experiment was conducted in batch process and investigated the optimum time for adsorption. The amount of Pb(II) ion being adsorbed by RHB-MH2 was considered difference of original concentration and concentration after adsorption. As a control, the rice husk biocomposites without amine group also used as adsorbent for their capability to adsorb Pb(II) ion.

Pb(II) ion kinetic adsorption was evaluated with initial concentration of 50 mg/L at pH 5. The Pb(II) ion adsorbed capacity increases linearly up to 139 mg/g in 1 h adsorption as shown in Fig. 9. Afterward, the Pb(II) ion adsorbed rate increases slightly and constant to final of 163.9 mg/g was reached after 3 h. On this condition, a phase of equilibrium adsorption rate was occurred where there is no Pb(II) ion absorbed. Surprisingly, the optimum adsorption time is shorter than other type of adsorbent for same condition such as montmorillonite coated magnetic nanoparticle (Mt@MH) (MH@C) [7]. The data was fit to Pb(II) ion adsorption using 2 models, there are pseudo 1st order and pseudo 2nd order kinetic models. The calculation are described [38]:


$$\frac{dq_t}{dt} = k_1(q_e - q_t)$$

(1)

where q_e : Pb(II) ion adsorbed (mg/g) at equilibrium

alt-text: Fig. 9

Fig. 9

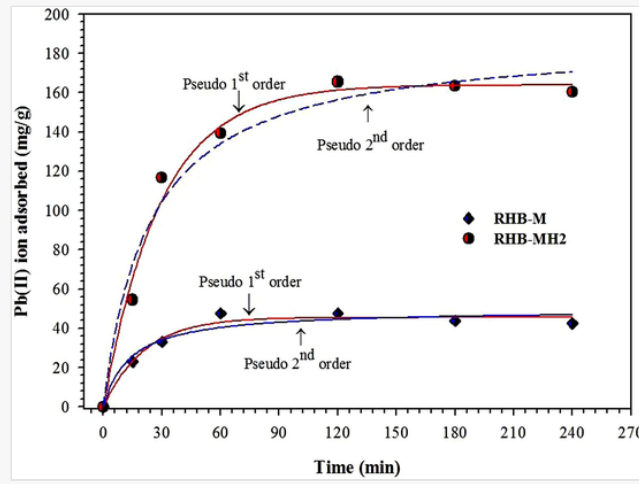

Pb(II) adsorbed after adsorption at various of contact time onto RHB-M and RHB-MH2 at room temperature. Pb(II) initial concentration of 50 mg/L, pH 5, shaking rate 150 rpm.

q_t : Pb(II) ion adsorbed (mg/g) time

k_1 : is the rate constant of adsorption (min^{-1}).

$$\frac{dq_t}{dt} = k_2(q_e - q_t)^2$$

(2)

where q_e : the maximum adsorption capacity (mg/g)

k_2 : rate constant of the pseudo-2nd order equation (g/mg min)

q_t :the amount of Pb(II) adsorbed (mg/g).

The parameters of these two kinetic models (equilibrium value of q_e and rate constant) were calculated by using non-linear regression and the result shown in Table 1. It seems that the pseudo 1st order kinetic model fitted well because of the higher number of coefficient correlation (r^2).

alt-text: Table 1

Table 1

i The table layout displayed in this section is not how it will appear in the final version. The representation below is solely purposed for providing corrections to the table. To preview the actual presentation of the table, please view the Proof.

The kinetic parameters of Pb(II) ion adsorption onto RHB-M and RHB-MH2 at room temperature.

Adsorbent	Kinetic Model	Parameter Constant	Value
RHB-M	pseudo 1 st order	q_e (mg/g)	45.54
		k_1 (min)	0.048

		r^2	0.977
	pseudo 2 nd order	q_e (mg/g)	49.50
		K_2 (g/mg min)	0.0015
		r^2	0.973
RHB-MH2	pseudo 1 st order	q_e (mg/g)	163.93
		k_1 (min)	0.0342
		r^2	0.9875
	pseudo 2 nd order	q_e (mg/g)	187.43
		k_2 (g/mg min)	0.0002
		r^2	0.972


Based on adsorption maximum capacity of both adsorbent, the RHB-MH2 has better adsorption capacity 3.6-fold higher than RHB-M, this may occur because RHB-MH2 functionalized by amine group which has more ligand to capture ion. Beside, RHB-MH2 has a smaller diameter particle size, so it can provide high surface area, with high permeability and stable of mechanical and thermal properties.

3.3 The Effect of pH on Pb(II) ion adsorption onto amine functionalized rice husk magnetic nanoparticle biocomposites

It is known the equilibrium pH (pH_e) of solution is a key factor in the term of metal ion removal and also determine the main driving force for adsorption. Adsorption capacity of RHB-M and RHB-MH2 has influenced by pH of solution, this could be happened corresponds to protonation or deprotonation of adsorbent active side surface and also degree of ionization and species type [39,40]. In this research, only 5-7 range of pH were applied, because Pb(II) ion will precipitate on base condition to form $Pb(OH)_2$. The ability of RHB-M and RHB-MH2 as adsorbents on Pb(II) ion adsorption can be seen in Fig. 10. It shows the optimum condition at pH 5 for RHB-M and RHB-MH2 adsorbent with adsorption capacity about 45.54 mg/g and 163.93 mg/g, respectively. For RBH-MH2, the trend of adsorption capacity is quite constant at pH 5, 6, and 7. In addition, capability of RHB-MH2 adsorption toward Pb(II) ion about 3.6-fold than that RHB-M at pH 5. The higher adsorption capacity of RHB-MH2 because presence amine groups on biocomposites surface, it makes surface stable in positive charged due to formation of $-NH_3^+$. Water solubility of amines is enhanced by hydrogen bonding involving these lone electron pairs, then interacted with Pb(II) ion as shown in Fig. 11. This phenomenon is also supported by surface charge measurement of materials (Fig. S1). The RHB-MH2 is positive charged at pH value < 7 , then become negative charged at pH > 7 . It proved that the formation of cationic amine groups on the range of pH 2-7. In addition, the surface charged of RH-D will shift to higher positive charged due to formation of magnetic nanoparticle.

alt-text: Fig. 10


Fig. 10

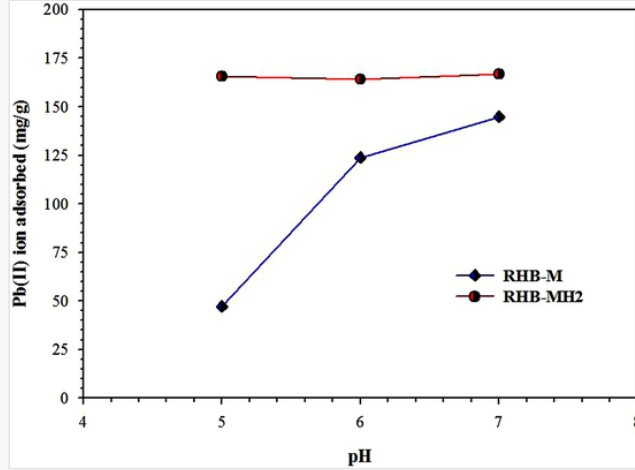

Pb(II) adsorbed in various of pH onto RHB-M and RHB-MH2 as adsorbent. Pb(II) initial concentration of 50 mg/L, shaking rate 150 rpm, 2 h.

alt-text: Fig. 11

Fig. 11

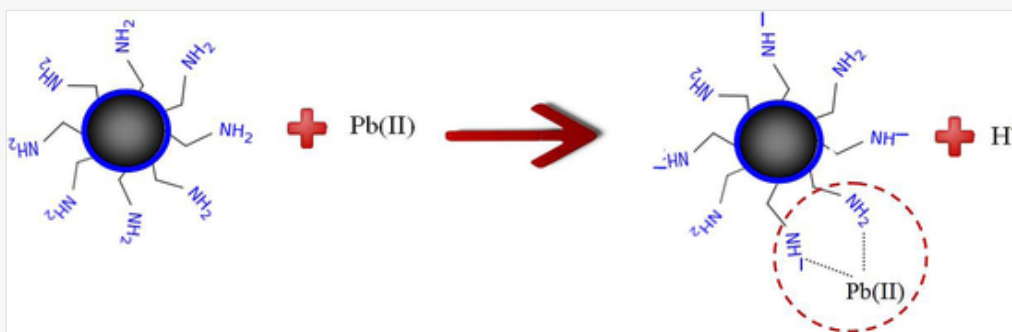

Adsorption mechanism of Pb(II) ion on amine magnetic nanoparticle biocomposites.

The RBH-M have point zero charge (PZC) at pH about 5.5, so that the surface of RHB-M below PZC on positive charged and over PZC in negative charged. On this condition, the adsorption capacity of RHB-M will increased due to negative charged formation and electrostatic interaction is the dominant driving forces to capture Pb(II) ion. The protonation of Pb(II) ion in the range of pH facilitate electrostatic and complexation mechanism will have good capability for adsorption.

3.4 Adsorption Isotherm of Pb(II) ion onto magnetic nanoparticle rice husk cellulose based biocomposites

The adsorption isotherm of Pb(II) ion toward RHB-M and RHB-MH2 was applied by using Langmuir adsorption model as shown in equation (3).

$$q_e = \frac{Q^0 b C_e}{1 + b C_e}$$

Where:

q_e : amount of Pb(II) ion adsorbed at equilibrium (mg/g)

Q^0 : maximal adsorption capacity (mg/g)


C_e : equilibrium concentration (mg/L)

b : adsorption constant (L/ mg).

Fig. 12 shows the adsorption isotherms of adsorbent, the isotherms could be well-fitted with Langmuir model as demonstrated by the square of correlation coefficients close to unity about 0.95 in Table 2.

alt-text: Fig. 12

Fig. 12

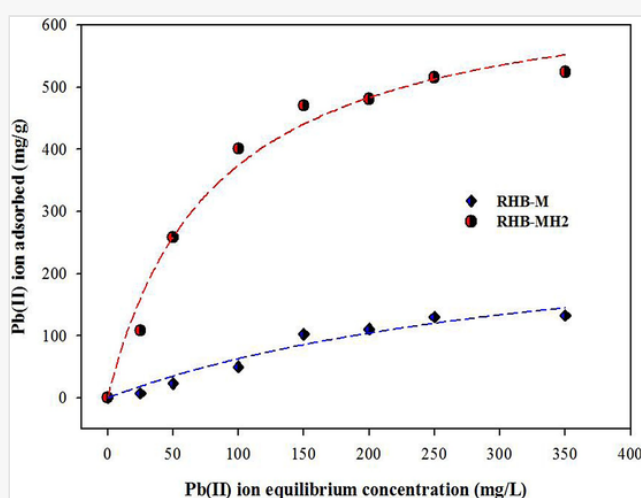

Langmuir adsorption isotherm of Pb(II) ion onto RHB-M and RHB-MH2 as adsorbent at room temperature for 2 h, pH 5 and shaking rate 150 rpm.

alt-text: Table 2

Table 2

i The table layout displayed in this section is not how it will appear in the final version. The representation below is solely for providing corrections to the table. To preview the actual presentation of the table, please view the Proof.

Parameter of Langmuir adsorption isotherm of Pb(II) ion onto RBH-M and RBH-MH2 at room temperature, 2 h, pH 5.

Isotherm constant	RHB-M	RHB-MH2
Q^0 (mg/g)	300.78	680.19
b (L/mg)	0.0027	0.0123
r^2	0.952	0.982

The maximal adsorption capacity of RHB-M and RHB-MH2 were 300.78 mg/g and 680.19 mg/g, respectively. The adsorption capacity of RHB-M and RHB-MH2 for Pb(II) ion adsorption was also studied and reported by researcher using different adsorbents [4–6,9,41] as shown in Table 3. When compared to same Pb(II) ion adsorption, the adsorbed maximum capacity of RBH-MH2 approximately 5.26-fold higher than EDTA functionalized magnetic-biochar as highest adsorbent.

alt-text: Table 3

Table 3

i The table layout displayed in this section is not how it will appear in the final version. The representation below is solely purposed for providing corrections to the table. To preview the actual presentation of the table, please view the Proof.


The maximum adsorption capacity of Pb(II) ion adsorption on different adsorbent.

Adsorbent	Adsorption capacity (mg/g)	pH _e	Reference
Magnetic-biochar	64.13	6	[5]
Magnetic polyethyleneimine	96.60	6	[4]
Fe ₃ O ₄ -SO ₃ H MNPs	108.93	7	[41]
Amine/thiol bifunctionalized MNPs	110.13	5	[6]
L-arginine modified magnetic chitosan	128.63	6	[9]
EDTA functionalized magnetic-biochar	129.31	6	[5]
Magnetic nanoparticle rice husk biocomposites (RHB-M)	300.78	5	This study
Amine functionalized rice husk magnetic nanoparticle biocomposites (RHB-MH2)	680.19	5	This study

The prepared RHB-M and RHB-MH2 were successfully regenerated with nearly constant number of adsorption capacity. The recovered adsorbents were kept in 0.1 N HCl for 4 h with vigorous stirring to remove Pb(II) ion. The capacity of the recovered RHB-MH2 was slightly lower than that observed in the first run. For 4-repetition adsorption, only 4% uptake capacity decrease was observed (Fig. 13). In other words, the Pb(II) ion can be adsorbed on RHB-MH2 and the performance has not significantly deteriorated after several times repetition. The RHB-MH2 has been shown as a effective adsorbent for wastewater treatment, especially for metal ion removal in the wastewater effluent

alt-text: Fig. 13

Fig. 13

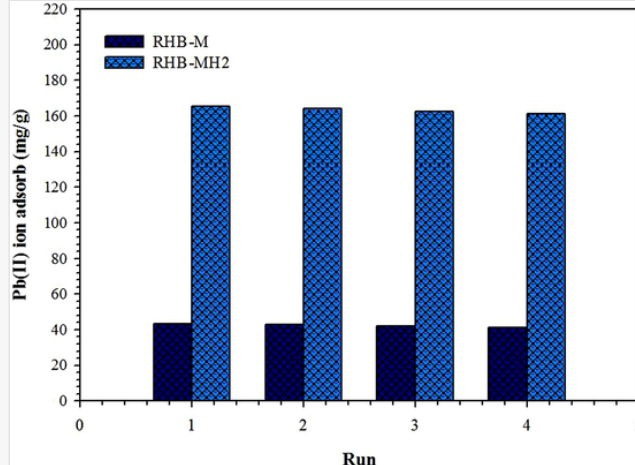

Pb(II) ion adsorbed in number of recycle by RHB-M and RHB-MH2 as adsorbent at room temperature. Pb(II) initial concentration of 50 mg/L, pH 5, shaking rate 150 rpm for 2 h.

4 Conclusions

Amine-rich functionalized on cellulose based magnetic nanoparticles rice husk biocomposites was successfully synthesized onto rice husk cellulose (RH). The rice husk cellulose was coated by aminated magnetic nanoparticle via one-step solvothermal method. The maximum adsorption capacity for Pb(II) ion was achieved up to 680.19 mg/g at $pH_e \sim 5$. The high up take capacity of RHB-MH2 is significantly increased due to amine functionalization on surface of magnetic nanoparticle. The electrostatic interaction was proposed as the primary driving force for Pb(II) ion adsorption. In addition, the RHB-MH2 has ferromagnetic properties which can facilitate the retrieval of adsorbent from waste stream by external magnetic field. The cellulose based magnetic nanoparticles rice husk biocomposites as promoting effective adsorbent for heavy metal ion removal from aqueous solution. The low cost raw material used also has good impact for waste utilization and green environment.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper

Acknowledgement(s)

The authors acknowledge the financial support from [Ministry of Research, Technology and Higher Education, Republic of Indonesia](#) (contract No. 123.9/UN8.2/PP/2019).

Appendix A Supplementary data

Supplementary material related to this article can be found, in the online version, at doi:<https://doi.org/10.1016/j.jece.2020.104339>.

References

- [1] Martíne I., Maria A., Bernal P., Environmental Impact of Metals, Metalloids, and Their Toxicity, in: Deshmukh R., Tripathi D.K., Guerriero G. (Eds.), Metalloids in Plants, 2020, pp. 451–488.
- [2] Eshlaghi M.A., Kowsari E., Ehsani A., Akbari-Adergani B., Hekmati M., Functionalized graphene oxide GO-[imi-(CH₂)₂-NH₂] as a high efficient material for electrochemical sensing of lead: Synthesis surface and electrochemical characterization, Journal of Electroanalytical Chemistry 858 (2020) 113784.
- [3] Naseem R., Tahir S.S., Removal of Pb(II) from aqueous/acidic solutions by using bentonite as an adsorbent, Water Research 35 (2001) 3982–3986.
- [4] Zhang X., Li Y., Hou Y., Preparation of magnetic polyethylenimine lignin and its adsorption of Pb(II), International Journal of Biological Macromolecules 141 (2019) 1102–1110.
- [5] Li M., Wei D., Liu T., Liu Y., Yan L., Wei Q., Du B., Xu W., EDTA functionalized magnetic biochar for Pb(II) removal: Adsorption performance, mechanism and SVM model prediction, Separation and Purification Technology 227 (2019) 115696.
- [6] Ji J., Chen G., Zhao J., Preparation and characterization of amino/thiol bifunctionalized magnetic nanoadsorbent and its application in rapid removal of Pb (II) from aqueous system, Journal of Hazardous Materials 368 (2019) 255–263.
- [7] Irawan C., Nata I.F., Lee C.-K., Removal of Pb(II) and As(V) using magnetic nanoparticles coated montmorillonite via one-pot solvothermal reaction as adsorbent, Journal of Environmental Chemical Engineering 1 (2019).
- [8] Pawar R.R., Lalhmunsiana, Kim M., Kim J.-G., Hong S.-M., Sawant S.Y., Lee S.M., Efficient removal of hazardous lead, cadmium, and arsenic from aqueous environment by iron oxide modified clay-activated carbon composite beads, Applied Clay Science 162 (2018) 339–350.
- [9] Guo S., Jiao P., Dan Z., Duan N., Zhang J., Chen G., Gao W., Synthesis of magnetic bioadsorbent for adsorption of Zn(II), Cd(II) and Pb(II) ions from aqueous solution, Chemical Engineering Research and Design 126 (2017) 217–231.
- [10] Yang Y., Zheng Z., Yang M., Chen J., Li C., Zhang C., Zhang X., In-situ fabrication of a spherical-shaped Zn-Al hydrotalcite with BiOCl and study on its enhanced photocatalytic mechanism for perfluorooctanoic acid removal performed with a response surface methodology, Journal of Hazardous Materials 399 (2020) 123070.
- [11] Wang Y., Yu L., Wang R., Wang Y., Zhang X., A novel cellulose hydrogel coating with nanoscale Fe₀ for Cr(VI) adsorption and reduction, Science of The Total Environment 726 (2020) 138625.
- [12] Chen J., Zhang X., Bi F., Zhang X., Yang Y., Wang Y., A facile synthesis for uniform tablet-like TiO₂/C derived from Materials of Institut Lavoisier-125(Ti) (MIL-125(Ti)) and their enhanced

visible light-driven photodegradation of tetracycline, *Journal of Colloid and Interface Science* 571 (2020) 275–284.

- [13] Izadi A., Mohebbi A., Amiri M., Izadi N., Removal of iron ions from industrial copper raffinate and electrowinning electrolyte solutions by chemical precipitation and ion exchange, *Minerals Engineering* 113 (2017) 23–35.
- [14] He F., Lu Z., Song M., Liu X., Tang H., Huo P., Fan W., Dong H., Wu X., Han S., Selective reduction of Cu^{2+} with simultaneous degradation of tetracycline by the dual channels ion imprinted POPD- CoFe_2O_4 heterojunction photocatalyst, *Chemical Engineering Journal* 360 (2019) 750–761.
- [15] He F., Lu Z., Song M., Liu X., Tang H., Huo P., Fan W., Dong H., Wu X., Xing G., Construction of ion imprinted layer modified ZnFe_2O_4 for selective Cr(VI) reduction with simultaneous organic pollutants degradation based on different reaction channels, *Applied Surface Science* 483 (2019) 453–462.
- [16] El-Sheikh A.H., Nofal F.S., Shtaiwi M.H., Adsorption and magnetic solid-phase extraction of cadmium and lead using magnetite modified with schiff bases, *Journal of Environmental Chemical Engineering* 7 (2019) 103229.
- [17] Effendi E.Z., Hariady Y.C., Salaahuddin M.D., Irawan C., Nata I.F., Utilization of Rice Husk Cellulose as a Magnetic Nanoparticle Biocomposite Fiber Source for the Absorption of Manganese (Mn^{2+}) Ions in Peat Water, *Jurnal Kimia Sains dan Aplikasi* 22 (2019) 7 2019.
- [18] Nata I.F., Mirwan A., Wicakso D.R., Irawan C., Isnaini M.D., Fitriani R., Adsorption of Fe^{3+} ion from Aqueous Solution onto Rice Husk Biocomposite Magnetic Nanoparticle, *IOP Conference Series: Earth and Environmental Science*, 506, 2020 012006.
- [19] Colapicchioni V., Mosca S., Guerriero E., Cerasa M., Khalid A., Perilli M., Rotatori M., Environmental impact of co-combustion of polyethylene wastes in a rice husks fueled plant: Evaluation of organic micropollutants and PM emissions, *Science of The Total Environment* 716 (2020) 135354.
- [20] Quispe I., Navia R., Kahhat R., Life Cycle Assessment of rice husk as an energy source. A Peruvian case study, *Journal of Cleaner Production* 209 (2019) 1235–1244.
- [21] Wu J.-H., He C.-Y., Advances in Cellulose-Based Sorbents for Extraction of Pollutants in Environmental Samples, *Chromatographia* 82 (2019) 1151–1169.
- [22] Dominic M., Joseph R., Sabura Begum P.M., Kanoth B.P., Chandra J., Thomas S., Green tire technology: Effect of rice husk derived nanocellulose (RHNC) in replacing carbon black (CB) in natural rubber (NR) compounding, *Carbohydrate Polymers* 230 (2020) 115620.
- [23] Collazo-Bigliardi S., Ortega-Toro R., Chiralt A., Improving properties of thermoplastic starch films by incorporating active extracts and cellulose fibres isolated from rice or coffee husk, *Food Packaging and Shelf Life* 22 (2019) 100383.
- [24]

Tan J., Deng Z.-H., Wu T., Tang B., Propagation and interaction of magnetic solitons in a ferromagnetic thin film with the interfacial Dzyaloshinskii-Moriya interaction, *Journal of Magnetism and Magnetic Materials* 475 (2019) 445–452.

- [25] Zhao Y., Cao M., McClelland J.F., Shao Z., Lu M., A Photoacoustic Immunoassay for Biomarker Detection, *Biosensors and Bioelectronics* 85 (2016) 261–266.
- [26] Lu Z., Zhou G., Song M., Liu X., Tang H., Dong H., Huo P., Yan F., Du P., Xing G., Development of magnetic imprinted PEDOT/CdS heterojunction photocatalytic nanoreactors: 3-Dimensional specific recognition for selectively photocatalyzing danofloxacin mesylate, *Applied Catalysis B: Environmental* 268 (2020) 118433.
- [27] Lu Z., Zhou G., Song M., Wang D., Huo P., Fan W., Dong H., Tang H., Yan F., Xing G., Magnetic functional heterojunction reactors with 3D specific recognition for selective photocatalysis and synergistic photodegradation in binary antibiotic solutions, *Journal of Materials Chemistry A* 7 (2019) 13986–14000.
- [28] Nata I.F., Putra M.D., Nurandini D., Irawan C., Fitriani R., Isnaini M.D., Rice Husk Fiber Magnetic Nanoparticle Biocomposites: Preparation and Characterization, *IOP Conference Series: Earth and Environmental Science*, 175, 2018, pp. 1–6.
- [29] Pi-Boleda B., Bouzas M., Gaztelumendi N., Illa O., Nogués C., Branchadell V., Pons R., Ortuño R.M., Chiral pH-sensitive cyclobutane β -amino acid-based cationic amphiphiles: Possible candidates for use in gene therapy, *Journal of Molecular Liquids* 297 (2020) 111856.
- [30] Menya E., Olupot P.W., Storz H., Lubwama M., Kiros Y., John M.J., Effect of alkaline pretreatment on the thermal behavior and chemical properties of rice husk varieties in relation to activated carbon production, *Journal of Thermal Analysis and Calorimetry* 139 (2020) 1681–1691.
- [31] Kaur P., Kaur P., Kaur K., Adsorptive removal of imazethapyr and imazamox from aqueous solution using modified rice husk, *Journal of Cleaner Production* 244 (2020) 118699.
- [32] Keshavarz H., Khavandi A., Alamolhoda S., Naimi-Jamal M.R., Magnetite mesoporous silica nanoparticles embedded in carboxybetaine methacrylate for application in hyperthermia and drug delivery, *New Journal of Chemistry* 44 (2020) 8232–8240.
- [33] Zhang X., Kan X., Wang M., Rao R., Qian N., Zheng G., Ma Y., Mechanism of enhanced magnetization in $\text{CoFe}_2\text{O}_4/\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ composites with different mass ratios, *Ceramics International* 46 (2020) 14847–14856.
- [34] Li X., Xie Y., Jiang F., Wang B., Hu Q., Tang Y., Luo T., Wu T., Enhanced phosphate removal from aqueous solution using resourceable nano- CaO_2/BC composite: Behaviors and mechanisms, *Science of The Total Environment* 709 (2020) 136123.
- [35] Pi X., Sun F., Gao J., Qu Z., Wang A., Qie Z., Wang L., Liu H., A new insight into the SO_2 adsorption behavior of oxidized carbon materials using model adsorbents and DFT calculations, *Physical Chemistry Chemical Physics* 21 (2019) 9181–9188.

[36]

Bi F., Zhang X., Xiang S., Wang Y., Effect of Pd loading on ZrO₂ support resulting from pyrolysis of UiO-66: Application to CO oxidation, *Journal of Colloid and Interface Science* 573 (2020) 11–20.


[37] Xiao R., Yang W., Cong X., Dong K., Xu J., Wang D., Yang X., Thermogravimetric analysis and reaction kinetics of lignocellulosic biomass pyrolysis, *Energy* 201 (2020) 117537.

[38] Qu J., Tian X., Jiang Z., Cao B., Akindolie M.S., Hu Q., Feng C., Feng Y., Meng X., Zhang Y., Multi-component adsorption of Pb(II), Cd(II) and Ni(II) onto microwave-functionalized cellulose: Kinetics, isotherms, thermodynamics, mechanisms and application for electroplating wastewater purification, *Journal of Hazardous Materials* 387 (2020) 121718.

[39] Aghazadeh V., Barakan S., Bidari E., Determination of surface protonation-deprotonation behavior, surface charge, and total surface site concentration for natural, pillared and porous nano bentonite heterostructure, *Journal of Molecular Structure* 1204 (2020) 127570.

[40] Periyasamy S., Gopalakannan V., Viswanathan N., Fabrication of magnetic particles imprinted cellulose based biocomposites for chromium(VI) removal, *Carbohydrate Polymers* 174 (2017) 352–359.

Graphical abstract

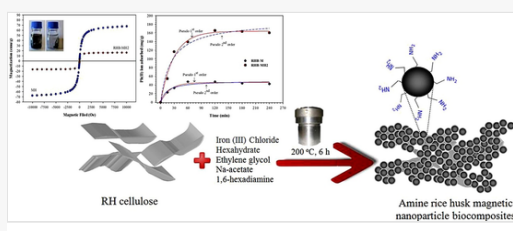

Highlights

- The amine magnetic nanoparticles can be easily synthesized onto rice husk cellulose.
- The rice husk biocomposites was provide a high adsorption capacity towards Pb(II) ion.
- The e asily retrievable of biocomposites makes the adsorption process easy and simple.

Appendix A Supplementary data

The following is Supplementary data to this article:

[Multimedia Component 1](#)

Queries and Answers

Query: Please check the presentation for Tables 1–3, and correct if necessary.

Answer: Table 1-3 are ok

Query: Have we correctly interpreted the following funding source(s) and country names you cited in your article:

Ministry of Research, Technology and Higher Education, Republic of Indonesia?

Answer: Yes