

Removal of artificial iron ions using activated carbon from sago pith waste

by Ahmad Saiful Haqqi

Submission date: 10-Apr-2023 11:06AM (UTC+0700)

Submission ID: 2060211292

File name: al_-_Removal_of_artificial_iron_ions_AC_from_sago_pith_waste.pdf (586.28K)

Word count: 5862

Character count: 32023



ELSEVIER

Contents lists available at ScienceDirect

Materials Today: Proceedings

journal homepage: www.elsevier.com/locate/matpr

Removal of artificial iron ions using activated carbon from sago pith waste

Isna Syauqiah^{a,b}, Awali Sir Kautsar Harivram^{a,c}, Erdina Lulu Atika Rampun^c, Dina Amryna Chairul Putri^{a,c}, Namira Ghina Safitri^{a,c}, Muthia Elma^{a,b,c,*}

^aChemical Engineering Department, Lambung Mangkurat University (ULM), J.L.A. Yani KM 36, Banjarbaru, South Kalimantan 70714, Indonesia

^bWetland Based Materials Research Center, Lambung Mangkurat University (ULM), J.L.A. Yani KM 36, Banjarbaru, South Kalimantan 70714, Indonesia

^cMaterials and membranes Research Group (M2ReG), Lambung Mangkurat University, J.L.A. Yani KM 36, Banjarbaru, South Kalimantan 70714, Indonesia

ARTICLE INFO

Article history:

Available online xxxx

Keywords:

Activated carbon
Adsorbent
Iron ions
Sago pith waste

ABSTRACT

In the present day, the industry is growing rapidly. Every process in the industries brings out pollution. Heavy metals, especially iron ions have contaminated water resources due to industrial activity. The high concentration of iron ions is dangerous for human life. To solve this issue an activated carbon from sago pith waste was developed to remove iron ions from industrial wastewater represented by artificial iron solution. The objective of this research is to measure the adsorption capacity of sago pith waste activated carbon (SPWAC) for treating artificial iron solution. The adsorbent was carbonized at 300 °C and 80 min. Further, it was activated by citric acid 0.1 M. The treated iron solution was analyzed by conductometer to examine the iron content. Subsequently, the functional groups of SPWAC were tested via Fourier Transform Infra-Red (FTIR). The result indicates that the SPWAC can reject iron ions of more than 80 % with an iron ions concentration of 1.81 mg/L at 60 min and 300 rpm. While, FTIR analysis show alkenes, carbonyl, and hydroxyl groups are present in SPWAC. The iron ions concentration in treated water is below the allowable threshold (0.3 mg/L) based on World Health Organization (WHO) guidelines for drinking water. Therefore, the SPWAC is promising technology to be applied for treating industrial wastewater.

Copyright © 2023 Elsevier Ltd. All rights reserved.

Selection and peer-review under responsibility of the scientific committee of the 2nd Regional Congress on Membrane Technology 2022 in Conjunction with the 16th AUN/SEED-NET Regional Conference on Environmental Engineering 2022.

1. Introduction

Fe is a symbol of iron which is a chemical element. Industrial activities such as the utilization of pesticides, metals leaching from waste dumps, runoff, landfill, acid mine drainage, smelting, and foundries generate heavy metal pollution. It negatively impacts soil, water, and air ecosystems. Not only from industrial activities but high iron is also found in peat water or wetland water as well [1–12]. Iron excess can be harmful to human bodies because it has high solubility that can easily be absorbed in the body [13]. Even at low concentrations, heavy metals can be a threat to living creatures [14]. This has been a challenge in many developing countries in decreasing human exposure to heavy metals in the water.

Several methods have been attempted to remove the iron content. It included zero-valent iron (ZVI), electro-coagulation, oxidation, ion exchange, lime softening, membrane separation, and adsorption [15–26]. Membrane is advance technology which widely for metal or organic removal in water [27–49]. Meanwhile, adsorption is recognized as the most effective method to remove the heavy metal because it is easy to operate and simple design, and more convenience [50]. In recent years, there is an improvement in the use of renewable materials as adsorbents for heavy metal rejection in water. Several natural adsorbents such as Juniper bark and wood [51], rice bran [52], sugarcane bagasse [53], orange peel [54], pomelo peel [55], and potato peel [56] have been reported to adsorb heavy metals.

Sago waste is mainly produced from starch processing [57]. Sago (*Metroxylon sagu* Rott.) can be easily found in the wetland area where other crops cannot grow without improved soil and drainage [58]. The distribution of sago has spread around Southeast

* Corresponding author at: Materials and membranes Research Group (M2ReG), Lambung Mangkurat University.

E-mail address: melma@ulm.ac.id (M. Elma).

<https://doi.org/10.1016/j.matpr.2022.12.090>

2214-7853/Copyright © 2023 Elsevier Ltd. All rights reserved.

Selection and peer-review under responsibility of the scientific committee of the 2nd Regional Congress on Membrane Technology 2022 in Conjunction with the 16th AUN/SEED-NET Regional Conference on Environmental Engineering 2022.

Asia (Malaysia, Indonesia, Philippines, Thailand) and north-western Melanesia (Solomon island and Papua New Guinea). Indonesia has 2.3 million ha (51 % of the sago area in the world) [59]. It has been consumed by humans and animals as sago starch. However, about 50 % of the sago palm is not extracted [60]. Yamamoto [60] fabricates a charcoal briquette, biodegradable foam, and ethanol from sago pith waste. This is a reason to find another alternative that can reuse sago pith waste with high economic value and minimize environmental damage.

Sago pith waste which is lignocellulosic biomass can be a promising material for activated carbon fabrication [61]. Activated carbon in particular is a very flexible material as it can be easily tailored with appropriate chemical and physical treatments [62]. A prior study has studied sago waste as a biosorbent using H_2SO_4 and $(NH_4)_2S_2O_8$ activation [63]. But these activating agents have difficult accessibility in rural areas and complex preparation. Therefore, the present paper reports the adsorption capacity of sago pith waste activated carbon (SPWAC) using citric acid for treating industrial wastewater. It is because citric acid contains a carboxylic functional group and is abundant [64]. Carboxyl is negatively charged. Fe ions will be more easily attached to the carboxyl functional group because of its positively charged surface. The effect of carboxyl in adsorption has reported in another study [65].

The objective of this study is to measure the adsorption capacity of sago pith waste activated carbon (SPWAC) for treating artificial iron solution. Majority of studies use pseudo-first order (PFO) and pseudo-second order (PSO) models to describe adsorbent kinetics. The SPWAC can provide low-cost material with simple fabrication to remove iron from an aqueous solution.

2. Materials & method

2.1. Materials

In this experiment, sago waste was collected from the sago industry located in Sungai Tabuk sub district-Banjar district, South Kalimantan Province, Indonesia, $Fe_2(SO_4)_3$ powder to make an artificial iron solution of 10 ppm, distilled water, 0.1 M citric acid ($C_6H_8O_7$), conductivity meter (Lutron CD-4301, Taiwan) as well as furnace and oven.

2.2. Sago pith waste activated carbon fabrication

Sago pith waste undergoes a washing and drying process under the sun to remove dirt. Next, the sago pith meshed. Carbonaceous sago pith waste (CSPW) is made by meshing sago pith waste. It is then followed by a calcination process for 80 min at 300 °C in air condition to remove ash, water content, and volatiles. The CSPW was sifted to 120 mesh and dried. Citric acid was added (0.1 M) and stirred for 2 h. It is dried again at 100 °C for 2 h to obtain Sago pith waste activated carbon (SPWAC). Finally, distilled water was used to wash SPWAC until pH is neutral and dried in an oven for 2 h at 80 °C. Fourier Transform Infrared (FTIR) was tested to characterize the SPWAC.

2.3. Batch adsorption and kinetic studies

An adsorption study was performed using a batch process to obtain kinetic data. $Fe_2(SO_4)_3$ was diluted in distilled water to make a 10 ppm artificial iron solution. After that, 0.1 mg SPWAC was mixed into an artificial iron solution and stirred at room temperature for 60 min. During the adsorption process, the solution conductivity was observed to determine Fe concentration [66]. After all, the suspension was filtrated using a vacuum filter to separate the adsorbent from the solution and final conductivity was

measured. The Fe removal efficiency and Fe adsorbed at equilibrium (q_e) were calculated using the equation below:

$$\text{Removal}(\%) = \frac{(C_i - C_e)}{C_i} \times 100\% \quad (1)$$

$$q_e = \frac{(C_i - C_e)}{w} \times V \quad (2)$$

Where C_i is initial concentration of Fe ion (mg/L), C_e is concentration of Fe ion at equilibrium condition (mg/L), w is weight of adsorbent used (g) and V is volume of Fe solution (L). The kinetic adsorption of Fe ion was observed using Pseudo First Order (PFO) and Pseudo Second Order (PSO) models [67–69]. PFO and PSO models can be written as:

$$\ln(q_e - q_t) = \ln q_e - k_1 t \quad (3)$$

$$\frac{1}{q_e} = \frac{1}{k_2 q_e^2} \times \frac{1}{t} \quad (4)$$

Where k_1 is PFO constant (s^{-1}), k_2 is PSO constant (g/mg s) and t is adsorption time (min).

3. Results and discussions

3.1. Fourier Transform Infrared (FTIR)

Fig. 1 depicts the difference between sago pith waste and sago pith waste activated carbon (SPWAC) based on Fourier Transform Infrared (FTIR). The FTIR is operated within 4000–600 cm^{-1} wavelength numbers. FTIR works by identifying functional groups. Alkenes (C=C) and carbonyls (C=O) are found at 1639 and 1733 cm^{-1} for sago pith waste, while at 1629 and 1716 cm^{-1} for SPWAC. It is noteworthy that the C=O drastically increases after sago pith waste is turned into SPWAC with citric acid addition. Citric acid as organic acid will enhance adsorption capacity because several new sites are created on the SPWAC. Carboxyl from citric acid donates a proton (H^+) and transforms a negatively charged car-

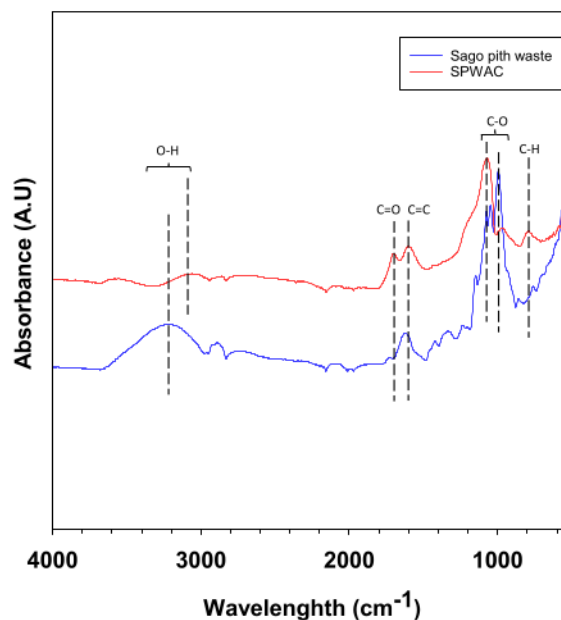


Fig. 1. FTIR of sago pith waste and sago pith waste activated carbon (SPWAC).

boxyl group [70]. The absorption bands at 817 cm^{-1} for SPWAC and 767 cm^{-1} for sago pith waste attributed to alkenes (C–H). This is in line with a study by Skoog, et al. [71], C–H appears at $995\text{--}675\text{ cm}^{-1}$. C–H was also observed in sago waste activated carbon with the addition of phosphoric acid and potassium hydroxide [72]. As mentioned before, the peaks at 1718 and 1753 cm^{-1} corresponded to C=O groups. The spectra around 3152 and 3256 cm^{-1} are indicative of O–H (hydroxyl) groups. The O–H is related to lignin, cellulose, and hemicellulose content [73]. Carboxylic acids (R-COOH) are formed from carbonyl and hydroxyl [74]. The absorption bands of C–O are shown at 1092 cm^{-1} for SPWAC and 1005 cm^{-1} for sago pith waste. Identical absorbance bands were also observed in a previous study by Al-Swaidan and Ahmad [75]. As shown from all the functional groups in Fig. 1, it can be concluded that the SPWAC has more carbon than sago pith waste.

3.2. Adsorption

The adsorption effect of SPWAC on the artificial iron solution can be seen in Fig. 2. The rate of adsorption is high at the initial 10 min. It indicates the majority of iron adsorption occurred during the times. It is probably caused by a high Fe ion concentration at the initial condition that leads to massively Fe ion mass transfer into the abundant unoccupied active site [69]. Then, the rate of adsorption drastically decreases at 20 – 60 min due to the high concentration of Fe(III) ion at the surface and adsorbent pore, especially on active sites. It causes the adsorbent becomes saturated and loses its ability to Fe(III) ion adsorption. In addition, it shows the adsorbent reaches maximum adsorption capacity at 10 ppm of Fe(III) ion concentration. Moreover, it proves that the adsorption process depends on time, therefore contact time has an essential role [76].

In this study, the highest removal efficiency is obtained more than 80%. This result is better than previous researches [77,78]. Comparison to other studies with different activating agent can be shown in Table 1. Activating agent may influence the adsorption performance by modifying surface area of adsorbent [79]. This condition denotes the potential of SPWAC to be applied for treating water with iron content. However, comprehensive studies are still required for implementing the adsorbent in the scale-up case, especially its interaction with another metal ion and dye.

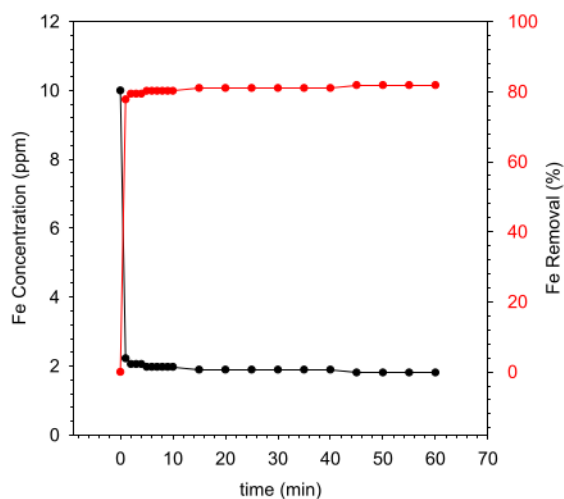


Fig. 2. Remain concentration of Fe ions and percent of Fe ions removal.

3.3. Kinetic studies

Pseudo-first order (PFO) and pseudo-second order (PSO) kinetic were used to identify which model fitted well to the adsorption data. The data was obtained from various sampling times. The parameters of the models and calculated data are illustrated in Table 2.

Fig. 3 shows the correlation between the PFO model and experimental data. It is clear evidence that the model does not fit Fe(III) adsorption experimental data. The PFO model is firmly related to an un-equilibrium state that describes a slow and steady adsorption rate due to a few active sites in the adsorbent. It also elucidates that at the initial stages of adsorption, the active sites are nearly zero due to the high concentration of adsorbate at the initial stage [84]. Thus, based on PFO characteristics, the present study shows the concentration of adsorbate is relatively low. Meanwhile, the unoccupied active site is abundant. Its characteristics belong to the PSO model. Generally, the PSO model has several conditions before it can be applied such as the final stages of adsorption, abundant active sites and, low concentration of adsorbate. In this research, the PSO model is fitted well to adsorption experimental data. The same result and pattern are found in previous researches [67,77,85]. Moreover, the kinetic constant and correlation coefficients (R^2) of PSO are higher than PFO. It indicates the kinetic adsorption of Fe(III) is better described by the PSO model [67].

PSO model characteristics is a good kinetic model to explain about rapid adsorption that occurred at the initial stages of the Fe(III) adsorption process. It is related to the abundant active site that appears compared to adsorbate concentration in artificial solution. This condition drives the adsorbate to adsorb at the active site massively.

4. Conclusion

The study of characteristic and kinetic models of SPWAC during the adsorption process was conducted. It found that the SPWAC has been created successfully via carbonization and chemical activation procedures. FTIR analysis shows that the active sites have formed by citric acid via chemical activation. It was proven by increasing C=O absorbance intention. In addition, PSO kinetic model fits well with adsorption experiment data. It has also confirmed that abundant active sites appear on the adsorbent. The adsorbent exhibit a good performance with a removal efficiency of more than 80%. Therefore, the SPWAC promises to be applied for treating industrial wastewater.

Data availability

Data will be made available on request.

Declaration of Competing Interest

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: Muthia Elma reports article publishing charges was provided by Lambung Mangkurat University. Muthia Elma reports a relationship with Lambung Mangkurat University that includes: employment. Muthia Elma has no patent pending.

Acknowledgements

Authors thanks to Materials and Membranes Research Group for the facilities provided. Isnasyauqiah thanks to Compulsory Lecturer Grant 2022 Lambung Mangkurat University-Indonesia. Muthia also thanks to Applied Research Universities Grant 2021-

Table 1
Comparison of heavy metal rejection using different biomass and activating agent.

Adsorbent type	Rejection (%)	Solution	Activating agent	References
Sago pith waste	81	Iron solution	C ₆ H ₆ O ₇	This work
Sago	95	Mercury solution	H ₂ SO ₄ and (NH ₄) ₂ S ₂ O ₈	[63]
Robusta coffee waste	65.4	Iron content in peat water	HCL	[80]
Mango peel	84	Iron in Batik wastewater	H ₂ SO ₄	[81]
<i>Albizia lebbbeck</i> seed	87	Lead solution	HCL	[82]
Banana Peel Activated Carbon (BPAC)	61	Chopper and chromium in textile waste solution	NaOH	[83]

Table 2
Parameters of the kinetic model for PFO and PSO at equilibrium time (60 min), ambient temperature and pH 5.

Models	Constant (k)	Equilibrium (q _e)	Adjusted R ²
PFO	0,0853(s ⁻¹)	81,87 (mg/g)	0.7638
PSO	8.6355 (g/mg.s)	81,58 (mg/g)	0.9999

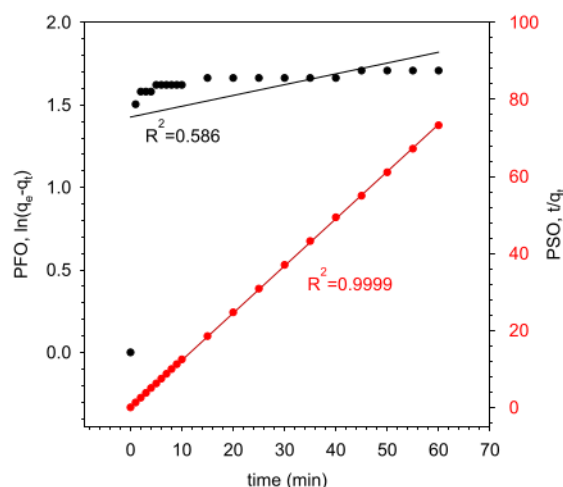


Fig. 3. PFO vs PSO kinetic models.

2023, Thesis and Dissertation Grant 2022 The Ministry of Research and Technology / National Research and Innovation Agency, The Ministry of Education and Culture of the Republic of Indonesia.

References

- [1] J. Briffa, E. Sinagra, R. Blundell, Heavy metal pollution in the environment and their toxicological effects on humans, *Heliyon* 6 (9) (2020) e04691.
- [2] M. Elma et al., Combination of Coagulation, Adsorption, and Ultrafiltration Processes for Organic Matter Removal from Peat Water, *Sustainability* 14 (1) (2022) 370, <https://doi.org/10.3390/su14010370>.
- [3] Mahmud et al., Effect of Two Stages Adsorption as Pre-Treatment of Natural Organic Matter Removal in Ultrafiltration Process for Peat Water Treatment [Online]. Available: *Materials Science Forum* 988 (2020) 114–121. <https://www.scientific.net/MSF.988.114>.
- [4] A. Rahma, M. Elma, E.L. Rampun, S.L. Sintungkir, M.F. Hidayat, Effect of backwashing process on the performance of an interlayer-free silica-pectin membrane applied to wetland saline water pervaporation, *Membrane Technology* 3 (2022) 2022, [https://doi.org/10.12968/S0958-2118\(22\)70019-5](https://doi.org/10.12968/S0958-2118(22)70019-5).
- [5] M. Elma et al., Long-Term Performance and Stability of Interlayer-Free Mesoporous Silica Membranes for Wetland Saline Water Pervaporation, *Polymers* 14 (5) (2022) 895, <https://doi.org/10.3390/polym14050895>.
- [6] Z.L. Assyaifi et al., Photocatalytic-pervaporation using membranes based on organo-silica for wetland saline water desalination, *Membrane Technology* 2021 (7) (2021) 7–11, [https://doi.org/10.1016/S0958-2118\(21\)00109-9](https://doi.org/10.1016/S0958-2118(21)00109-9).
- [7] A. Rahma, M. Elma, E. L. A. Rampun, A. E. Pratiwi, A. Rakhman, and Fitriani, "Rapid Thermal Processing and Long Term Stability of Interlayer-free Silica-P123 Membranes for Wetland Saline Water Desalination," *Advanced Research in Fluid Mechanics and Thermal Sciences*, vol. 71, no. 2, pp. 1-9, July 2020 2020, Art no. 1, doi: <https://doi.org/10.37934/arfm.71.2.19>.
- [8] R.A. Lestari et al., Organo Silica Membranes for Wetland Saline Water Desalination: Effect of membranes calcination temperatures, *E3S Web Conf.* 148 (2020) 07006, <https://doi.org/10.1051/e3sconf/202014807006>.
- [9] M. Elma, A. Rahma, A. E. Pratiwi, and E. L. A. Rampun, "Coagulation as pretreatment for membrane-based wetland saline water desalination," *Asia-Pacific Journal of Chemical Engineering*, vol. n/a, no. n/a, p. e2461, 2020, doi: 10.1002/apj.2461.
- [10] M. Elma, N. Riskawati, and Marhamah, "Silica Membranes for Wetland Saline Water Desalination: Performance and Long Term Stability," *IOP Conference Series: Earth and Environmental Science*, vol. 175, no. 1, p. 012006, 2018, doi: 10.1088/1755-1315/175/1/012006.
- [11] M. Elma, Hairullah, and Z. L. Assyaifi, "Desalination Process via Pervaporation of Wetland Saline Water," in *IOP Conference Series: Earth and Environmental Science*, 2018, vol. 175, no. 1: IOP Publishing, p. 012009, doi: <https://iopscience.iop.org/article/10.1088/1755-1315/175/1/012009>.
- [12] M. Elma, Fitriani, A. Rakhman, and R. Hidayati, "Silica P123 Membranes for Desalination of Wetland Saline Water in South Kalimantan," in *IOP Conference Series: Earth and Environmental Science*, 2018, vol. 175, no. 1: IOP Publishing, p. 012007, doi: <https://iopscience.iop.org/article/10.1088/1755-1315/175/1/012007>.
- [13] G.K. Kinuthia, V. Ngure, D. Beti, R. Lugalía, A. Wangila, L. Kamau, Levels of heavy metals in wastewater and soil samples from open drainage channels in Nairobi, Kenya: community health implication, *Scientific Reports* 10 (1) (2020) 8434, <https://doi.org/10.1038/s41598-020-65359-5>.
- [14] U. Sumiya, N. Anu, Nitrate removal from synthetic wastewater by using bio-adsorbent, *International Journal of Scientific and Engineering Research* 7 (4) (2016) 307–310.
- [15] S. Dey, N.S.A. Kotaru, G.T.N. Veerendra, A. Sambangi, "The removal of iron from synthetic water by the applications of plants leaf biosorbents, *Cleaner Engineering and Technology* 9 (2022), <https://doi.org/10.1016/j.clet.2022.100530>.
- [16] Y. Wu et al., Zero-valent iron-based technologies for removal of heavy metal (loid)s and organic pollutants from the aquatic environment: Recent advances and perspectives, *Journal of Cleaner Production* 277 (2020), <https://doi.org/10.1016/j.jclepro.2020.123478>.
- [17] S. Chaturvedi, P.N. Dave, Removal of iron for safe drinking water, *Desalination* 303 (2012) 1–11, <https://doi.org/10.1016/j.desal.2012.07.003>.
- [18] M. Elma, I. F. Nata, N. A. Maulida, S. H. Fitriah, E. L. A. Rampun, and A. Rahma, "Organosilica Multichannel Membranes Prepared by Inner Coating Method Applied for Brackish Water Desalination," in *Materials Science Forum*, 2022, vol. 1057: Trans Tech Publ, pp. 136–143.
- [19] E. Pradhana et al., "The Functionalization Study of PVDF/TiO₂ Hollow Fibre Membranes Under Vacuum Calcination Exposure," in *Journal of Physics: Conference Series*, 2021, vol. 1912, no. 1: IOP Publishing, p. 012035.
- [20] F.R. Mustalifah, A. Rahma, S. Mahmud, M. Elma, Chemical cleaning to evaluate the performance of silica-pectin membrane on acid mine drainage desalination, *IOP Conference Series: Materials Science and Engineering* 1195 (1) (2021), <https://doi.org/10.1088/1757-899x/1195/1/012057>.
- [21] N. Huda, E. Lulu Atika Rampun, R. Ayu Lestari, Y. Raharjo, D. Heri Yuli Yanto, and M. Elma, "Membrane pervaporation performance applied for brackish water prepared by vacuum impregnation method," *IOP Conference Series: Materials Science and Engineering*, vol. 1195, no. 1, p. 012056, 2021/10/01 2021, doi: 10.1088/1757-899x/1195/1/012056.
- [22] A. E. Lestari, M. Elma, S. Rabiha, E. L. A. Rampun, A. Rahma, and A. E. Pratiwi, "Performance of Mesoporous Organo Silica Membrane for Desalination," in *Materials Science Forum*, 2020, vol. 1000: Trans Tech Publ, pp. 285–292.
- [23] M. Elma, G.S. Saputro, Performance of Cobalt-Silica Membranes through Pervaporation Process with Different Feed Solution Concentrations [Online]. Available: *Materials Science Forum* 981 (2020) 342–348. <https://www.scientific.net/MSF.981.342>.
- [24] M. Elma et al., Carbon templated strategies of mesoporous silica applied for water desalination: A review, *Journal of Water Process Engineering* 38 (2020), <https://doi.org/10.1016/j.jwpe.2020.101520>.
- [25] M. Elma, A.E. Pratiwi, A. Rahma, E.L.A. Rampun, N. Handayani, The Performance of Membranes Interlayer-Free Silica-Pectin Templated for Seawater Desalination via Pervaporation Operated at High Temperature of Feed Solution, *Materials Science Forum* 981 (2020) 349–355, <https://doi.org/10.4028/www.scientific.net/MSF.981.349>.
- [26] M. Elma et al., Development of Hybrid and Templated Silica-P123 Membranes for Brackish Water Desalination, *Polymers* 12 (11) (2020) 2644.

- [27] N.I. Mat Nawi et al., A Rotary Spacer System for Energy-Efficient Membrane Fouling Control in Oil/Water Emulsion Filtration, *Membranes* 12 (6) (2022) 554.
- [28] S. Waqas et al., An energy-efficient membrane rotating biological contactor for wastewater treatment, *Journal of Cleaner Production* 282 (2021).
- [29] A. Sumardi et al., Designing a mesoporous hybrid organo-silica thin film prepared from an organic catalyst, *Membrane Technology* 2021 (2) (2021) 5–8, [https://doi.org/10.1016/S0958-2118\(21\)00029-X](https://doi.org/10.1016/S0958-2118(21)00029-X).
- [30] Isnasyauqiah et al., Hollow fiber membrane applied for Sasirangan wastewater desalination integrated with photocatalysis and pervaporation set-up, *Materials Today: Proceedings* (2021), <https://doi.org/10.1016/j.matpr.2021.10.343>.
- [31] N. Hidayah et al., Physicochemical Properties of Membrane Adsorber from Palm Empty Fruit Bunch (PEFB) by Acid Activation [Online]. Available: *Membranes* 11 (12) (2021) 917. <https://www.mdpi.com/2077-0375/11/12/917>.
- [32] M. Elma et al., Physicochemical Properties of Mesoporous Organo-Silica Xerogels Fabricated through Organo Catalyst, *Membranes* 11 (8) (2021) 607.
- [33] M. Elma et al., Organo-Silica Membrane Prepared from TEOS-TEVS Modified with Organic-Acid Catalyst for Brackish Water Desalination, *Jurnal Rekayasa Kimia & Lingkungan* 16 (2) (2021) 11–18.
- [34] M.R. Adam et al., Ammonia removal by adsorptive clinoptilolite ceramic membrane: Effect of dosage, isothermal behavior and regeneration process, *Korean Journal of Chemical Engineering* 38 (4) (2021) 807–815.
- [35] I. Syauiqiah, M. Elma, D. Mailani, and N. Pratiwi, "Activated carbon from Nypa (Nypa fruticans) leaves applied for the Fe and Mn removal," in: *IOP Conference Series: Materials Science and Engineering*, 2020, vol. 980, no. 1: IOP Publishing, p. 012073.
- [36] M. E. Riani Ayu Lestari, Erdina Lulu Atika Rampun, Anna Sumardi, Adhe Paramitha, Apat Eka Lestari, Sadidan Rabiah, Zaini Lambri Assyaifi and Gesit Satriaji, "Functionalization of Si-C Using TEOS (Tetra Ethyl Ortho Silica) as Precursor and Organic Catalyst," *ETMC and RC EnvE 2019*, vol. 148, 2020.
- [37] N.N.A.N. Razak et al., Finned spacer for enhancing the impact of air bubbles for membrane fouling control in *Chlorella vulgaris* filtration, *Bioresource Technology Reports* 11 (2020), <https://doi.org/10.1016/j.biteb.2020.100429>.
- [38] S. K. Rahman, E. L. A. Rampun, A. Rahma, and M. Elma, "Deconvolution of carbon silica templated thin film using ES40 and P123 via rapid thermal processing method," *Materials Today: Proceedings*, 2020.
- [39] S. K. Rahman, Maimunawaro, A. Rahma, S. Isna, and M. Elma, "Functionalization of hybrid organosilica based membranes for water desalination – Preparation using Ethyl Silicate 40 and P123," *Materials Today: Proceedings*, 2020/01/31/ 2020, doi: <https://doi.org/10.1016/j.matpr.2020.01.187>.
- [40] A. Rahma, M. Elma, A.E. Pratiwi, E.L. Rampun, Performance of interlayer-free pectin template silica membranes for brackish water desalination, *Membrane Technology* 2020 (6) (2020) 7–11, [https://doi.org/10.1016/S0958-2118\(20\)30108-7](https://doi.org/10.1016/S0958-2118(20)30108-7).
- [41] Maimunawaro, S. K. Rahman, E. L. A. Rampun, A. Rahma, and M. Elma, "Deconvolution of carbon silica templated thin film using ES40 and P123 via rapid thermal processing method," *Materials Today: Proceedings*, 2020/02/05/ 2020, doi: <https://doi.org/10.1016/j.matpr.2020.01.195>.
- [42] M. Elma et al., "Organo-silica membrane for brine water pervaporation," 2020.
- [43] R. Ayu Lestari et al., Functionalization of Si-C Using TEOS (Tetra Ethyl Ortho Silica) as Precursor and Organic Catalyst, *E3S Web Conf.* 148 (2020) 07008, <https://doi.org/10.1051/e3sconf/202014807008> [Online]. Available:..
- [44] I. Syauiqiah, M. Elma, M.D. Putra, A. Rahma, A.E. Pratiwi, E.L.A. Rampun, Interlayer-free Silica-carbon Template Membranes from Pectin and P123 for Water Desalination, *MATEC Web Conf.* 280 (2019) 03017, <https://doi.org/10.1051/mateconf/201928003017> [Online]. Available:..
- [45] E.L.A. Rampun, M. Elma, A. Rahma, A.E. Pratiwi, Interlayer-free silica-pectin membrane for sea-water desalination, *Membrane Technology* 2019 (12) (2019) 5–9, [https://doi.org/10.1016/S0958-2118\(19\)30222-8](https://doi.org/10.1016/S0958-2118(19)30222-8).
- [46] A.E. Pratiwi, M. Elma, A. Rahma, E.L.A. Rampun, G.S. Saputro, Deconvolution of pectin carbonised template silica thin-film: synthesis and characterisation, *Membrane Technology* 2019 (9) (2019) 5–8, [https://doi.org/10.1016/S0958-2118\(19\)30167-3](https://doi.org/10.1016/S0958-2118(19)30167-3).
- [47] M. Elma, H. Setyawan, A. Rahma, A. Pratiwi, and E. L. A. Rampun, "Fabrication of Interlayer-free P123 Carbonised Template Silica Membranes for Water Desalination: Conventional Versus Rapid Thermal Processing (CTP vs RTP) Techniques," in: *IOP Conference Series: Materials Science and Engineering*, 2019, vol. 543, no. 1: IOP Publishing, p. 012076.
- [48] M. Elma et al., Fabrication of interlayer-free silica-based membranes – effect of low calcination temperature using an organo-catalyst, *Membrane Technology* 2019 (2) (2019) 6–10, [https://doi.org/10.1016/S0958-2118\(19\)30037-0](https://doi.org/10.1016/S0958-2118(19)30037-0).
- [49] M. Elma and H. Setyawan, "Synthesis of Silica Xerogels Obtained in Organic Catalyst via Sol Gel Route," in: *IOP Conference Series: Earth and Environmental Science*, 2018, vol. 175, no. 1: IOP Publishing, p. 012008, doi: 10.1088/1755-1315/175/1/012008.
- [50] A. Bhatnagar, M. Sillanpää, A. Witek-Krowiak, Agricultural waste peels as versatile biomass for water purification – A review, *Chemical Engineering Journal* 270 (2015) 244–271, <https://doi.org/10.1016/j.cej.2015.01.135>.
- [51] E.W. Shin, K.G. Karthikeyan, M.A. Tshabalala, Adsorption mechanism of cadmium on juniper bark and wood, *Bioresource technology* 98 (3) (2007) 588–594, <https://doi.org/10.1016/j.biortech.2006.02.024>.
- [52] X.S. Wang, Y. Qin, Z.F. Li, Biosorption of zinc from aqueous solutions by rice bran: kinetics and equilibrium studies, *Separation science technology* 41 (4) (2006) 747–756.
- [53] E.O. Ajala, A.M. Ayanshola, C.I. Obodo, M.A. Ajala, O.J. Ajala, Simultaneous removal of Zn(II) ions and pathogens from pharmaceutical wastewater using modified sugarcane bagasse as biosorbents, *Results Engineering* (2022), <https://doi.org/10.1016/j.rineng.2022.100493>.
- [54] X. Li, Y. Tang, Z. Xuan, Y. Liu, F. Luo, Study on the preparation of orange peel cellulose adsorbents and biosorption of Cd²⁺ from aqueous solution, *Separation Purification Technology* 55 (2007) 69–75.
- [55] P. Tasaso, Adsorption of Copper Using Pomelo Peel and Depectinated Pomelo Peel, *Journal of Clean Energy Technologies* 2 (2014) 154–157, <https://doi.org/10.7763/JOCET.2014.V2.112>.
- [56] T. Aman, A.A. Kazi, M.U. Sabri, Q. Bano, Potato peels as solid waste for the removal of heavy metal copper(II) from waste water/industrial effluent, (in eng), *Colloids and surfaces B, Biointerfaces* 63 (1) (2008) 116–121, <https://doi.org/10.1016/j.colsurfb.2007.11.013>.
- [57] M. Leatemia, C. Silahoo, A. Jacob, The impact analysis of piled of sago pith waste on river water quality around the location of sago processing in waisamu village, kairatu sub district, West Ceram district, *Jurnal Budidaya Pertanian* 9 (2) (2013) 86–91.
- [58] F.-S. Jong, Research for the development of sago palm (Metroxylon sagu Rottb.) cultivation in, Wageningen University and Research, Sarawak, Malaysia, 1995.
- [59] F. Sidiq, D. Coles, C. Hubbard, B. Clark, L. Frewer, Sago and the indigenous peoples of Papua, Indonesia: A review, *Journal of Agriculture and Applied Biology* 2 (10/26 2021,) 138–149, <https://doi.org/10.11594/jaab.02.02.08>.
- [60] Y. Yamamoto, Outcomes and Recommendations from the 12th International Sago Symposium, in: H. Ehara, Y. Toyoda, D.V. Johnson (Eds.), *Sago Palm: Multiple Contributions to Food Security and Sustainable Livelihoods*, Springer Singapore, Singapore, 2018, pp. 319–330.
- [61] H. Liu, C. Cheng, H. Wu, Sustainable utilization of wetland biomass for activated carbon production: A review on recent advances in modification and activation methods, *Science of The Total Environment* 790 (2021), <https://doi.org/10.1016/j.scitotenv.2021.148214>.
- [62] E. Auer, A. Freund, J. Pietsch, T. Tacke, Carbons as supports for industrial precious metal catalysts, *Applied Catalysis A: General* 173 (2) (1998) 259–271, [https://doi.org/10.1016/S0926-860X\(98\)00184-7](https://doi.org/10.1016/S0926-860X(98)00184-7).
- [63] K. Kadirivelu, M. Kavipriya, C. Karthika, N. Vennilamani, S. Pattabhi, Mercury (II) adsorption by activated carbon made from sago waste, *Carbon* 42 (4) (2004) 745–752, <https://doi.org/10.1016/j.carbon.2003.12.089>.
- [64] U.S. Rashid, A.N. Bezbaruah, Citric acid modified granular activated carbon for enhanced defluorination, *Chemosphere* 252 (2020), <https://doi.org/10.1016/j.chemosphere.2020.126639>.
- [65] M. Poorsargol, Z. Razmara, M.M. Amiri, The role of hydroxyl and carboxyl functional groups in adsorption of copper by carbon nanotube and hybrid graphene-carbon nanotube: insights from molecular dynamic simulation, *Adsorption* 26 (3) (2020) 397–405, <https://doi.org/10.1007/s10450-020-00214-7>.
- [66] F. Prieto García, E. Barrado Esteban, M. Vega, and L. Debán, "A Rapid estimation of metal contents in wastewater treatment for conductivity measurements," *Journal of the Chilean Chemical Society*, vol. 50, pp. 547–551, 2005. [Online]. Available: http://www.scielo.cl/scielo.php?script=sci_arttext&pid=S0717-97072005000300004&nrm=iso.
- [67] M. Corral-Bobadilla, R. Lostado-Lorza, F. Somovilla-Gómez, R. Escobano-García, Effective use of activated carbon from olive stone waste in the biosorption removal of Fe(III) ions from aqueous solutions, *Journal of Cleaner Production* 294 (2021), <https://doi.org/10.1016/j.jclepro.2021.126332>.
- [68] Y.S. Ho, G. McKay, Pseudo-second order model for sorption processes, *Process Biochemistry* 34 (5) (1999) 451–465, [https://doi.org/10.1016/S0032-9592\(98\)00112-5](https://doi.org/10.1016/S0032-9592(98)00112-5).
- [69] S. Das, S. Mishra, Insight into the isotherm modelling, kinetic and thermodynamic exploration of iron adsorption from aqueous media by activated carbon developed from *Limonia acidissima* shell, *Materials Chemistry and Physics* 245 (2020), <https://doi.org/10.1016/j.materchemphys.2020.122751>.
- [70] C. Faizul, C. Abdullah, B. Fazlul, Extraction of silica from palm ash via citric acid leaching treatment, *Advances in Environmental Biology* 7 (12) (2013) 3690–3695.
- [71] D.A. Skoog, F.J. Holler, T.A. Nieman, *Principle of Instrumental Analysis*, (Saunders College Publishing), Philadelphia, 1998.
- [72] O. Togibasa, Y.O. Ansanay, K. Dahlan, M. Erari, Identification of surface functional group on activated carbon from waste sago, *Journal of Physics: Theories Applications* 5 (1) (2021) 1–8.
- [73] B. Janković et al., Physico-chemical characterization of carbonized apricot kernel shell as precursor for activated carbon preparation in clean technology utilization, *Journal of Cleaner Production* 236 (2019).
- [74] A. Munajad, C. Subroto, Fourier transform infrared (FTIR) spectroscopy analysis of transformer paper in mineral oil-paper composite insulation under accelerated thermal aging, *Energies* 11 (2) (2018) 364.
- [75] H. M. Al-Swaidan and A. Ahmad, "Synthesis and characterization of activated carbon from Saudi Arabian dates tree's fronds wastes," in: 3rd international conference on chemical, biological and environmental engineering, 2011, vol. 20: Citeseer, pp. 25–31.
- [76] M. Ahmaruzzaman, V.K. Gupta, Rice Husk and Its Ash as Low-Cost Adsorbents in Water and Wastewater Treatment, *Industrial & Engineering Chemistry Research* 50 (24) (2011) 13589–13613, <https://doi.org/10.1021/ie201477c>.

- [77] Ç. Kırbıyık, A.E. Pütün, E. Pütün, Equilibrium, kinetic, and thermodynamic studies of the adsorption of Fe(III) metal ions and 2,4-dichlorophenoxyacetic acid onto biomass-based activated carbon by ZnCl₂ activation, *Surfaces and Interfaces* 8 (2017) 182–192, <https://doi.org/10.1016/j.surfin.2017.03.011>.
- [78] A. Üçer, A. Uyanık, S. Çay, Y. Özkan, Immobilisation of tannic acid onto activated carbon to improve Fe(III) adsorption, *Separation and Purification Technology* 44 (1) (2005) 11–17, <https://doi.org/10.1016/j.seppur.2004.11.011>.
- [79] Z. Safitri, A. Pangestika, F. Fauziah, V. Wahyuningrum, and Y. Astuti, "The influence of activating agents on the performance of rice husk-based carbon for sodium lauryl sulfate and chrome (Cr) metal adsorptions," in: IOP Conference Series: Materials Science and Engineering, 2017, vol. 172, no. 1: IOP Publishing, p. 012007.
- [80] D. Rakhmina, R. Mulanova, H. Haitami, Effect of Active Carbon of Coffee Robusta Waste (*Coffea robusta* Lindl.) in Reducing Iron of Peat Water, *Medical Laboratory Technology Journal* 4 (1) (2018) 12–15.
- [81] A. Nugroho, N.L. Amanah, R.G. Firdaus, Adsorption study of mango peel activated carbon as iron removal for batik waste industry, *Jurnal Rekayasa Proses* 16 (1) (2022) 19–24.
- [82] M. Ullah et al., The effective removal of heavy metals from water by activated carbon adsorbents of *Albizia lebbbeck* and *Melia azedarach* seed shells, *Soil Water Research* 15 (1) (2019) 30–37.
- [83] O. P. Prastuti, E. L. Septiani, Y. Kurniati, and H. Setyawan, "Banana peel activated carbon in removal of dyes and metals ion in textile industrial waste," in: *Materials Science Forum*, 2019, vol. 966: Trans Tech Publ, pp. 204–209.
- [84] X. Guo, J. Wang, A general kinetic model for adsorption: Theoretical analysis and modeling, *Journal of Molecular Liquids* 288 (2019), <https://doi.org/10.1016/j.molliq.2019.111100>.
- [85] H. Koyuncu, A.R. Kul, Synthesis and characterization of a novel activated carbon using nonliving lichen *cestraria islandica* (L.) ach. and its application in water remediation: Equilibrium, kinetic and thermodynamic studies of malachite green removal from aqueous media, *Surfaces and Interfaces* 21 (2020), <https://doi.org/10.1016/j.surfin.2020.100653>.

Removal of artificial iron ions using activated carbon from sago pith waste

ORIGINALITY REPORT

10%

SIMILARITY INDEX

9%

INTERNET SOURCES

8%

PUBLICATIONS

2%

STUDENT PAPERS

MATCH ALL SOURCES (ONLY SELECTED SOURCE PRINTED)

6%

★ www.researchgate.net

Internet Source

Exclude quotes Off

Exclude matches < 2%

Exclude bibliography On