

TENSILE STRENGTH AND DURABILITY OF OIL PALM EMPTY FRUIT BUNCH FIBER IN SOFT SOIL

by

Submission date: 26-Apr-2023 10:08PM (UTC+0700)

Submission ID: 2076185956

File name: Tensile_Strength.pdf (1.81M)

Word count: 6754

Character count: 33599

TENSILE STRENGTH AND DURABILITY OF OIL PALM EMPTY FRUIT BUNCH FIBER IN SOFT SOIL

Yulian Firmana Arifin^{1,2}, *Muhammad Arsyad², Rudi Siswanto³, I Komang Tri Febi Astawa²,
Muhammad Hafizhi Ridha², Muhammad Rafiqi Ramadhani²

¹Wetland Based Material Research Center, University of Lambung Mangkurat, Banjarbaru, Indonesia;

²Civil Engineering Study Program, University of Lambung Mangkurat, Banjarbaru, Indonesia;

³Mechanical Engineering Study Program, University of Lambung Mangkurat, Banjarbaru, Indonesia

*Corresponding Author, Received: 14 Sep. 2022, Revised: 23 Oct. 2022, Accepted: 30 Oct. 2022

ABSTRACT: Natural fibers are already being used to stabilize the soil. However, the exact mechanism by which natural fibers improve the shear strength of soil is still not clear, and it varies according to the morphology of each fiber. Its durability in the soil is also an important issue in the use of natural fibers for soil stabilization. This study focused on the strength and durability of oil palm empty fruit bunch (OPEFB) fiber as a stabilizing material for soft clay. The durability was determined according to the changes in tensile strength and friction of the soil after a certain period. The clay was obtained from Banyu Hirang in South Kalimantan. The OPEFB fiber was obtained without further treatment from a palm oil processing plant. Tensile, soil-fiber friction, and unconfined compression tests were conducted for mixtures of fiber and soil. Preparations were made for each test with the same duration and conditions (1, 7, 14, 28, and 90 days) in closed and open conditions. The results showed that the average tensile strength of the fiber before use was 101 MPa. This value decreased sharply after 14 days in the soil, leaving a strength of 35.71 MPa in the open condition and 23.89% in the closed condition on the 90th day. The soil-fiber friction increased with increasing time, reaching 0.15 MPa in both conditions from the initial value of 0.06 MPa. The compressive strength of the soil-fiber mixture also increased with time. The corresponding scanning electron microscope results strengthened the findings of this study.

Keywords: Tensile strength, Durability, Soft soil, Fiber, OPEFB.

1. INTRODUCTION

In addition to concrete, synthetic or natural fibers can be used for soil stabilization. The synthetic fibers presently being used include strands of waste tires [1], nylon fibers [2], polypropylene fibers [3–5], glass fibers [6], and basalt fibers [7]. The emerging natural fibers include coir fiber [8], wheat straw, barley straw, wood shavings [9], bamboo fiber [10], and oil palm empty fruit bunches (OPEFBs) [11,12]. In contrast to synthetic reinforcements such as geotextiles and geogrids, fiber reinforcements can be easily implanted for slope improvement and thin-layer reinforcement in field applications [13]. The inclusion of fibers is an efficient method for decreasing the cement content of collapsible soils [3]. Wu et al. [14] reported that natural fibers contribute not only to reinforcement, but also to protect against slope soil losses and riverbed erosion; they can also provide filtration or drainage for eliminating heavy metals.

Soil stabilization with fiber is influenced by many factors, including the amount of fiber [1,2,4–7,9,10,12,15,16], fiber length [5,7,10,15], moisture contents of the samples [16], fiber characteristics [6,9,12,17], fiber diameter [10], soil properties [2,17], and soil stress [1,8,17]. In some cases,

natural fibers can absorb sufficient quantities of water [9,18,19]. This causes an increase in the fiber's moisture content, resulting in poor interface adhesion between the fiber and composite material [19]. Arifin et al. [11,20] found that a 7% OPEFB fiber absorbed water, allowing soft soil to be further compacted. Consequently, the compressive strength increased. In general, this tendency is particularly important for the stabilization of soft, high-water-content soils.

Although they have been widely studied, the interactions between soil and fiber remain very interesting for improving the geotechnical properties of soils. The shear strength of fiber-reinforced soil comprises two components: the shear strength of the soil matrix and the tensile stress acting on the fiber [13]. In addition, the contribution of the fiber to the increase in shear strength is caused by the bonding of the soil and fiber in the pull-out mechanism as well as the tensile strength of the fiber itself [16]. These mechanisms explain the interactions between the soil and fiber in general, but other interactions may occur between the soil and fiber, especially natural fibers. However, it is still unclear which of the two mechanisms—the shear of the soil matrix with the fiber or the tensile strength of the fiber—is the most

important. This means that the tensile strength and soil-fiber friction must be tested to determine how they affect the shear strength of the soil after mixing.

It is also important to test the tensile strengths of natural fibers to obtain a cheap and lightweight composite material for withstanding loads [21]. In previous studies, natural fibers such as vakka, date palm stems, and bamboo were tested and compared with other fibers such as sisal, banana stem, coconut, and oil palm. It was not explained where the palm fiber was sourced from. The order of fiber tensile strength from largest to smallest was date palm, bamboo, oil palm, coconut, vakka, sisal, and banana fiber. From reference, data on 23 natural fibers, including data on the tensile strengths of fibers such as coir (15–500 MPa), sisal (31–640 MPa), jute (29–773 MPa), and kenaf bast (18–476 ± 46 MPa) were collected and summarized by Ali [22]. The tensile strength of these fibers was very high. The tensile strength of OPEFB is reported to vary widely, even though tensile strength is a basic parameter that is directly related to other parameters. It has been reported as being in the range of 60–81 MPa [18], 74.4 MPa [23], and 21–260 MPa [24].

Besides functioning as synthetic fibers, natural fibers have the advantages of being environmentally friendly [25], locally available, able to become composites with cement or lime, inexpensive, and degradable [2,24,26]. The degradation of natural fibers is an important issue in their use as construction materials, especially in soils that tend to be moist and whose conditions can change. The fiber resistance allows for the bonds in the soil to be strengthened over time, such that when the fiber is degraded, the soil strength increases. However, there is no information on the resilience of OPEFB fibers in soils over time, so testing is required.

In addition to durability, another aspect that must be considered in the use of natural fibers is sustainability [27]. Based on data from the Directorate General of Plantations, a total of 49.71 million tons of palm oil production occurred in Indonesia in 2021 [28]. This production continues to increase annually, with an average annual increase of 9.88%. In South Kalimantan, 1.6 million tons of palm oil are produced. The remaining production, in the form of empty oil palm fruit bunches by weight, is approximately 25% of the fruit [29]. This shows the large amount of this fiber available in South Kalimantan and Indonesia.

The problem statements of this study are what mechanism most influences the stabilization of soft clay utilizing fiber and how much do the tensile strength of OPEFB fiber and its friction stress with soil change over time in the soil. This study aimed to test the strength of the OPEFB fiber (including the tensile strength), along with its friction with the soil and resistance in the soil. There was no

reference for the curing time for the resistance of this fiber, so the test used a maximum of 90 days, according to the planned duration of the study. The OPEFB fiber was an untreated fiber intended to attain the starting conditions before being treated.

2. RESEARCH SIGNIFICANCE

OPEFB fiber is still relatively new in construction, especially for soil stabilization. The data obtained is expected to provide references to important components, namely the tensile strength and friction of natural fibers with the soil. The results of this study clarify the fiber contribution in the context of increasing soil strength from these two components. Besides strength, an important issue of OPEFB fiber is its resistance in the soil. After a certain time, the remaining strength of the two components provides important information on the design of the reinforcement.

3. MATERIALS AND METHODS

3.1 Materials

The materials used in this study were soft soil and OPEFBs. Clay was obtained from Jl. Gubernur Sarkawi, Banyu Hirang, Gambut, Banjar Regency, South Kalimantan. The clay had an initial moisture content of 56% and a specific gravity of 2.31. The liquid limit, plastic limit, and soil plasticity index (ASTM D 4318) values were 61%, 34.87%, and 26.13%, respectively. The soil contained a fine content of 95.12% and a clay content of 56.32% (ASTM D7928). According to the Unified Soil Classification System (USCS) (ASTM D2487), the soil was classified as organic clay (OH) soil.

The OPEFB was a waste product from palm oil mills at Kec. Angsana, Kab. Tanah Bumbu, South Kalimantan Province. The fiber was taken from the OPEFBs. Figure 1 shows fiber preparation from the row material of an empty fruit bunch (Figure 1(a)) to the fine fiber. OPEFB was shredded until the crude fiber was obtained (Figure 1(b)). These fibers are then separated and air dried to obtain the fine fibers (Figure 1(c)).

In this study, no treatment was performed on the fibers before testing. To maintain the consistency of the results, fibers were selected with diameters between 0.4–0.6 mm. A digital micrometer was used to measure the fiber diameter. The measurements were performed at three points (i.e., both ends and in the middle), and the average of the three measurements was used. This was because the natural fiber cross-section is not uniform along the length of the fiber and varies within a fiber bundle [30]. This diameter was considered when determining the stress occurring when calculating the tensile stress.



Fig. 1 Fiber preparation from the row material of an empty fruit bunch to the fine fiber (a) oil palm empty fruit bunch (OPEFB), (b) empty fruit bunch shredded fiber, and (c) final fiber as used.

3.2 Sample Preparation and Testing

The sample consisted of soil that had been supplemented with fiber at the optimal percentage, as determined by previous studies [11,12]. Based on the results of previous studies, the compacted soil sample with the fiber had a dry volume weight (γ_d) of 0.92 gr/cm³ and a moisture content of 51%. The optimum fiber content was 7%. The length of the fiber was adjusted to the diameter of the sample. For the unconfined compression test (UCT) (ASTM-D2166), a length of 10 mm was used, and for a compaction test, a length of 100 mm was used. Tensile tests were conducted on untreated samples soaked in the soil. The compaction was performed using a standard Proctor (ASTM D698), and the fibers were placed in each layer of the compaction. After compaction, the samples were placed in a layer of soil and allowed to stand for 1, 7, 14, 28, and 90 days under two conditions: an open condition (i.e., allowed to interact with the atmosphere) and a closed condition (i.e., coated with plastic wrap so that there was no change in the moisture content of the samples). These conditions indicated whether the soil was dry (above the water table) or moist (below the water table), and were expected to affect the durability of the fibers. At the specified time, the fibers were removed, cleaned, and tensile-tested. The tensile test equipment and its settings are shown in Figure 2(a).

In addition to the tensile strength, the friction between the fiber and soil is an important component in their interactions; thus, it was also tested. A mold was specially designed to perform static compaction to achieve the same density as in the UCT test (i.e., 0.92 g/cm³ with 51% moisture content) where the fibers were not cut, as shown in Figure 2(b). The shear test was performed using the same tool as in the tensile test by modifying the bottom part, as shown in the inset of Figure 2(a).

Figure 3(a) depicts a test sample of the fiber put

on a tensile apparatus. This effect is obtained if the fiber breaks at the center of the span rather than in the pinched fiber region, as illustrated in Figure 3. (b). Figure 3(c) shows the implementation of UCT on a soil sample mixed with fiber. The compressive strength taken is the compressive stress at its maximum value or at 15% strain.

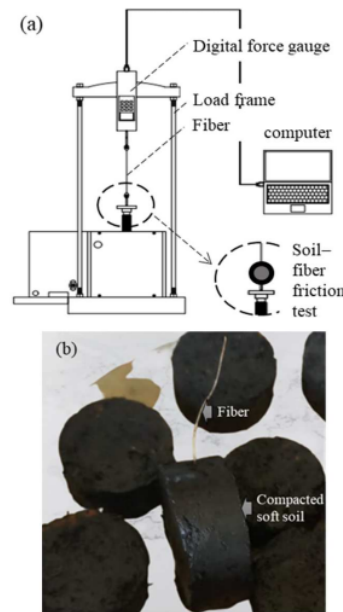


Fig. 2 Tensile and friction soil-fiber tests (a) equipment sets, and (b) soil-fiber friction samples.

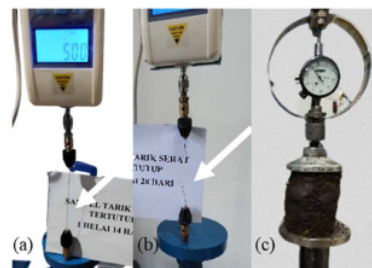


Fig. 3. (a) Pulling fiber tensile test; (b) fiber breaking; and (c) soil and fiber samples after UCT

Physically, the samples were evaluated by using scanning electron microscopy (SEM) to determine the impact of long-term fiber exposure on the tensile strength and friction between the soil and fiber. Researchers have used SEM to study the microscopic shapes of several natural fibers suggested as building materials ([31][18][32]).

4. RESULTS AND DISCUSSIONS

4.1 Tensile Stress of the OPEFB

Figure 4 shows typical results from the OPEFB fiber tensile test in this study. This curve is similar to that reported by Omar et al. [23], where three regions are generated: elastic, plastic, and fracture regions. The fiber begins to be pulled into the elastic region at a strain of 0.06%–0.08%, resulting in a tensile stress of 60–70 MPa. This strain is higher than that reported by Ramlee et al. [18] (0.03%) and Omar et al. [33] (0.04%). Moreover, it continues in the plastic region until the 5%–6% strain reaches a tensile stress of 97–107 MPa (mean of 101 MPa). In addition, the tensile strength obtained in this study exceeds that reported by Ramle et al. [18] and Omar et al. [33]. The tensile strength obtained in this study is close to that reported by Danso (i.e., 110 MPa) [34] and less than that summarized by Rao and Ramakrishna (i.e., 283 MPa) [24]. The age of the parent plants, the age of the fiber after extraction, fiber surface condition (cell wall peel off, skin damage, surface treatments), gauge length, and grip pressure fluctuation during testing all contribute to this variation [24].

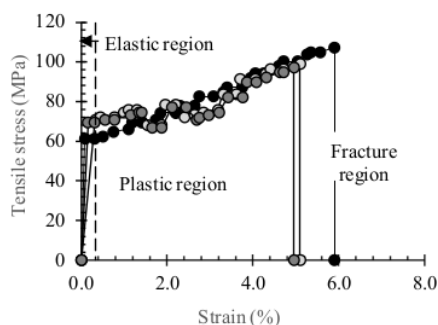


Fig. 4 Typical tensile test result.

4.1.1 Tensile strength of fiber as a function of time

Figure 5 shows the results from the tensile tests of the fibers soaked in the soil under the open and closed conditions. The values are listed in Table 1. The tensile strength decreases from 98.59 MPa on day 1 to 40.82 MPa on day 28. By 90 days, the tensile strength decreases by 5.10 to 35.71 MPa at a rate of 0.08 MPa/day.

Figure 5 also shows that the fiber in the open state has a higher tensile strength (by 10–26 MPa) than that in the closed state. The smallest difference in the 14-day cure time is approximately 6 MPa. This difference might be owing to large variations in the physical and chemical conditions of the natural fibers in the bunch even though they are taken from the same plant; this also affects their

mechanical properties, including the tensile strength [30,35]. The application conditions also affect the tensile strength, as shown in Figure 4. It is very likely that cellulose, the most influential component of the fiber tensile strength, degrades more in the closed state. In aerobic, nutrient-rich water, fibers decompose quickly, whereas previously dried fibers disintegrate more slowly [36]. In addition, the moisture affects the microorganism's development and multiplication. This is especially true for fungi, which grow quickly on cellulosic fibers when the humidity is high (approximately 80%) [37]. In general, natural fibers decompose naturally. This is advantageous when using natural fibers, as they are low in pollution. However, for long-term use, efforts must be made to maintain the strength over time. Further research is needed, especially regarding their use in soils.

Based on Table 1, the residual tensile strength after 90 days can be determined from one unit minus the percentage reduction to obtain 36.22% and 28.13% for open and closed conditions, respectively. As these numbers tend to be stable, it is safe to utilize approximately 25% of the fiber's tensile strength for calculating long-term use in the soft soil.

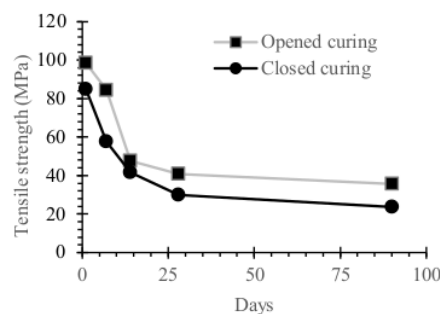


Fig. 5 Tensile strength of fiber as a function of curing time.

Table 1 Tensile strength of fiber over time with two different conditions

Time	Open curing				Closed curing				
	Day	MPa	MPa	%	Rate/day	MPa	MPa	%	Rate/day
1	98.59				84.92				
7	84.51	14.08	14.29	2.35	57.72	27.20	32.03	4.53	
14	47.62	50.97	51.70	5.27	41.59	43.33	51.02	2.30	
28	40.82	57.78	58.60	0.49	29.97	54.95	64.71	0.83	
90	35.71	62.88	63.78	0.08	23.89	61.04	71.87	0.10	

4.1.2 Soil-fiber friction as a function of time

Figure 6 shows the friction results for the soil fibers as a function of time. As shown in the figure, the friction increases from day 1 to day 7. On day 1,

both conditions produce the same friction, namely 0.06 MPa. Furthermore, in the first 7 days, the friction increases by 0.07 MPa (i.e., 111.11%) for the exposed soil, as shown in Table 2. For the closed sample, the friction increase is slightly smaller at approximately 0.05 MPa or 73.33%. A quite large increase continues to occur until day 14, with an increase of 0.01 and 0.02 MPa for the samples with open and closed conditions, respectively. The interactions between the fiber and soil can be seen in this test, especially in the first 7 days. The resulting friction is greater because large quantities of fiber interact with the soil. To maintain the interactions between the soil and fiber, the amount of fiber being used is limited. Arifin et al. [11,20] found that 7% fiber on a dry-weight basis was the optimum condition for soft clay soils. Notably, the vertical compressive strength decreases as a result of the high number of fiber-to-fiber contacts.

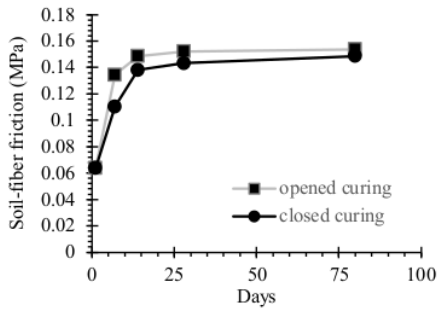


Fig. 6 Soil-fiber friction as a function of curing time.

Table 2 Soil-fiber friction as a function of time

Time Day	Opened curing			Closed curing		
	MPa	MPa	%	MPa	MPa	%
1	0.06			0.06		
7	0.13	0.07	111.11	0.11	0.05	73.33
14	0.14	0.08	133.33	0.14	0.07	116.67
28	0.15	0.09	139.00	0.14	0.08	125.00
90	0.15	0.09	141.67	0.15	0.08	133.33

4.1.3 Unconfined compressive strength of stabilized clay

Figure 7 shows the UCT results for a clay-fiber mixture sample with 7% fiber content under open curing (Figure 7(a)) and closed curing (Figure 7(b)). In addition to the curing method, time is also assumed to affect the strength of the soil and fiber mixture. The compressive strength of the undisturbed sample is 94.39 kPa. For the open-curing condition sample shown in Figure 7(a), the compressive stress increases with increasing strain until it reaches a maximum value of approximately

1509, 5131, 7434, 8719, and 8239 kPa for the samples cured for 1, 7, 14, 28, and 90 days, respectively. For the closed-condition sample, the maximum compressive strengths are 780, 996, 1132, 1303, and 1756 kPa, respectively. It can be observed that the samples left open and in equilibrium with the room conditions have much higher compressive strengths than those that are closed. These results are plotted in Figure 8 in a graph of the relationship between the time and compressive strength. The figure also shows the relationship of the weight change, i.e., the process of reducing water in the samples cured under open conditions. This decrease in water content is owing to the sample adjusting to the relative humidity of the room (ranging from 41.2%–62.4% with a temperature of 27.4–30.5 °C). As expected, the closed sample shows no change in weight, indicating that there is no change in the water content of the sample.

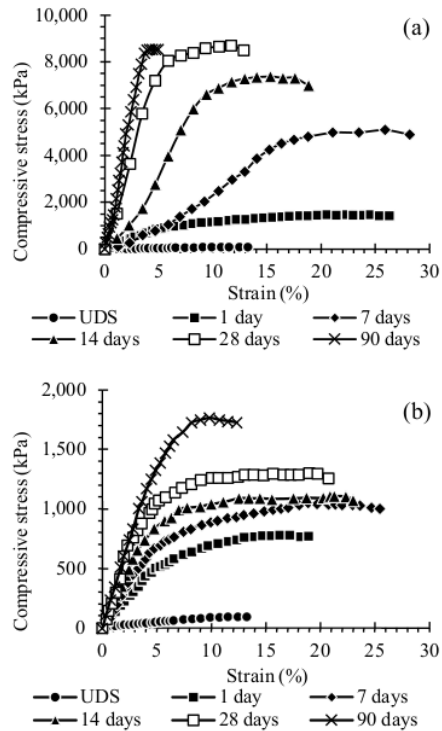


Fig. 7 Typical results of the unconfined compression test (UCT) for clay-fiber content at different curing times (a) open condition and (b) closed condition.

The decrease in the water content of the sample results in an increase in the strength of the clay owing to an increase in its negative pore water stress

[38,39]. Although no direct measurements were made, suction can be calculated from the relative humidity and room temperature data. In particular, the sample is equilibrated under these conditions with a thermodynamic relationship between the suction and partial pressure of the pore water [40,41]. The negative pore water stress of the sample is in the range of 65759–122490 kPa. This increase in the negative pore water pressure causes the strength of the open sample to be much greater than that of the closed sample. At closed condition, the sample's compressive strength increases with increasing curing time, even though the water content does not change. This is consistent with the results concerning the soil-fiber friction, which increases with increasing time (Figure 6). It can be observed that this friction has a large effect on increasing the compressive strength of the sample, although the tensile strength of the fiber decreases with increasing time. This friction, together with the restrain effect, even increases the durability of the fiber-reinforced soil against freeze-thaw cycling [26]. In addition, the curing time also reduces the pore water pressure, thereby increasing the strength of the fiber-reinforced soil [42].

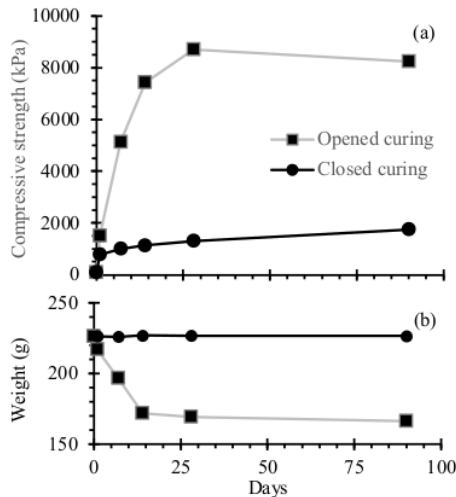


Fig. 8 Compressive strength and weight of samples as a function of time.

The increase in strength is directly proportional to the number of fibers used. Additionally, the presence of fiber creates a bridging effect on the shear plane, preventing the sample from cracking and improving its strength [43]. However, an excessive number of these results in reduced strength owing to increased friction of the fibers and reduced soil-fiber interactions [11,20]. To stabilize a soil sample using the technique proposed by Arifin et al. [11], the optimum fiber content must be

determined beforehand.

Figure 9 shows the Young's modulus (E) of samples as a function of time. For samples cured in opened condition, E values are 18.31, 35.42, 72.76, 168.68, and 138.28 MPa for samples cured in 1, 7, 14, 28, and 90 days, respectively. Meanwhile, the samples that were cured at the same period of time in the opened condition had E values of 10.4, 15.42, 20.41, 24.44, and 29.30 MPa, respectively. It can be seen from the graphs and figures that the samples cured in the open condition produced higher E than those cured in the closed condition. However, the addition of fiber as a function of time has increased the E value from 10–30 times that of the UDS sample (i.e., 0.96 MPa). Considering the Young's modulus [44], the addition of this fiber also resulted in an increase in sample consistency from very soft (i.e., $E < 4$ MPa) to stiff in 1–7 days (i.e., $7 < E < 20$ MPa) and to hard after 14 days (i.e., $20 < E < 32$ MPa). Several researchers have also noticed this rise in the stiffness of fiber-reinforced soils [45–48]. The increase in strength and stiffness is only for samples with the addition of a 10 mm long fiber. Longer than that, both strength and stiffness tend to decrease [46,47]. Short fibers increase the possibility of crossing the slip plane, resulting in a rise in shear strength. This stiffness is also influenced by tensile strength, confining pressure, and fiber content [45].

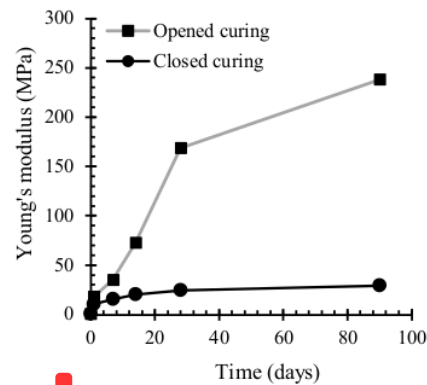


Fig. 9 Young's modulus as a function of time

4.2 Cross-Section and Longitudinal Surface of the OPEFB

Figures 10(a)–(d) show the cross-sections of the OPEFB fibers cured in dry conditions at 1, 28, 90, and 360 days. One sample was prepared for a period longer than the duration of the study (i.e., 360 days) to observe the changes in its cross-section. Figures 11(a)–(d) depict the longitudinal surfaces of the OPEFB fiber in this study after being cured for 1, 28, 90, and 360 days, respectively.

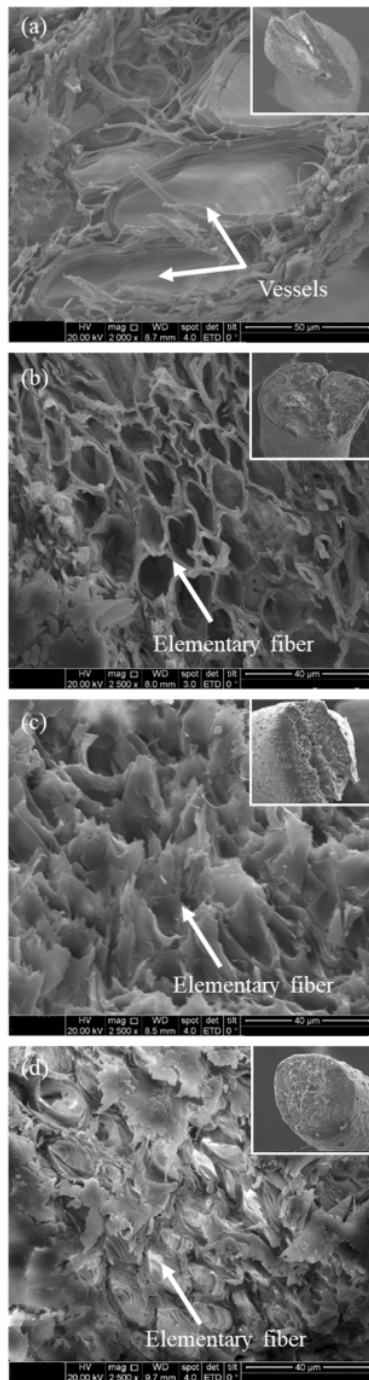


Fig. 10 Cross-section of the OPEFB (a) 1 day, (b) 28 days, (c) 90 days, and (d) 360 days.

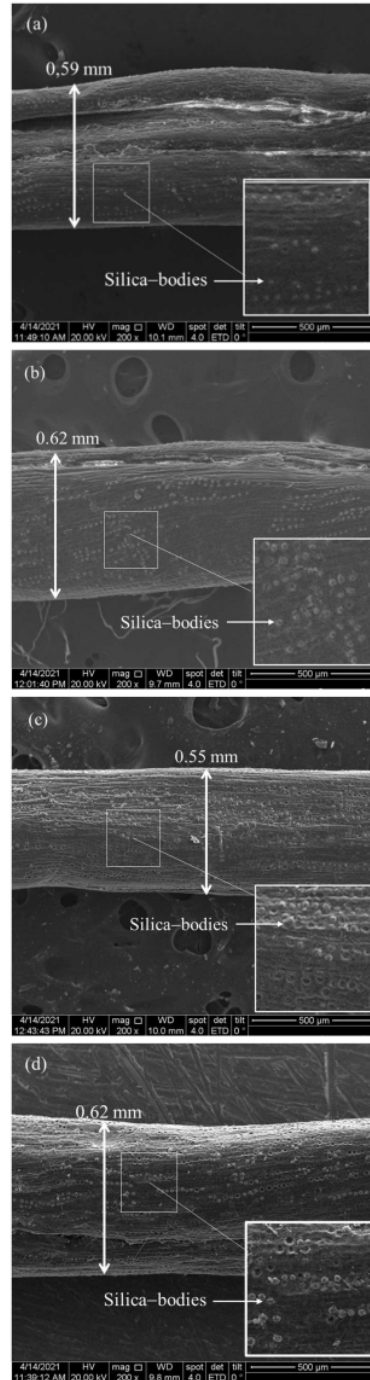


Fig. 11 Scanning electron microscopy (SEM) image of fiber surface cured in open condition for (a) 1 day, (b) 28 days, (c) 90 days, and (d) 360 days.

Figure 10(a) depicts a fresh cross-section with vessels and elementary fibers on the sidewalls. Even though the tensile strength decreases by 58% from 1 to 28 days, the elementary fiber remains clearly visible, and there is no damage at this age (Figure 10(b)). The damage is clearly visible in the fiber cross-section in the soil for 90 days, as shown in Figure 10(c).

The damage to the fiber cross-section results in a decrease in the tensile strength of the remaining fiber by almost 35 MPa, or a decrease of more than 63.78%. At 360 days, the fiber cross-section is degraded (Figure 10(d)) and based on observations, the fiber can be broken into 3–4 cm-long pieces. The longer the fiber in the soil, the more its cross-sectional structure changes.

As can be seen, the fiber diameter remains in the range being used, i.e., between 0.4–0.6 mm on average. The figures show the presence of silica bodies on the fiber surface, both in the fiber cured for 1 day (Figure 11(a)) and that cured for 360 days (Figure 11(d)). In previous studies, the silica bodies were found to play a role in the amount of friction on the surface of the OPEFB fiber [23,24,33]. In this study, there was no change in the fiber surface even though it interacted with the soil for 360 days. These results provide great hope for the use of these fibers by relying on the friction between the fiber and other materials (such as soft soil). The large difference in the fiber tensile strength and clay-fiber friction does not allow them to work together to increase the soil strength. The soil-fiber bond is released before the tensile force begins to act. However, a sufficiently high tensile force, even after curing for 90 days, will ensure that there is friction between the soil and fiber. If friction is dominant, then the important parameters in the use of this fiber will be the diameter and length of the fiber, so as to ensure the size of the surface of the fiber interacting with the soil. SEM results show that the increased strength of the fiber-stabilized soil is caused by a physical process [42].

5. CONCLUSION

This paper presents the results of research on the tensile strength and durability of OPEFB fibers used as stabilizing materials for soft clay soils under two conditions (open and closed). The results show that the tensile strength of the OPEFB fiber is approximately 98.59 MPa in the open condition and 84.92 MPa in the closed condition. These values decrease significantly with time, taking 14 days to reach 50%. The maximum tensile strength that can be safely used in the calculation for long periods of time in the soil is approximately 25% of the initial tensile strength. This study also found that soil-fiber friction plays an important role in the use of fibers

for the stabilization of soft soils. This friction increases with time, particularly in the first 14 days. The results from the UCT test show an increase in compressive strength with increasing time, with a similar tendency to the soil-fiber curve.

The SEM results support the results of this study, as there is a change in the structure of the cross-section of the fiber soaked in the soil, resulting in a decrease in the tensile strength of the fiber. The SEM results on the longitudinal surface show little change; the silica bodies which affects the soil-fiber friction on the surface of the fiber remain present, even after the fiber is cured for up to 360 days.

6. ACKNOWLEDGMENTS

The authors acknowledge that this research was funded by the University of Lambung Mangkurat through the *Dosen Wajib Meneliti* Program in 2022 under contract number 026.18/UN8.2/PL/2022.

7. REFERENCES

- [1] Ahmed, A., Naggat, M.H.E. Effect of Cyclic Loading on the Compressive Strength of Soil Stabilized with Bassanite-Tire Mixture. *J. Mater. Cycles Waste Manag.*, Vol. 20, 2018, pp. 525–532. doi:10.1007/s10163-017-0617-1.
- [2] Brahmachary, T.K., Ahsan, M.K., Rokonzaman, M. Impact of Rice Husk Ash (RHA) and Nylon Fiber on the Bearing Capacity of Organic Soil. *SN Appl. Sci.*, Vol. 1, 2019, pp. 1–13. doi:10.1007/s42452-019-0275-0.
- [3] Ayeldeen, M., Azzam, W., Arab, M.G. The Use of Fiber to Improve the Characteristics of Collapsible Soil Stabilized with Cement. *Geotech. Geol. Eng.*, Vol. 40, 2022, pp. 1873–1885. doi:10.1007/s10706-021-01997-4.
- [4] Chore, H.S., Vaidya, M.K. Strength Characterization of Fiber Reinforced Cement-Fly Ash Mixes. *Int. J. Geosynth. Gr. Eng.*, Vol. 1, 2015, pp. 1–8. doi:10.1007/s40891-015-0032-4.
- [5] Gupta, D., Kumar, A. Strength Characterization of Cement Stabilized and Fiber Reinforced Clay-Pond Ash Mixes. *Int. J. Geosynth. Gr. Eng.*, Vol. 2, 2016, pp. 1–11. doi:10.1007/s40891-016-0069-z.
- [6] Khelifi, H., Lecompte, T., Perrot, A., Ausias, G. Mechanical Enhancement of Cement-Stabilized Soil by Flax Fibre Reinforcement and Extrusion Processing. *Mater. Struct. Constr.*, Vol. 49, 2016, pp. 1143–1156. doi:10.1617/s11527-015-0564-z.
- [7] Gao, L., Zhou, Q., Yu, X., Wu, K., Mahfouz, A.H. Experimental Study on the Unconfined Compressive Strength of Carbon Fiber Reinforced Clay Soil. *Mar. Georesources*

- Geotechnol., Vol. 35, 2017, pp. 143–148. doi:10.1080/1064119X.2015.1102184.
- [8] Anggraini, V., Asadi, A., Huat, B.B.K., Nahazanan, H. Performance of Chemically Treated Natural Fibres and Lime in Soft Soil for the Utilisation as Pile-Supported Earth Platform. *Int. J. Geosynth. Gr. Eng.*, Vol. 1, 2015, pp. 1–14. doi:10.1007/s40891-015-0031-5.
- [9] Ashour, T., Wu, W. The Influence of Natural Reinforcement Fibers on Erosion Properties of Earth Plaster Materials for Straw Bale Buildings. *J. Build. Apprais.*, Vol. 5, 2010, pp. 329–340. doi:10.1057/jba.2010.4.
- [10] Brahmachary, T.K., Rokonzaman, M. Investigation of Random Inclusion of Bamboo Fiber on Ordinary Soil and Its Effect CBR Value. *Int. J. Geo-Engineering*, Vol. 9, 2018 doi:10.1186/s40703-018-0079-x.
- [11] Arifin, Y.F., Misnawati, Ridha, M. Laboratory Compaction Method of Soft Clay and Natural Plant Fiber/Shell Mixtures. *IOP Conf. Ser. Earth Environ. Sci.*, Vol. 499, 2020 doi:10.1088/1755-1315/499/1/012002.
- [12] Arifin, Y.F., Misnawati, Normelani, E. The Use of Natural Fiber from Oil Palm Empty Fruit Bunches for Soft Soil Stabilization. *IOP Conf. Ser. Mater. Sci. Eng.*, Vol. 669, 2019, pp. 2–10. doi:10.1088/1757-899X/669/1/012026.
- [13] Li, C., Zornberg, J.G. Mobilization of Reinforcement Forces in Fiber-Reinforced Soil. *J. Geotech. Geoenvironmental Eng.*, Vol. 139, 2013, pp. 107–115. doi:10.1061/(asce)gt.1943-5606.0000745.
- [14] Wu, H., Yao, C., Li, C., Miao, M., Zhong, Y., Lu, Y., Liu, T. Review of Application and Innovation of Geotextiles in Geotechnical Engineering. *Materials (Basel)*, Vol. 13, 2020, pp. 1–21. doi:10.3390/MA13071774.
- [15] Deb, K., Namaware, Y.K. Strength and Compressibility Characteristics of Fiber-Reinforced Subgrade and Their Effects on Response of Granular Fill-Subgrade System. *Transp. Dev. Econ.*, Vol. 1, 2015, pp. 1–9. doi:10.1007/s40890-015-0006-1.
- [16] Diambra, A., Ibrahim, E. Modelling of Fibre-Cohesive Soil Mixtures. *Acta Geotech.*, Vol. 9, 2014, pp. 1029–1043. doi:10.1007/s11440-013-0283-y.
- [17] Chou, J.S., Ngo, N.T. Engineering Strength of Fiber-Reinforced Soil Estimated by Swarm Intelligence Optimized Regression System. *Neural Comput. Appl.*, Vol. 30, 2018, pp. 2129–2144. doi:10.1007/s00521-016-2739-0.
- [18] Ramlie, N.A., Jawaid, M., Zainudin, E.S., Yamani, S.A.K. Tensile, Physical and Morphological Properties of Oil Palm Empty Fruit Bunch/Sugarcane Bagasse Fibre Reinforced Phenolic Hybrid Composites. *J. Mater. Res. Technol.*, Vol. 8, 2019, pp. 3466–3474. doi:10.1016/j.jmrt.2019.06.016.
- [19] Sandchee, S. Sustainable Kenaf/Bamboo Fibers/Clay Hybrid Nanocomposites: Properties, Environmental Aspects and Applications. 2022.
- [20] Arifin, Y.F., Misnawati, Normelani, E. The Use of Natural Fiber from Oil Palm Empty Fruit Bunches for Soft Soil Stabilization. In *Proceedings of the IOP Conference Series: Materials Science and Engineering*; 2019; Vol. 669.
- [21] Rao, K.M.M., Rao, K.M. Extraction and Tensile Properties of Natural Fibers: Vakka, Date and Bamboo. *Compos. Struct.*, Vol. 77, 2007, pp. 288–295. doi:10.1016/j.compstruct.2005.07.023.
- [22] Ali, M. Natural Fibres as Construction Materials. *J. Civ. Eng. Constr. Technol.*, Vol. 3, 2012, pp. 80–89. doi:10.5897/jcect11.100.
- [23] Omar, F.N., Mohammed, M.A.P., Baharuddin, A.S. Effect of Silica Bodies on the Mechanical Behaviour of Oil Palm Empty Fruit Bunch Fibres. *BioResources*, Vol. 9, 2014, pp. 7041–7058. doi:10.15376/biores.9.4.7041-7058.
- [24] Rama Rao, P., Ramakrishna, G. Oil Palm Empty Fruit Bunch Fiber: Surface Morphology, Treatment, and Suitability as Reinforcement in Cement Composites- A State of the Art Review. *Clean. Mater.*, Vol. 6, 2022, pp. 100144. doi:10.1016/j.clema.2022.100144.
- [25] Spritzer, J.M., Khachan, M.M., Bhatia, S.K. Influence of Synthetic and Natural Fibers on Dewatering Rate and Shear Strength of Slurries in Geotextile Tube Applications. *Int. J. Geosynth. Gr. Eng.*, Vol. 1, 2015, pp. 1–14. doi:10.1007/s40891-015-0027-1.
- [26] Wei, L., Chai, S., Xue, M., Wang, P., Li, F. Structural Damage and Shear Performance Degradation of Fiber-Lime-Soil under Freeze-Thaw Cycling. *Geotext. Geomembranes*, Vol. 50, 2022, pp. 845–857. doi:10.1016/j.geotextmem.2022.04.005.
- [27] Kozłowski, R.M., Mackiewicz-Talarczyk, M. Introduction to Natural Textile Fibres. Woodhead Publishing Limited: Sawston, UK, 2012.
- [28] DJP Produksi Kelapa Sawit Menurut Provinsi Di Indonesia , 2017-2021 Available online: <https://www.pertanian.go.id/>.
- [29] Santi, L.P., Kalbuadi, D.N., Geonadi, D.H. Empty Fruit Bunches As a Potential Source for Biosilica Fertilizer for Oil Palm. In *Proceedings of the Semnas Biologi Tropika: Pemanfaatan biodiversitas tropika untuk mewujudkan bio-based economy*; Jogjakarta, 2018; pp. 1–12.
- [30] Komuraiah, A., Kumar, N.S., Prasad, B.D. Chemical Composition of Natural Fibers and

- Its Influence on Their Mechanical Properties. *Mech. Compos. Mater.*, Vol. 50, 2014, pp. 359–376. doi:10.1007/s11029-014-9422-2.
- [31] Hamad, S.F., Stehling, N., Holland, C., Foreman, J.P., Rodenburg, C. Low-Voltage SEM of Natural Plant Fibers: Microstructure Properties (Surface and Cross-Section) and Their Link to the Tensile Properties. *Procedia Eng.*, Vol. 200, 2017, pp. 295–302. doi:10.1016/j.proeng.2017.07.042.
- [32] Paridah, M.T., Juliana, A.H., Zaidon, A., Abdul Khalil, H.P.S. Nonwood-Based Composites. *Curr. For. Reports*, Vol. 1, 2015, pp. 221–238. doi:10.1007/s40725-015-0023-7.
- [33] Omar, F.N., Mohammed, M.A.P., Baharuddin, A.S. Microstructure Modelling of Silica Bodies from Oil Palm Empty Fruit Bunch (OPEFB) Fibres. *BioResources*, Vol. 9, 2014, pp. 938–951. doi:10.15376/biores.9.1.938-951.
- [34] Danso, H. Properties of Coconut, Oil Palm and Bagasse Fibres: As Potential Building Materials. *Procedia Eng.*, Vol. 200, 2017, pp. 1–9. doi:10.1016/j.proeng.2017.07.002.
- [35] Peponi, L., Biagiotti, J., Torre, L., Kenny, J.M., Mondragon, I. Statistical Analysis of the Mechanical Properties of Natural Fibers and Their Composite Materials. I. Natural Fibers. *Polym. Compos.*, Vol. 29, 2008, pp. 313–320. doi:10.1002/pc.
- [36] Van Hofsten, B., Edberg, N. Estimating the Rate of Degradation of Cellulose Fibres in Water. *Oikos*, Vol. 23, 1972, pp. 29–34. doi:10.2307/3543924.
- [37] Tomšič, B., Marković, D., Janković, V., Simončič, B., Nikodinovic-Runic, J., Ilic-Tomic, T., Radetić, M. Biodegradation of Cellulose Fibers Functionalized with CuO/Cu₂O Nanoparticles in Combination with Polycarboxylic Acids. *Cellulose*, Vol. 29, 2022, pp. 287–302. doi:10.1007/s10570-021-04296-6.
- [38] Ye, W., Zhang, Y., Chen, B., Zhang, S. Characteristics of Shear Strength of Unsaturated Weak Expansive Soil. In *Proceedings of the International Symposium on Geoenvironmental Engineering*; Hangzhou, 2009; p. 505.
- [39] Vanapalli, S.K. Shear Strength of Unsaturated Soils and Its Applications in Geotechnical Engineering Practice. In *Proceedings of the Unsaturated Soils*; Buzzi, Fityus, Sheng, Eds.; Taylor & Francis: London, 2010; pp. 579–598.
- [40] Schanz, T., Arifin, Y.F., Khan, M.I., Agus, S.S. Time Effects on Total Suction of Bentonites. *Soils Found.*, Vol. 50, 2010 doi:10.3208/sandf.50.195.
- [41] Agus, S.S., Arifin, Y.F., Tripathy, S., Schanz, T. Swelling Pressure-Suction Relationship of Heavily Compacted Bentonite-Sand Mixtures. *Acta Geotech.*, Vol. 8, 2013, pp. 155–165. doi:10.1007/s11440-012-0189-0.
- [42] Moslemi, A., Tabarsa, A., Mousavi, S.Y., Aryaie Monfared, M.H. Shear Strength and Microstructure Characteristics of Soil Reinforced with Lignocellulosic Fibers-Sustainable Materials for Construction. *Constr. Build. Mater.*, Vol. 356, 2022, pp. 129246. doi:10.1016/j.conbuildmat.2022.129246.
- [43] Nezhad, M.G., Tabarsa, A., Latifi, N. Effect of Natural and Synthetic Fibers Reinforcement on California Bearing Ratio and Tensile Strength of Clay. *J. Rock Mech. Geotech. Eng.*, Vol. 13, 2021, pp. 626–642. doi:10.1016/j.jrmge.2021.01.004.
- [44] Obrzud, R.F., Truty, A. *The Hardening Soil Model - a Practical Guidebook*. Zace Services Ltd, Software engineering: Switzerland, 2018.
- [45] Muntohar, A.S., Widiarti, A., Hartono, E., Diana, W. Engineering Properties of Silty Soil Stabilized with Lime and Rice Husk Ash and Reinforced with Waste Plastic Fiber. *J. Mater. Civ. Eng.*, Vol. 25, 2013, pp. 1260–1270. doi:10.1061/(asce)mt.1943-5533.0000659.
- [46] Wu, Y., Li, Y., Niu, B. Assessment of the Mechanical Properties of Sisal Fiber-Reinforced Silty Clay Using Triaxial Shear Tests. *Sci. World J.*, Vol. 2014, 2014 doi:10.1155/2014/436231.
- [47] Estabragh, A.R., Ranjbari, S., Javadi, A.A. Properties of a Clay Soil and Soil Cement Reinforced with Polypropylene Fibers. *ACI Mater. J.*, Vol. 114, 2017 doi:10.14359/51689469.
- [48] Lal, D., Reddy, P., Kumar, R.S., Rao, V.G. Stabilization of Expansive Soil by Using Jute Fiber. *IOP Conf. Ser. Mater. Sci. Eng.*, Vol. 998, 2020, pp. 1–6. doi:10.1088/1757-899X/998/1/012045.

TENSILE STRENGTH AND DURABILITY OF OIL PALM EMPTY FRUIT BUNCH FIBER IN SOFT SOIL

ORIGINALITY REPORT

17%

SIMILARITY INDEX

11%

INTERNET SOURCES

15%

PUBLICATIONS

%

STUDENT PAPERS

MATCH ALL SOURCES (ONLY SELECTED SOURCE PRINTED)

3%

★ Cellulose Fibers Bio- and Nano-Polymer Composites, 2011.

Publication

Exclude quotes On

Exclude matches Off

Exclude bibliography On