

# Selective Hydrogenation of Dodecanoic Acid to Dodecane- 1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy

*by Susi .*

---

**Submission date:** 29-May-2023 12:06PM (UTC+0700)

**Submission ID:** 2104300764

**File name:** Selective\_Hydrogenation\_of\_Dodecanoic\_Acid\_to.pdf (469.18K)

**Word count:** 5774

**Character count:** 29400

Research Article

## Selective Hydrogenation of Dodecanoic Acid to Dodecane-1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy

R. Rodiansono<sup>1,\*</sup>, Muhammad Iqbal Pratama<sup>1</sup>, Maria Dewi Astuti<sup>1</sup>, A. Abdullah<sup>1</sup>, Agung Nugroho<sup>2</sup>, S. Susi<sup>2</sup>

<sup>1</sup>Department of Chemistry, Faculty of Mathematics and Natural Sciences, Lambung Mangkurat University, Jl. A. Yani Km 36.0 Banjarbaru South Kalimantan, Indonesia.

<sup>2</sup>Department of Agro-industrial Engineering, Faculty of Agriculture, Lambung Mangkurat University, Jl. A. Yani Km 36.0 Banjarbaru South Kalimantan, Indonesia

Received: 26<sup>th</sup> November 2017; Revised: 24<sup>nd</sup> December 2017; Accepted: 24<sup>th</sup> January 2018;  
Available online: 11<sup>th</sup> June 2018; Published regularly: 1<sup>st</sup> August 2018

### Abstract

Selective hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn alloy catalysts into dodecane-1-ol is demonstrated. Bimetallic nickel-tin supported on titanium oxide (Ni-Sn(1.5)/TiO<sub>2</sub>) and gamma-alumina (Ni-Sn(1.5)/γ-Al<sub>2</sub>O<sub>3</sub>); 1.5 = Ni/Sn molar ratio) were synthesized via hydrothermal method in a sealed-Teflon autoclave reactor at 150 °C for 24 h, then followed by reducing with hydrogen gas at 400 °C for 1.5 h. The synthesized catalysts were characterized by means of XRD, IC-AES, N<sub>2</sub>-adsorption (BET method), H<sub>2</sub>-chemisorption, and NH<sub>3</sub>-TPD. Bimetallic Ni-Sn(1.5)/TiO<sub>2</sub> catalyst was found to be effective for hydrogenation of dodecanoic acid (>99 % conversion) to dodecane-1-ol (93% yield) at 160 °C, 30 bar H<sub>2</sub>, and 20 h and the highest dodecane-1-ol (97 % yield) was obtained at initial pressure of H<sub>2</sub>, 50 bar. An increase of reaction temperature slightly enhanced the degree of hydrodeoxygenation of dodecanoic acid to produce dodecane over both Ni-Sn(1.5)/TiO<sub>2</sub> and Ni-Sn(1.5)/γ-Al<sub>2</sub>O<sub>3</sub> catalysts. Copyright © 2018 BCREC Group. All rights reserved

**Keywords:** Bimetallic Nickel-Tin Alloy Catalyst; Dodecane; Dodecanoic Acid; Dodecane-1-ol; Hydrogenation

**How to Cite:** Rodiansono, R. Pratama, M.I., Astuti, M.D., Abdullah, A., Nugroho, A., Susi, S. (2018). Selective Hydrogenation of Dodecanoic Acid to Dodecane-1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy. *Bulletin of Chemical Reaction Engineering & Catalysis*, 13 (2): 311-319 (doi:10.9767/bcrec.13.2.1790.311-319)

**Permalink/DOI:** <https://doi.org/10.9767/bcrec.13.2.1790.311-319>

### 1. Introduction

The development of oleochemical products including surfactants, lubricants, plasticizers, coatings, and polymers has been made possible by remarkable advances made in organic syn-

thesis, catalysis, and biotechnology [1]. Fatty alcohol is one of the important basic oleochemicals which could be produced by hydrogenation of fatty acids or its esters by using heterogeneous catalysts (e.g. bimetallic copper chromite), but the reaction requires harsh temperature (e.g., up to 300 °C) and pressure (e.g., up to 300 bar of H<sub>2</sub>) in the presence of copper-chromite catalysts, which are potentially harmful for the environ-

\* Corresponding Author.

E-mail: [rodiansono@ulm.ac.id](mailto:rodiansono@ulm.ac.id) (R. Rodiansono)  
Telp: +62-5114773112, Fax: +62-5114782899

ment [2,3]. In this regard, the development of catalysts to produce fatty alcohols under milder conditions has been long-standing industrial target.

Many previous attempts on the reduction of the reaction pressures (down to 20 bar H<sub>2</sub>) have been achieved with high conversion and selectivities by replacing Cu or Cr with noble metals such as Ru, Rh, Re, Pd, or Pt [4]. For example, the hydrogenation of carboxylic acids to alcohols using a Pt/TiO<sub>2</sub> catalyst as reported recently by Hardacre et al. at only 130 °C, 20 bar H<sub>2</sub> and gave over 80 % conversion (with 90 % selectivity) after 12 h [5]. Although these results are remarkable, it would be desirable to replace the expensive noble metals with more abundant and economic catalysts still capable of working at low H<sub>2</sub> pressures and moderate reaction temperatures. The commercial Ni-based catalysts such as: RANEY Ni/Kieselgur, or Ni/Al<sub>2</sub>O<sub>3</sub> had been applied for fatty acids or fatty ester hydrogenation with high activity. However, the important drawbacks of these catalysts are low selectivity to desired products (i.e., produced the mixture of *cis*- and *trans*-product) and easily deactivated due to carbon deposited on the metal surface [6].

Interactions between metals in bimetallic catalysts can modify their surfaces, which can be beneficial for the conversion and upgrading of highly complex biomass derived compounds [7-9]. In previously published studies, several bimetallic alloy transition metal catalysts (e.g. Pd-M (M = Cu, Co, Ni) [10], Pd-Nb<sub>2</sub>O<sub>5</sub> [11], Ru-Sn [12] Rh-Sn [13], and Ru<sub>3</sub>-B [14] have shown superior performance for the selective hydrogenation of fatty acids compared with their single metal counterpart. Huang et al. [10] reported the catalytic performances of supported bimetallic Pd-M (M = Cu, Co, Ni) catalysts in hydrogenation of methyl palmitic in n-heptane solvent at 270 °C, H<sub>2</sub> 55 bar within 22 h. Among these bimetallic catalysts, Pd-Cu/diatomite with loading amount of 1 % (Pd/Cu = 3) displayed the highest catalytic performances in hydrogenation of palmitic acid (99 % conversion) giving 1-hexadecanol (83 % yield) [10]. On the other hand, by using Pd/Nb<sub>2</sub>O<sub>5</sub>/SiO<sub>2</sub> catalyst, a significant improvement of 1-hexadecanol yield was achieved (c.a. 97 % yield) from palmitic acid in cyclohexane at 180 °C, H<sub>2</sub> 25 bar, within 24 h of reaction time [11].

In previous reports, bimetallic Ru-based catalysts have also demonstrated high activity in hydrogenation of methyl oleate at relatively high temperature and H<sub>2</sub> pressure (ca. 270 °C and 44 bar, respectively) within 7 h. However,

the conversion of methyl oleate and selectivity of oleyl alcohol were only 80 % and 70 %, respectively. The addition of electropositive atom of Sn and B to Ru enhanced the dispersion of Ru and improved the electron density of Ru. The change of electron density Ru enhanced the affinity of Ru towards C=O bond of fatty acids which facilitated the reaction hydrogenation [12,13]. Similar results have been also reported on the hydrogenation of dodecanoic acid and palmitic acid at 300 °C, 60 bar H<sub>2</sub>, within 4 h over Ru-Sn/Al<sub>2</sub>O<sub>3</sub> and Rh-Sn/Al<sub>2</sub>O<sub>3</sub> catalysts and produced lauryl alcohol and hexadecane-1-ol, respectively. On the other hand, Ru-Ge-B/Al<sub>2</sub>O<sub>3</sub> catalyst gave only 20 % of oleyl alcohol with conversion of methyl oleic, ca. 80 % [14].

In our previous investigations, we have reported the synthesis of both bulk and supported bimetallic Ni-Sn alloy catalysts from two types nickel precursors: first, from nickel salt (e.g. NiCl<sub>2</sub> or NiCl<sub>2</sub>·4H<sub>2</sub>O) produced from both bulk and supported Ni-Sn alloys [15] and, second, from Raney Ni-supported on aluminium hydroxide (R-Ni/AlOH), which produced a nickel-tin alloy supported on aluminium hydroxide (Ni-Sn(x)/AlOH; x = Ni/Sn molar ratio) [16]. We have also recently reported the catalytic performance of the Ni-Sn alloy during hydrogenation of biomass-derived levulinic acid in water to  $\gamma$ -valerolactone (GVL) [17]. Over bulk Ni-Sn alloy catalysts, a relatively high reaction temperature (150 °C, 40 bar H<sub>2</sub>, 6 h) was applied to achieve both a high conversion and GVL yield (99 %) [18]. Alternatively, a GVL yield of >99 % was obtained over Ni-Sn(x)/AlOH catalysts at a lower reaction temperature (120 °C) compared to the bulk catalysts [19].

In this present report, we continue our extend investigation of the hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn alloy catalysts to the corresponding of lauryl alcohol. Bimetallic Ni-Sn alloy was supported on two types of supports c.a. titanium oxide (TiO<sub>2</sub>) and gamma-alumina ( $\gamma$ -Al<sub>2</sub>O<sub>3</sub>). Monometallic nickel supported on TiO<sub>2</sub> (Ni/TiO<sub>2</sub>) and  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>) catalysts were also evaluate for comparison.

8

## 2. Materials and Methods

### 2.1 Materials

Sodium hydroxide (NaOH) (97 %), nickel(II) chloride hexahydrate (NiCl<sub>2</sub>·6H<sub>2</sub>O, 99.9%), tin(II) chloride dihydrate (SnCl<sub>2</sub>·2H<sub>2</sub>O, 99.9%), aluminium hydroxide, and TiO<sub>2</sub> (mixture of rutile and anatase; S<sub>BET</sub> = 50 m<sup>2</sup>g<sup>-1</sup>) were pur-

19

chased and used as received from WAKO Pure Chemical Industries, Ltd. unless otherwise stated. The  $\gamma$ - $\text{Al}_2\text{O}_3$  ( $S_{\text{BET}} = 100 \text{ m}^2\text{g}^{-1}$ ) were purchased from Japan Aerosil Co. All organic chemical compounds were purified using standard procedures prior to use.

## 2.2 Catalyst preparation

### 2.2.1 Synthesis of Ni-Sn(1.5)/TiO<sub>2</sub>

A typical procedure of the synthesis of titanium oxide supported Ni-Sn (1.5 is feeding ratio) alloy catalyst is described as follows [15]:  $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$  (7.2 mmol) was dissolved in deionized water (denoted as solution A), and  $\text{SnCl}_4 \cdot 2\text{H}_2\text{O}$  (4.8 mmol) was dissolved in ethanol/2-methoxy ethanol (2:1) (denoted as solution B) at room temperature. A one-gram titanium dioxide ( $\text{TiO}_2$ ), solutions A, and B were mixed at room temperature; the temperature was subsequently raised to 50 °C and the mixture was stirred for 12 h. The pH of the mixture was adjusted to 12 through the dropwise addition of an aqueous solution of NaOH (3.1 M). The mixture was then placed into a sealed-Teflon autoclave for the hydrothermal reaction at 150 °C for 24 h. The resulting black precipitate was filtered, washed with distilled water, and then dried under vacuum overnight. Prior to the catalytic reaction, the obtained black powder was treated under hydrogen at 400 °C for 1.5 h.

### 2.2.2 Catalyst characterization

Powder X-ray diffraction (XRD) measurements were recorded on a Mac Science M18XHF instrument using monochromatic CuK $\alpha$  radiation ( $\lambda = 0.15418 \text{ nm}$ ). The XRD was operated at 40 kV and 200 mA with a step width of 0.02° and a scan speed of 4° min<sup>-1</sup> ( $\alpha_1 = 0.154057 \text{ nm}$ ,  $\alpha_2 = 0.154433 \text{ nm}$ ). Inductively coupled plasma-atomic emission spectroscopy (ICP-AES) measurements were performed on an SPS 1800H plasma spectrometer by Seiko Instruments Inc. Japan (Ni: 221.7162 nm and Zn: 189.898 nm). The Brunauer-Emmett-Teller surface area ( $S_{\text{BET}}$ ) and pore volume ( $V_p$ ) were measured using N<sub>2</sub> physisorption at -196 °C on a Belsorp Max (BEL Japan). The samples were degassed at 200 °C for 2 h to remove physisorbed gases prior to the measurement. The amount of nitrogen adsorbed onto the samples was used to calculate the BET surface area via the BET equation. The pore volume was estimated to be the liquid volume of nitrogen at a relative pressure of approximately 0.995 ac-

ording to the Barrett-Joyner-Halenda (BJH) approach based on desorption data [20].

The H<sub>2</sub> uptake was determined through irreversible H<sub>2</sub> chemisorption. After the catalyst was heated at 100 °C under vacuum for 30 min, it was then heated at 400 °C under H<sub>2</sub> for 30 min. The catalysts were subsequently cooled to room temperature under vacuum for 30 min. The H<sub>2</sub> measurement was conducted at 0 °C, and the H<sub>2</sub> uptake was calculated according to a method described in the literature [21,22].

The NH<sub>3</sub>-TPD was carried out on a Belsorp Max (BEL Japan). The samples were degassed at elevated temperature of 100-200 °C for 2 h to remove physisorbed gases prior to the measurement. The temperature was then kept at 200 °C for 2 h while flushed with He gas. NH<sub>3</sub> gas (balanced NH<sub>3</sub>, 80 %, and He, 20 %) was introduced at 100 °C for 30 min, then evacuated by helium gas to remove the physisorbed also for 30 min. Finally, temperature programmed desorption was carried out at temperature of 100-800 °C and the desorbed NH<sub>3</sub> was monitored by TCD.

## 2.3 Catalytic reaction

Typical catalytic reaction procedure as follows. Catalyst (0.05 g), dodecanoic acid (1.8 mmol), internal standard 1,6-hexanediol (0.03 mmol) and *iso*-PrOH (5 mL) as solvent were placed into a glass reaction tube, which fitted inside a stainless-steel reactor. The reactor was flushed with H<sub>2</sub> for ~30 times. Finally, after H<sub>2</sub> was introduced into the reactor with an initial H<sub>2</sub> pressure of 30 bar at room temperature, the temperature of the reactor was increased to 160 °C. After 6 h of the reaction, both heating and stirring were stopped, the autoclave was removed from the hot plate and then cooled in ice-cold water. Once cooled, the contents of the autoclave were transferred into sample bin then centrifuged (~4000 rpm for 10 min) and ready for GC-FID analysis. The Ni-Sn(1.5)/TiO<sub>2</sub> catalyst was easily separated using either simple centrifugation (4000 rpm for 10 min) or filtration, then finally dried overnight under vacuum at room temperature prior to re-usability testing.

## 2.4 Product analysis

Gas chromatography analysis of the reactant (dodecanoic acid) and products was performed on a Perkin Elmer Autosystem XL with a flame ionization detector with an InertCap 225 (i.d. 0.25 mm, length 30 m, d.f. 0.25 mm) capillary column of GL Science Inc. Tokyo Ja-

pan. The products were confirmed by a comparison of their GC retention time, mass spectra with those of authentic sample. Gas chromatography-mass spectrometry (GC-MS) was performed on a Shimadzu GC-17B equipped with a thermal conductivity detector and an RT- $\beta$ DEXsm capillary column.

The amount of remained reactant and products were determined from GC data using internal standard of 1,6-hexanediol that was introduced to the reactor before reaction run. Calibration curve was performed using known concentrations of internal standard, reactants and products in order to determine the correct response factors. The conversion of dodecanoic acid, yield, and selectivity of the products were calculated according to the following equations:

$$\text{Conversion} = \frac{F_0 - F_t}{F_0} \times 100\% \quad (1)$$

$$\text{Yield} = \frac{\text{mol product}}{F_0} \times 100\% \quad (2)$$

$$\text{Selectivity} = \frac{\text{mol product}}{\text{total mol products}} \times 100\% \quad (3)$$

where  $F_0$  is the introduced mol reactant (dodecanoic acid),  $F_t$  is the remaining mol reactant, and  $\Delta F$  is the consumed mol reactant (introduced mol reactant - remained mol reactant), which are all obtained from GC analysis using an internal standard technique.

### 3. Results and Discussion

#### 3.1 Catalyst characterization

The chemical compositions, BET specific surface area ( $S_{\text{BET}}$ ), and total pore volume ( $V_p$ ) for  $\gamma$ - $\text{Al}_2\text{O}_3$  or  $\text{TiO}_2$  supported Ni-Sn(1.5) catalysts after  $\text{H}_2$  treatment at 400 °C for 1.5 h are summarized in Table 1. Based on the ICP-AES analyses, the compositions of the supported Ni-Sn alloy were approximately equivalent to the

feeding ratios of each precursor and were reflected in the composition of each Ni-Sn alloy phase. The total loading amount of Ni-Sn 2.3~2.4 mmol.g<sup>-1</sup> for all of the supported Ni-Sn(1.5) samples (the composition (mol%) of Ni and Sn are listed in Table 1). The  $S_{\text{BET}}$  and total pore volume ( $V_p$ ) of each supported Ni-Sn(1.5) alloy samples were also summarized in Table 1. It is found that the  $S_{\text{BET}}$  and  $V_p$  of Ni-Sn(1.5)/ $\gamma$ - $\text{Al}_2\text{O}_3$  were 94 m<sup>2</sup>g<sup>-1</sup> and 0.39 cm<sup>3</sup>g<sup>-1</sup>, respectively (entry 1), while for Ni-Sn(1.5)/ $\text{TiO}_2$  were 52 m<sup>2</sup>g<sup>-1</sup> and 0.17 cm<sup>3</sup>g<sup>-1</sup> (entry 2). It can be observed that  $S_{\text{BET}}$  and total pore volume of  $\text{TiO}_2$  supported catalyst lower than that of  $\gamma$ - $\text{Al}_2\text{O}_3$  supported catalysts. It was reported that metal species lead more dispersible on support with lower porosity (e.g.  $\text{TiO}_2$ ) due to strong interaction between metal and support which will prevent metal aggregation or sintering during thermal treatment [15,23].

The  $\text{H}_2$  uptake for Ni-Sn(1.5)/ $\text{TiO}_2$  and Ni-Sn(1.5)/ $\gamma$ - $\text{Al}_2\text{O}_3$  samples were 9.0 and 13.0  $\mu\text{mol g}^{-1}$ , respectively and the average Ni-Sn alloy crystallite sizes derived from Scherrer equation of  $\text{Ni}_3\text{Sn}_2$  (101) phase at  $2\theta = 30.8^\circ$  were 16 nm and 6 nm, respectively. The  $\text{H}_2$  uptake supported Ni-Sn alloy in this work was much lower than that of the Raney Ni or supported Ni on aluminium hydroxide, suggesting that the presence of second metal of Sn reduced significantly the accessibility of hydrogen on the surface of Ni metal. Consequently, the catalytic reaction may be effectively proceeded at high pressure of  $\text{H}_2$  as its have been reported previously [15-19].

The XRD patterns of Ni-Sn(1.5)/ $\gamma$ - $\text{Al}_2\text{O}_3$  alloy catalyst after  $\text{H}_2$  treatment at 400 °C for 1.5 h are shown in Figure 1. It can be observed easily that  $\text{Ni}_3\text{Sn}_2$  species as major alloy phase was formed on  $\gamma$ - $\text{Al}_2\text{O}_3$  with sharpened peaks with very similar patterns to the JCPDS card standard of  $\text{Ni}_3\text{Sn}_2$  of 6-414 [24]. On the other hand, the XRD patterns Ni-Sn(1.5)/ $\text{TiO}_2$  exhibited broadened peaks at  $2\theta = 30.8^\circ$ ,  $42.5^\circ$ , and  $44.2^\circ$ , which correspond to the  $\text{Ni}_3\text{Sn}_2$  (101),

**Table 1.** Chemical composition, BET surface area ( $S_{\text{BET}}$ ), and total pore volume ( $V_p$ ) for Ni-Sn(1.5)/ $\gamma$ - $\text{Al}_2\text{O}_3$  and Ni-Sn(1.5)/ $\text{TiO}_2$  catalysts after  $\text{H}_2$  treatment at 400 °C for 1.5 h.

Entry	Catalyst <sup>a</sup>	Comp. <sup>b</sup> (mol%)	$S_{\text{BET}}^c$ (m <sup>2</sup> g <sup>-1</sup> )	$V_p^c$ (cm <sup>3</sup> g <sup>-1</sup> )
1	Ni-Sn(1.5)/ $\gamma$ - $\text{Al}_2\text{O}_3$	Ni <sub>60.2</sub> Sn <sub>39.8</sub>	94	0.39
2	Ni-Sn(1.5)/ $\text{TiO}_2$	Ni <sub>60.4</sub> Sn <sub>39.6</sub>	52	0.17

<sup>a</sup>The value between the parenthesis is Ni/S molar ratio. <sup>b</sup>Molar composition of Ni or Sn, determined by ICP-AES. <sup>c</sup>Determined by  $\text{N}_2$  adsorption at -196 °C. The pore volume was estimated to be the liquid volume of nitrogen at a relative pressure of approximately 0.995 according to the Barrett-Joyner-Halenda (BJH) approach based on desorption data.

Ni<sub>3</sub>Sn<sub>2</sub> (102), and Ni<sub>3</sub>Sn<sub>2</sub> (110) diffraction peaks, respectively (Figure 2). These results suggest that the higher dispersions of Ni-Sn alloy on the TiO<sub>2</sub> were formed as roughly depicted in the average Ni<sub>3</sub>Sn<sub>2</sub> (101) crystallite sizes, which were 6 nm (Table 2). In conclusion, the XRD analysis and H<sub>2</sub> measurement results confirm that Ni-Sn alloy phases were also formed on the supports and that their characteristics were consistent with the results observed for the bulk material as reported previously [15].

The results of ammonia-temperature programmed desorption (NH<sub>3</sub>-TPD) measurements of the synthesized catalysts are summarized in Table 3 and the NH<sub>3</sub>-TPD profiles are shown in Figure 3 and Figure 4. It can be observed that Ni-Sn(1.5)/γ-Al<sub>2</sub>O<sub>3</sub> alloy catalyst consisted of three different peak positions of 178, 510, and

607 °C with acidic amount of 0.23, 0.03, and 0.09 mmol.g<sup>-1</sup>, respectively (Figure 3 and Table 3, entry 1) with total number of acid sites = 0.35 mmol.g<sup>-1</sup>. Therefore, it can be concluded that Ni-Sn(1.5)/γ-Al<sub>2</sub>O<sub>3</sub> catalyst has mainly weak acid sites. On the other hand, Ni-Sn(1.5)/TiO<sub>2</sub> displayed the peak position at 611 °C with total number of acidic sites = 0.29 mmol.g<sup>-1</sup> that can be attributed to the strong acid sites (Figure 4 and Table 3, entry 2) [25, 26].

### 3.2 Hydrogenation of dodecanoic acid

#### 3.2.1 Screening of catalysts

Results of selective hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn(1.5) catalysts are summarized in Table 4 and the reaction pathways are shown in

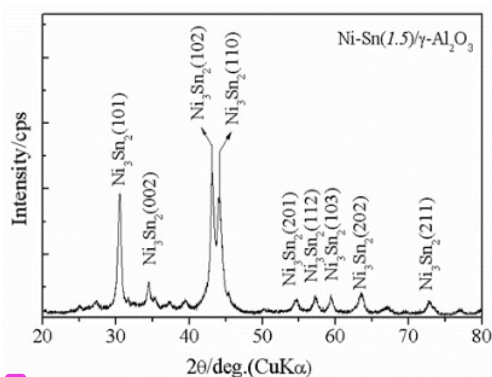


Figure 1. XRD patterns of bimetallic Ni-Sn(1.5) supported on g-Al<sub>2</sub>O<sub>3</sub> after H<sub>2</sub> treatment at 400 °C for 1.5 h

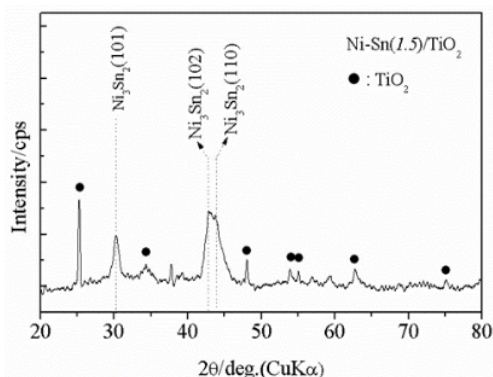


Figure 2. XRD patterns of bimetallic Ni-Sn(1.5) alloy supported on TiO<sub>2</sub> after H<sub>2</sub> treatment at 400 °C for 1.5 h

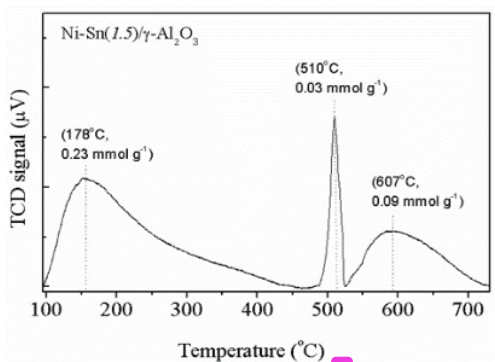


Figure 3. NH<sub>3</sub>-TPD spectra of Ni-Sn(1.5)/γ-Al<sub>2</sub>O<sub>3</sub> catalyst after H<sub>2</sub> treatment at 400 °C for 1.5 h

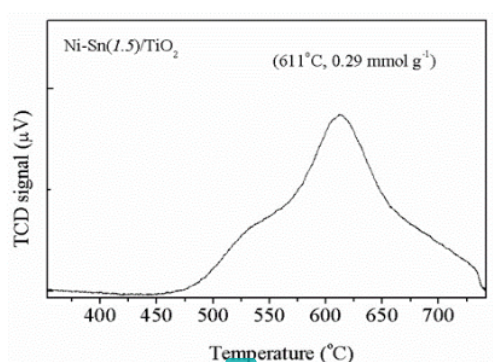


Figure 4. NH<sub>3</sub>-TPD spectra of Ni-Sn(1.5)/TiO<sub>2</sub> catalyst after H<sub>2</sub> treatment at 400 °C for 1.5 h

Scheme 1. It can be observed that by using the Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts, the conversion of dodecanoic acid was 59 % with dodecane-1-ol yield was 40 % while dodecane-1,1-diol and dodecane yields were 1 % and 4 %, respectively (entry 1). The conversion of dodecanoic acid reached 89 % when the reaction time was extended to 16 h and yielded 57 % and 4 % of dodecane-1-ol and dodecane, respectively (entry 2). Interestingly, Ni-Sn(1.5)/TiO<sub>2</sub> catalyst displayed a high conversion of dodecanoic acid (c.a. 85 %) and high yield of dodecane-1-ol (c.a. 80 %) (entry 3). The yield of dodecane-1-ol increased significantly to 90 % (with 97 % conversion) without significant formation of by-product when the reaction time was extended to 16 h (entry 4). It can be observed that Ni-

Sn(1.5)/TiO<sub>2</sub> catalyst showed higher catalytic performance than that of Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. The high conversion of dodecanoic acid and the high yield of dodecane-1-ol over Ni-Sn(1.5)/TiO<sub>2</sub> can be attributed to the relatively high dispersion of Ni-Sn alloy on TiO<sub>2</sub> giving rise to active sites with a significantly higher catalytic activity. Alternatively, the high conversion and selectivity may be a result of the strong interactions between the active metals and TiO<sub>2</sub> generating significant interactions between C=O groups and Ni-TiO<sub>x</sub> sites and leading to high selectivity to dodecane-1-ol [27].

The results of re-usability test confirmed that Ni-Sn(1.5)/TiO<sub>2</sub> catalyst was re-usable and the activity and selectivity of the catalyst can be restored to the initial after reducing with H<sub>2</sub>

**Table 2.** H<sub>2</sub> chemisorption and average crystallite sizes of Ni<sub>3</sub>Sn<sub>2</sub> alloy phase for Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> and Ni-Sn(1.5)/TiO<sub>2</sub> catalysts after H<sub>2</sub> treatment at 400 °C for 1.5 h

Entry	Catalyst <sup>a</sup>	H <sub>2</sub> uptake <sup>b</sup> (mmol g <sup>-1</sup> )	D <sup>c</sup> (nm)
1	Ni-Sn(1.5)/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	9.1	16
2	Ni-Sn(1.5)/TiO <sub>2</sub>	13.0	6

<sup>a</sup>The value between the parenthesis is Ni/Sn molar ratio. <sup>b</sup>Based on total H<sub>2</sub> uptake at 0 °C (noted after corrected for physical and chemical adsorption). <sup>c</sup>The average crystallite sizes of Ni<sub>3</sub>Sn<sub>2</sub>(101) alloy phase at  $2\theta = 30.8^\circ$  was derived from Scherrer equation.

**Table 3.** NH<sub>3</sub>-TPD results for Ni-Sn(1.5) alloy supported on  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> and TiO<sub>2</sub> catalysts after H<sub>2</sub> treatment at 400 °C for 1.5 h

Entry	Catalyst <sup>a</sup>	NH <sub>3</sub> -TPD data <sup>b</sup>	
		Peak position (°C)	Acidic amount <sup>c</sup> (mmol.g <sup>-1</sup> )
1	Ni-Sn(1.5)/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	178 (weak)	0.23
		510 (medium)	0.03
		607 (strong)	0.09
2	Ni-Sn(1.5)/TiO <sub>2</sub>	611 (strong)	0.29

<sup>a</sup>The value in the parenthesis is Ni/Sn molar ratio. <sup>b</sup>Ammonia-temperature programmed desorption (NH<sub>3</sub>-TPD). <sup>c</sup>Acidic amount (mmol.g<sup>-1</sup>) was derived from NH<sub>3</sub>-TPD spectra.

**Table 4.** Results of dodecanoic acid hydrogenation/hydrodeoxygenation over supported Ni-based catalysts

Entry	Catalyst <sup>a</sup>	LA of Ni <sup>b</sup> (mmol g <sup>-1</sup> )	Conversion <sup>c</sup> (%)	Yield <sup>e</sup> (%)			
				(1)	(2)	(3)	Others <sup>d</sup>
1	Ni-Sn(1.5)/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	2.4	59	40	1	4	14
2 <sup>e</sup>	Ni-Sn(1.5)/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	2.4	89	57	0	4	28
3	Ni-Sn(1.5)/TiO <sub>2</sub>	2.5	85	80	0	3	2
4 <sup>e</sup>	Ni-Sn(1.5)/TiO <sub>2</sub>	2.5	97	90	0	6	1
5 <sup>f</sup>	Ni-Sn(1.5)/TiO <sub>2</sub>	2.5	85	83	0	1	1
6 <sup>g</sup>	Ni-Sn(1.5)/TiO <sub>2</sub>	2.5	11	0	0	0	10
7	Ni/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	2.7	55	23	0	7	25
8	Ni/TiO <sub>2</sub>	2.6	41	39	0	2	0
9	Sn/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	3.7	0	0	0	0	0
10 <sup>h</sup>	Ni-Sn(1.5)/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	2.4	>99	85	0	9	6

**Reaction conditions:** Catalyst, 0.01 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL, 160 °C; H<sub>2</sub> pressure 30 bar, reaction time is 6 h. <sup>a</sup>The value in the parenthesis is Ni/Sn molar ratio. <sup>b</sup>Loading amount of Ni metal, determined by ICP-AES. <sup>c</sup>Conversion and selectivity of the main products were determined by GC using an internal standard technique. Product (1) = dodecane-1-ol, (2) dodecane-1,1-diol, and (3) dodecane. <sup>d</sup>Other products were mainly C<sub>11</sub> hydrocarbon including undecane (C<sub>11</sub>H<sub>24</sub>), undecene (C<sub>11</sub>H<sub>22</sub>), and trace amount of cracking product like 1-pentylbenzene was identified by using GC-MS analysis. <sup>e</sup>Reaction time was 16 h. <sup>f</sup>Re-usability test (second reaction run) after the recovered Ni-Sn(1.5)/TiO<sub>2</sub> was re-activated by reducing with H<sub>2</sub> at 400 °C for 1.5 h. <sup>g</sup>The catalytic reaction in absence of H<sub>2</sub> gas. <sup>h</sup>Reaction temperature was 180 °C, reaction time 6 h.


(85 % conversion and 83 % yield, entry 5). Catalytic reaction over Ni-Sn(1.5)/TiO<sub>2</sub> catalyst in absence of H<sub>2</sub> gas gave dodecanoic acid conversion of 11 % without the formation of hydrogenated products (entry 6). Compared to the supported bimetallic catalysts, monometallic Ni/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> and Ni/TiO<sub>2</sub> catalysts exhibited lower activity under the same reaction conditions (entries 7 and 8). Moreover, Sn/AlOH was not active as catalysts and did not produce the hydrogenated products under the same conditions (entry 9). In addition, Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst produced dodecane-1-ol (85 %), dodecane (9%), and other products (6 %) when the reaction temperature was 180 °C within 6 h (entry 10).

### 3.2.2 Profile of reaction kinetics

Kinetics of the hydrogenation of dodecanoic acid over bimetallic Ni-Sn(1.5)/TiO<sub>2</sub> and Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts are shown in Figure 5. When Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst was used, dodecanoic acid was slowly increased at the initial reaction time to achieve a 93 % yield after 24 h. Therefore, a similar explanation can be applied to the current results as follows. The induction periods could be associated with the slow formation of oxidic tin (Sn<sup>IV</sup>) from metallic tin (Sn<sup>0</sup>), as reported by Sordelli *et al.* (Rh-Sn) [28] and Margitfalvi *et al.* (Pt-Sn) [29]. Since the crystallite size or dispersion of Ni-Sn alloy could affect the length of the induction period, the induction period of Ni-Sn(1.5)/TiO<sub>2</sub> diminished, and a 100 % dodecanoic acid conversion (~90 % dodecane-1-ol yield) was achieved after 20 h. The excellent catalytic performance of Ni-Sn(1.5)/TiO<sub>2</sub> produces a promising candidate suitable for the large-scale production of dodecane-1-ol from the selective hydrogenation of dodecanoic acid.

### 3.2.3 Effect of reaction temperature

The effect of reaction temperature on the catalytic performance of Ni-Sn(1.5)/TiO<sub>2</sub> in do-

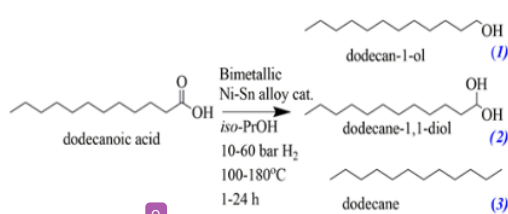


**Scheme 1.** Hydrogenation of dodecanoic acid over supported bimetallic Ni-Sn(1.5) alloy catalysts.

decanoic acid hydrogenation are also investigated and the results are shown in Figure 6. The conversion of dodecanoic acid gradually increased as the increase of reaction temperature and reached to completed reaction at 180 °C within 6 h with dodecane-1-ol yield of 91 % (entry 4). A small amount of dodecane (4 % yield) and other products (total yield of 12 %) were observed at 100 °C and diminished at higher reaction temperature. These results indicated that further reaction of dodecane-1-ol did not occur effectively over Ni-Sn(1.5)/TiO<sub>2</sub> catalyst.

### 3.2.4 Effect of initial pressure of H<sub>2</sub>

The effect of the initial H<sub>2</sub> pressure on the dodecanoic acid conversion and product selectivity is shown in Figure 7. The conversion of dodecanoic acid and dodecane-1-ol yield increased, whereas the selectivity of (2), (3), and other products decreased smoothly to almost 0% between 40-60 bar. The highest yield of dodecane-1-ol (97 %) was achieved at initial pressure H<sub>2</sub> of 50-60 bar, suggesting the hydrogenation reaction of dodecanoic acid to dodecane-1-ol over Ni-Sn(1.5)/TiO<sub>2</sub> catalyst can be proceed effectively under relatively high pressure of H<sub>2</sub>. These results are consistent with the low H<sub>2</sub> uptake of bimetallic Ni-Sn(1.5)/TiO<sub>2</sub>.

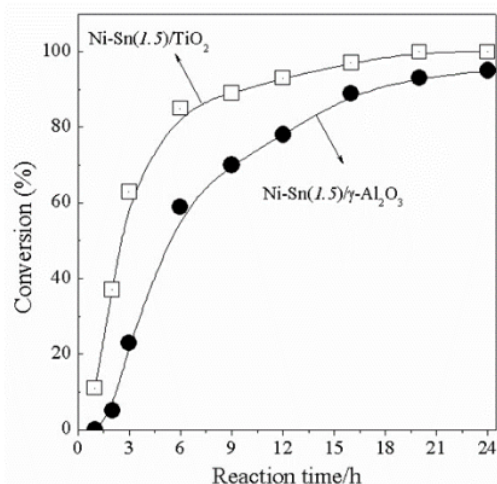

**Figure 5.** Kinetics of the hydrogenation of dodecanoic acid over bimetallic Ni-Sn(1.5)/TiO<sub>2</sub> and Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts. Reaction conditions: Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; iso-PrOH, 5 mL, 160 °C; H<sub>2</sub> pressure 30 bar, reaction time is 1-24 h



#### 4. Conclusion


Selective hydrogenation of dodecanoic acid into dodecane-1-ol over supported bimetallic Ni-Sn alloy catalysts is demonstrated. Bimetallic Ni-Sn(1.5)/TiO<sub>2</sub> catalyst was found to be effective for hydrogenation of dodecanoic acid (>99 % conversion) to dodecane-1-ol (93 % yield) at 160 °C, 30 bar H<sub>2</sub>, and 20 h and the highest dodecane-1-ol (97 % yield) was obtained at initial pressure of H<sub>2</sub> 50 bar. An increase of reaction temperature slightly enhanced the degree of hydrodeoxygenation of dodecanoic acid to produce dodecane over both Ni-Sn(1.5)/TiO<sub>2</sub> and Ni-Sn(1.5)/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts.

#### Acknowledgments


These works were financially supported by BPDP-Sawit, Ministry of Finances through GRK-2016 under contract number PRJ-49/2016. Partial these works were supported by Insentif Riset Pratama Individu (IRPI) FY 2016-2017 and International Publication Project of DGHE FY 2016 under Grant Number of DIPA-023-04.1.673453/2016 (XRD and ICP-AES measurements). We would also like thank to Dr. Husni Wahyu Wijaya for kind assistance in NH<sub>3</sub>-TPD measurements.

#### References

- [1] Biermann, U., Bornscheuer, U., Meier, M.A.R., Metzger, J.O., Schafer, H.J. (2011). Oils and Fats as Renewable Raw Materials in Chemistry. *Angew. Chem., Int. Ed.* 50: 3854-3871.
- [2] Turek, T., Trimm, D.L., Cant, N.W. (1994). The Catalytic Hydrogenolysis of Esters to Alcohols. *Catal. Rev. Sci. Eng.* 36: 645-683.
- [3] Adkins, H., Connor, R. (1931). The Catalytic Hydrogenation of Organic Compounds over Copper Chromite. *J. Am. Chem. Soc.* 53: 1091-1095.
- [4] Rozmyslowicz, B., Kirilin, A., Aho, A., Manyar, H.G., Hardacre, C., Warna, J., Salmi, T., Murzin, D.Y. (2015). Selective Hydrogenation of Fatty Acids to Alcohols over Highly Dispersed ReO<sub>x</sub>/TiO<sub>2</sub> Catalyst. *J. Catal.* 328: 197-207.
- [5] Manyar, H.G., Paun, C., Rilus, R., Rooney, D.W., Thompson, J.M., Hardacre, C. (2010). Highly Selective and Efficient Hydrogenation of Carboxylic Acids to Alcohols using Titania Supported Pt Catalysts. *Chem. Commun.* 46: 6279-6281.
- [6] Gallezot, P., Cerino, P.J., Blanc, B., Flèche, G., Fuertes, P. (1994). Glucose Hydrogenation on Promoted Raney-nickel Catalysts. *J. Catal.* 46: 93-102.

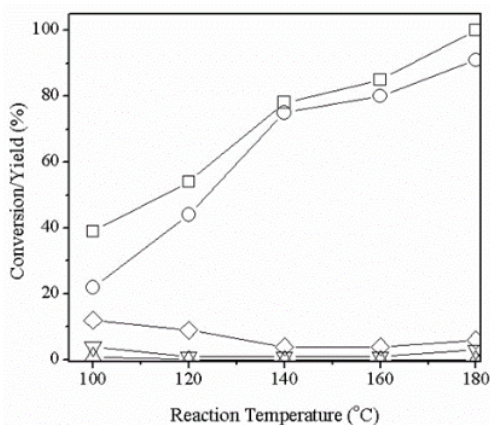

**Figure 6.** Results of dodecanoic acid hydrogenation over Ni-Sn(1.5)/TiO<sub>2</sub> at different reaction temperature. *Reaction conditions:* Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL; reaction temperature, 100-180 °C; H<sub>2</sub> pressure 30 bar; reaction time is 6 h. (□) Conversion of dodecanoic acid. (○) Yield of dodecane-1-ol. (△) Yield of dodecane-1,1-diol, and (▽) Yield of dodecane. (◇) Other products.

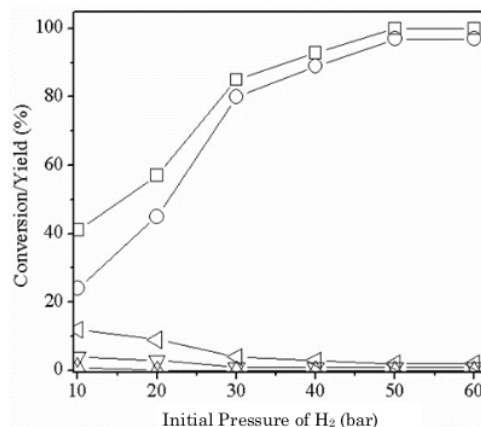

**Figure 7.** Results of dodecanoic acid hydrogenation over Ni-Sn(1.5)/TiO<sub>2</sub> at different initial pressure of H<sub>2</sub>. *Reaction conditions:* Catalyst, 0.065 g; dodecanoic acid, 3.2 mmol; *iso*-PrOH, 5 mL, 160 °C; H<sub>2</sub> pressure 10-50 bar; reaction time is 6 h. (□) Conversion of dodecanoic acid. (○) Yield of dodecane-1-ol. (△) Yield of dodecane-1,1-diol, and (▽) Yield of dodecane. (◇) Other products.

- [7] Alonso, D.M., Wettstein, S.G., Dumesic, J.A. (2012). Bimetallic Catalysts for Upgrading of Biomass to Fuels and Chemicals. *Chem. Soc. Rev.* 41: 8075-8098.
- [8] Pritchard, J., Filonenko, G.A., van Putten, R., Hensen, E.J.M., Pidko, E.A. (2015). Heterogeneous and Homogeneous Catalysis for the Hydrogenation of Carboxylic Acid Derivatives: History, Advances and Future Directions, *Chem. Soc. Rev.* 44: 3808-3833.
- [9] Besson, M., Gallezot, P., Pine, C. (2014). Conversion of Biomass into Chemicals over Metal Catalysts. *Chem. Rev.* 114: 1827-1870.
- [10] Huang, C., Zhang, H., Zhao, Y., Chen, S., Liu, Z. (2012). Diatomite-supported Pd-M (M = Cu, Co, Ni) Bimetal Nanocatalysts for Selective Hydrogenation of Long-chain Aliphatic Esters. *J. Coll. Interface Sci.* 386: 60-65.
- [11] Shao, Y., Xia, Q., Liu, X., Lu, G., Wang, Y. (2015). Pd/Nb<sub>2</sub>O<sub>5</sub>/SiO<sub>2</sub> Catalyst for the Direct Hydrodeoxygenation of Biomass-related Compounds to Liquid Alkanes under Mild Conditions. *ChemSusChem.* 8: 1761-1767.
- [12] Miyake, T., Makino, T., Taniguchi, S. I., Watanuki, H., Niki, T., Shimizu, S., Kojima, Y., Sano, M. (2009). Alcohol Synthesis by Hydrogenation of Fatty Acid Methyl Esters on Supported Ru-Sn and Rh-Sn Catalysts. *Appl. Catal. A.* 364: 108-112.
- [13] Deshpande, V. M., Patterson, W. R., Narasimhan, C. S. (1990). Studies on Ruthenium-tin Boride Catalysts I. Characterization. *J. Catal.* 121: 165-173.
- [14] Deshpande, V.M., Ramnarayan, K., Narasimhan, C.S. (1990). Studies on Ruthenium-tin Boride Catalysts II. Hydrogenation of Fatty Acid Esters to Fatty Alcohols. *J. Catal.* 21: 174-182.
- [15] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2012). Highly Efficient and Selective Hydrogenation of Unsaturated Carbonyl Compounds using Ni-Sn Alloy Catalysts. *Catal. Sci. Technol.* 2: 2139-2145.
- [16] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2012). A Novel Preparation Method of Ni-Sn Alloy Catalysts Supported on Aluminium Hydroxide: Application to Chemoselective Hydrogenation of Unsaturated Carbonyl Compounds. *Catal. Lett.* 41(8): 769-771.
- [17] Rodiansono, R., Hara, T., Ichikuni, N., Shimazu, S. (2014). Development of Nanoporous Ni-Sn Alloy and Application for Chemoselective Hydrogenation of Furfural to Furfuryl Alcohol. *Bull. Chem. React. Eng. Catal.* 9(1): 53-59
- [18] Rodiansono, R., Ghofur, A., Astuti, M.D., Sembiring, K.C. (2015). Catalytic Hydrogenation of Levulinic Acid in Water into  $\gamma$ -Valerolactone over Bulk Structure of Inexpensive Intermetallic Ni-Sn Alloy Catalysts. *Bull. Chem. React. Eng. Catal.* 10(2): 192-200.
- [19] Rodiansono, R., Astuti, M.D., Hara, T., Ichikuni, N., Shimazu, S. (2016). Efficient Hydrogenation of Levulinic Acid in Water using a Supported Ni-Sn Alloy on Aluminium Hydroxide Catalysts. *Catal. Sci. Technol.* 6: 2955-2961.
- [20] Lowell, S., Shields, J. E., Thomas, M. A., Thommes, M. (2004). *Characterization of Porous Solids and Powders: Surface Area, Pore Size and Density*, Kluwer Academic Publishers, Netherlands, Chapter 8.
- [21] Bartholomew, C.H., Pannel, R.B., Butler, J.L. (1980). Support and Crystallite Size Effects in CO Hydrogenation on Nickel. *J. Catal.* 65: 335-347.
- [22] Bartholomew, C.H., Pannel, R.B. (1980). The Stoichiometry of Hydrogen and Carbon Monoxide Chemisorption on Alumina- and Silica-supported Nickel. *J. Catal.* 65: 390-401.
- [23] Rodiansono, R., Astuti, M.D., Khairi, S., Shimazu, S. (2016). Selective Hydrogenation of Biomass-derived Furfural over Supported Ni<sub>3</sub>Sn<sub>2</sub> Alloy: Role of Supports. *Bull. Chem. React. Eng. Catal.* 11(1): 1-9.
- [24] Powder Diffraction File, JCPDS-International Center for Diffraction Data (ICDD), 1991.
- [25] Dumitriu, E., Hulea, V.J. (2003) Effects of Channel Structures and Acid Properties of Large Pore Zeolites in the Liquid Phase Tert-butylation of Phenol. *J. Catal.* 218: 249-257.
- [26] Khandan, N., Kazemeini, M., Aghaziarati, M. (2008). Determining an Optimum Catalyst for Liquid Phase Dehydration of Methanol to Dimethyl Ether. *J. Appl. Catal. A.* 349: 6-12.
- [27] Dandekar, A., Vannice, M.A. (1999). Crotonaldehyde Hydrogenation on Pt/TiO<sub>2</sub> and Ni/TiO<sub>2</sub> SMSI Catalysts. *J. Catal.* 183: 344-354.
- [28] Sordelli, L., Psaro, R., Vlaic, G., Cepparo, A., Recchia, S., Fusi, A., Zanoni, R. (1999). EXAFS Studies of Supported Rh-Sn Catalysts for Citral Hydrogenation. *J. Catal.* 182: 186-198.
- [29] Margitfalvi, J. L., Tompos, A., Kolosova, I., Valyon, J. (1998). Reaction Induced Selectivity Improvement in the Hydrogenation of Crotonaldehyde over Sn-Pt/SiO<sub>2</sub> Catalysts. *J. Catal.* 174: 246-249.

# Selective Hydrogenation of Dodecanoic Acid to Dodecane-1-ol Catalyzed by Supported Bimetallic Ni-Sn Alloy

## ORIGINALITY REPORT

19%

SIMILARITY INDEX

12%

INTERNET SOURCES

16%

PUBLICATIONS

1%

STUDENT PAPERS

## PRIMARY SOURCES

- 1** [www.ncbi.nlm.nih.gov](http://www.ncbi.nlm.nih.gov) 2%  
Internet Source
- 2** Nobutaka Yamanaka, Takayoshi Hara, Nobuyuki Ichikuni, Shogo Shimazu. "Chemoselective Hydrogenation of Unsaturated Nitro Compounds to Unsaturated Amines by Ni-Sn Alloy Catalysts", *Chemistry Letters*, 2018 2%  
Publication
- 3** Wahyu S. Putro, Takashi Kojima, Takayoshi Hara, Nobuyuki Ichikuni, Shogo Shimazu. "Selective hydrogenation of unsaturated carbonyls by Ni-Fe-based alloy catalysts", *Catal. Sci. Technol.*, 2017 1%  
Publication
- 4** Wahyu Satpriyo Putro, Takashi Kojima, Takayoshi Hara, Nobuyuki Ichikuni, Shogo Shimazu. "Selective hydrogenation of unsaturated carbonyls by Ni-Fe based alloy catalysts", *Catal. Sci. Technol.*, 2017 1%  
Publication

---

5	<a href="http://pure.tue.nl">pure.tue.nl</a> Internet Source	1 %
6	Changming Li, Yudi Chen, Shitong Zhang, Simin Xu, Junyao Zhou, Fei Wang, Min Wei, David G. Evans, Xue Duan. "Ni-In Intermetallic Nanocrystals as Efficient Catalysts toward Unsaturated Aldehydes Hydrogenation", <i>Chemistry of Materials</i> , 2013 Publication	1 %
7	<a href="http://coek.info">coek.info</a> Internet Source	1 %
8	<a href="http://www.mdpi.com">www.mdpi.com</a> Internet Source	1 %
9	Michèle Besson, Pierre Gallezot, Catherine Pinel. "Conversion of Biomass into Chemicals over Metal Catalysts", <i>Chemical Reviews</i> , 2013 Publication	1 %
10	Hara, Takayoshi, Masakazu Ishikawa, Junya Sawada, Nobuyuki Ichikuni, and Shogo Shimazu. "Creation of highly stable monomeric Pd(II) species in an anion-exchangeable hydroxy double salt interlayer: Application to aerobic alcohol oxidation under an air atmosphere", <i>Green Chemistry</i> , 2009. Publication	1 %
11	<a href="http://epdf.tips">epdf.tips</a> Internet Source	1 %

---

---

12 Park, S.J.. "KOH activation and characterization of glass fibers-supported phenolic resin", Journal of Colloid And Interface Science, 20030915

Publication

1 %

---

13 Elena Selishcheva, Jürgen Parisi, Joanna Kolny-Olesiak. "Copper-assisted shape control in colloidal synthesis of indium oxide nanoparticles", Journal of Nanoparticle Research, 2012

Publication

<1 %

---

14 [link.springer.com](http://link.springer.com)

Internet Source

<1 %

---

15 Kim, B.J.. "Optimization of the pore structure of nickel/graphite hybrid materials for hydrogen storage", International Journal of Hydrogen Energy, 201101

Publication

<1 %

---

16 [ebin.pub](http://ebin.pub)

Internet Source

<1 %

---

17 Zihao Zhang, Feng Zhou, Kequan Chen, Jie Fu, Xiuyang Lu, Pingkai Ouyang. " Catalytic Hydrogenation of Fatty Acids into Fatty Alcohols over Cu-Based Catalysts with Methanol in Hydrothermal Media ", Energy & Fuels, 2017

Publication

<1 %

---

18 SATYANARAYANA MURTY PUDI, ABDUL ZOEB, PRAKASH BISWAS, SHASHI KUMAR. "Liquid phase conversion of Glycerol to Propanediol over highly active Copper/Magnesia catalysts", Journal of Chemical Sciences, 2015  
Publication <1 %

---

19 Submitted to Nazarbayev University  
Student Paper <1 %

---

20 [uvadoc.uva.es](http://uvadoc.uva.es)  
Internet Source <1 %

---

21 Tepin Hengsawad, Chayasari Srimingkwanchai, Suchada Butnark, Daniel E. Resasco, Siriporn Jongpatiwut. "Effect of Metal-Acid Balance on Hydroprocessed Renewable Jet Fuel Synthesis from Hydrocracking and Hydroisomerization of Bio-hydrogenated Diesel over Pt-supported Catalysts", Industrial & Engineering Chemistry Research, 2018  
Publication <1 %

---

22 [www.science.gov](http://www.science.gov)  
Internet Source <1 %

---

23 [www.rsc.org](http://www.rsc.org)  
Internet Source <1 %

---

24 Tingshun Jiang, Yingjie Xie, Liming Dai, Yingying Li, Qian Zhao. "Alkylation of phenol <1 %

with tert-butyl alcohol catalyzed by ionic liquid-supported MCM-41 with different pore sizes", Reaction Kinetics, Mechanisms and Catalysis, 2018

Publication

---

25

Duraiswami Divakar. "Vapor-phase selective hydrogenation of citral over Pd/bentonite: effect of reduction method", Journal of Chemical Technology & Biotechnology, 10/2008

Publication

---

<1 %

26

John Keogh, Manishkumar S. Tiwari, Haresh Manyar. "Esterification of Glycerol with Acetic Acid Using Nitrogen-Based Brønsted-Acidic Ionic Liquids", Industrial & Engineering Chemistry Research, 2019

Publication

---

<1 %

27

Ling Xu, Renfeng Nie, Xilei Lyu, Juncheng Wang, Xiuyang Lu. "Selective hydrogenation of furfural to furfuryl alcohol without external hydrogen over N-doped carbon confined Co catalysts", Fuel Processing Technology, 2020

Publication

---

<1 %

28

Hui Li. "Ultrasound-assisted Cinnamaldehyde Hydrogenation to Cinnamyl Alcohol at Atmospheric Pressure over Ru-B Amorphous Catalyst", Chinese Journal of Chemistry, 05/2006

Publication

<1 %

---

29 James Pritchard, Aysegul Ciftci, M.W.G.M. (Tiny) Verhoeven, Emiel J.M. Hensen, Evgeny A. Pidko. "Supported Pt-Re catalysts for the selective hydrogenation of methyl and ethyl esters to alcohols", *Catalysis Today*, 2017  
Publication <1 %

---

30 Vidya Sagar Guggilla, Jale Akyurtlu, Ates Akyurtlu, Isaiah Blankson. " Steam Reforming of -Dodecane over Ru–Ni-Based Catalysts ", *Industrial & Engineering Chemistry Research*, 2010  
Publication <1 %

---

31 Zhihao Yu, Xuebin Lu, Chen Liu, Yiwen Han, Na Ji. "Synthesis of  $\gamma$ -valerolactone from different biomass-derived feedstocks: Recent advances on reaction mechanisms and catalytic systems", *Renewable and Sustainable Energy Reviews*, 2019  
Publication <1 %

---

32 [www.doria.fi](http://www.doria.fi)  
Internet Source <1 %

---

33 "Chemical Catalysts for Biomass Upgrading", *Wiley*, 2020  
Publication <1 %

---

34 "Modern Surface Organometallic Chemistry", *Wiley*, 2009  
Publication <1 %

---



35

Ibrahim Salem. "Recent Studies on the Catalytic Activity of Titanium, Zirconium, and Hafnium Oxides", *Catalysis Reviews*, 2003

Publication

<1 %

36

James D. Kammert, Ashwin Chemburkar, Naomi Miyake, Matthew Neurock, Robert J. Davis. " Reaction Kinetics and Mechanism for the Catalytic Reduction of Propionic Acid over Supported ReO Promoted by Pd ", *ACS Catalysis*, 2021

Publication

<1 %

37

Yuanyuan Zhao, Takayuki Nishida, Eiji Minami, Shiro Saka, Haruo Kawamoto. "TiO<sub>2</sub>-supported Ni-Sn as an effective hydrogenation catalyst for aqueous acetic acid to ethanol", *Energy Reports*, 2020

Publication

<1 %

38

[etheses.bham.ac.uk](https://theses.bham.ac.uk)

Internet Source

<1 %

39

[moam.info](https://moam.info)

Internet Source

<1 %

40

Freddy E. Oropeza, Bastian Mei, Ilia Sinev, Ahmet E. Becerikli, Martin Muhler, Jennifer Strunk. "Effect of Sn surface states on the photocatalytic activity of anatase TiO<sub>2</sub>", *Applied Catalysis B: Environmental*, 2013

Publication

<1 %

41

Deepak S. Thakur, Arunabha Kundu.  
"Catalysts for Fatty Alcohol Production from  
Renewable Resources", Journal of the  
American Oil Chemists' Society, 2016

Publication

---

<1 %

42

Huang, Changliang, Hongye Zhang, Yanfei  
Zhao, Sha Chen, and Zhimin Liu. "Diatomite-  
supported Pd-M (M=Cu, Co, Ni) bimetal  
nanocatalysts for selective hydrogenation of  
long-chain aliphatic esters", Journal of Colloid  
and Interface Science, 2012.

Publication

---

<1 %

---

Exclude quotes      On

Exclude matches      Off

Exclude bibliography      On